



DX

Marginally lubricated

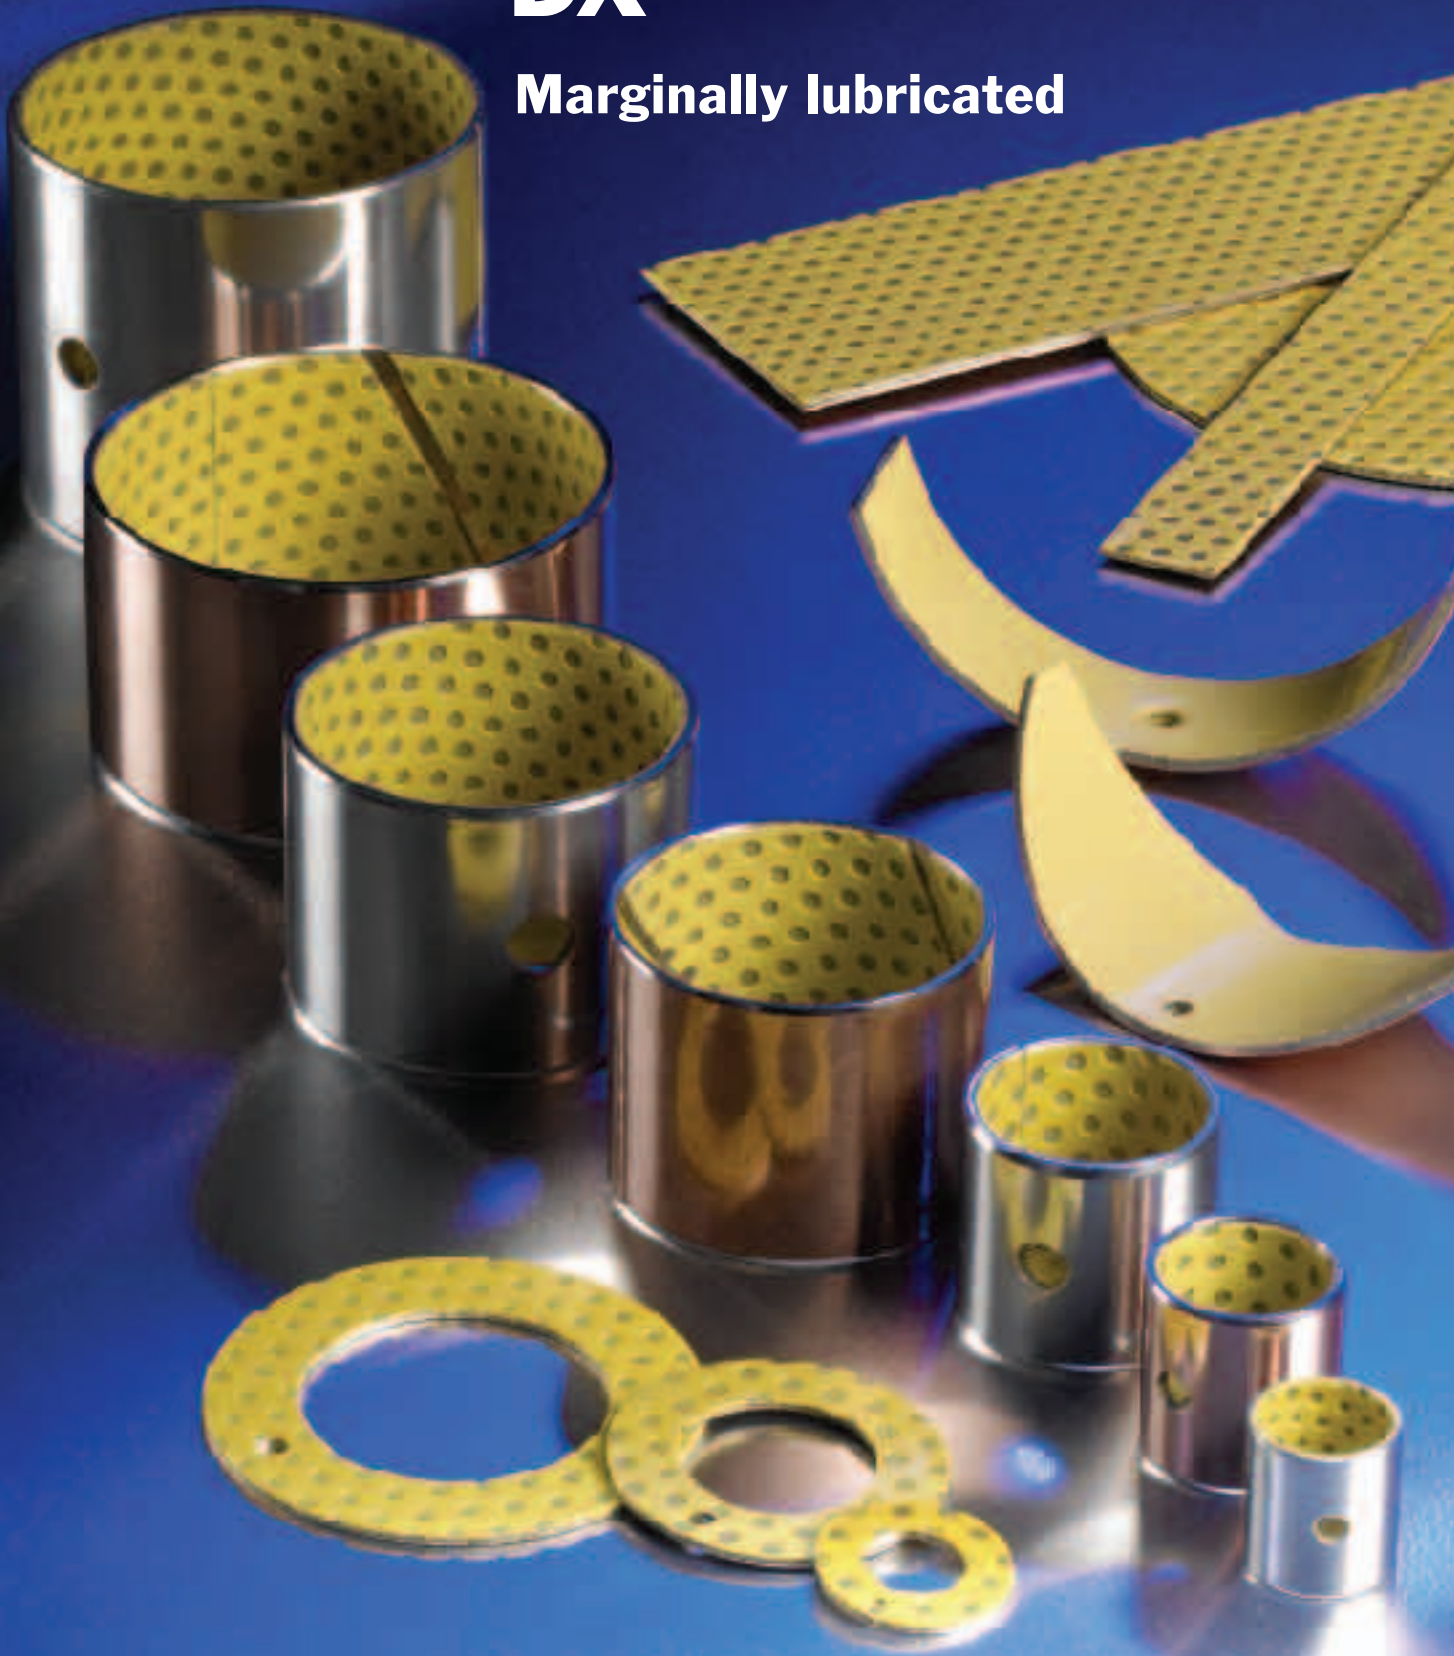

Quality

All the products described in this handbook are manufactured under DIN ISO 9001/2 or TS 16949 approved quality management systems.



ZERTIFIKAT

Die
DQS GmbH
Deutsche Gesellschaft zur Zertifizierung von Managementsystemen
bescheinigt hiermit, dass das Unternehmen

GGB GERMANY GMBH & CO. KG
Ochsenbunnenstraße 9
D-74078 Heilbronn

für den Geltungsbereich
Herstellung und Vertrieb von Getrieben für die Automobilindustrie
und andere industrielle Anwendungsbereiche mit Entwicklung bei
GGB France E.U.R.L. in Anney, Frankreich.

ein
Qualitätsmanagementsystem
eingeführt hat und anwendet.

Durch ein Audit, dokumentiert in einem Bericht, wurde in Übereinstimmung mit den Zertifizierungsregeln der Automobilindustrie für ISO/TS 16949:2002 der Nachweis erbracht, dass dieses Qualitätsmanagementsystem die Forderungen der folgenden Technischen Spezifikationen einschließlich ISO 9001:2000 erfüllt.


ISO/TS 16949:2002
2. Ausgabe März 2002

inkl. Produktüberwachung

Zertifizierungsaudit	2004-02-09 - 2004-02-13
Zertifizierungsgenehmigung	2005-03-07
Dieses Zertifikat ist gültig bis	2007-03-11
Zertifikat-Registrier-Nr.	062772 152/25253
Frankfurt am Main	2005-03-07

Anw. Nr. M. Dreier *M. Dreier* Dir. Ing. S. Henning *S. Henning*
GESCHÄFTSFÜHRER

D-60433 Frankfurt am Main, August-Solano-Straße 21
(Tel.: +49 69 95 42 70)



CERTIFICAT

N° TS/2003/21286
N° IATF : 0017381

GLACIER GARLOCK BEARINGS

pour les activités suivantes:
for the following activities:

**CONCEPTION, INDUSTRIALISATION, FABRICATION ET VENTE
DE SYSTEMES ANTI-FRICTION.**

**INDUSTRIALISATION, FABRICATION ET VENTE
DE PALIERS DE POMPES HYDRAULIQUES A ENGRENAGES.**

**DESIGN, DEVELOPMENT, MANUFACTURING AND SALES
OF ANTI-FRICTION SYSTEMS.**

**DEVELOPMENT, MANUFACTURING AND SALES
OF HYDRAULIC GEAR PUMP BEARINGS BLOCKS.**

exercées sur le site(s) suivant(s):
exercised on the following location(s):

65, chemin de la prairie BP n°2074 F-74009 ANNECY
Route de Saint-Avoird Zone Industrielle F-57260 DIEUZE
22-28, rue Henri Barbusse F-62110 CLICHY
(Liste des sites en annexes n° 1 à n° 2)
(List of locations on appendices n° 1 to n° 2)

ISO/TS 16949 : 2002


2003-11-07

2006-11-06

Le Président du Comité de Certification *M. Fondévoile* Le Directeur Général d'AF AQ *O. Peyrat* Le Responsable du Bureau *J. Zattaj*

M. FONDEVOLE O. PEYRAT J. ZATTAJ

AF AQ - 116, AVENUE INDUSTRIELLE BRUNO - BP 441 - 14000 METROPOLITAIN CESSY FRANCE



Glacier Garlock Bearings, LLC

700 Mid Atlantic Parkway
Thorofare, NJ 08086

Underwriters Laboratories Inc.® (UL), MetLife, NY, USA, issues this certificate to the Firm named above (and where applicable in the annex(es) to this certificate), after assessing the Firm's quality system and finding it in compliance with ISO/TS 16949:2002.

ISO/TS 16949: 2002

Having been audited in accordance with the "Rules for the registration scheme for ISO/TS 16949:2002 - First edition", for the following scope of registration

3542 (US): Ball and Roller Bearings
The design and manufacture of steel-backed bearings. The design and manufacture of filament wound bearings and washers.

The remote location at Ochsenbunnenstrasse 9, D-74078 Heilbronn, Germany performs the following primary functions: sales to Visteon (Europe).


Exclusions: None


This quality system registration is included in UL's Directory of Registered Firms and applies to the provision of goods and/or services as specified in the scope of registration from the address(es) shown above. By issuance of this certificate the firm represents that it will maintain its registration in accordance with the applicable requirements. This certificate is not transferable and remains the property of Underwriters Laboratories Inc.®.

File Number: A4360
Volume: 2 of 2
Page 1 of 3
ISO/TS 16949:2002 Issue Date: October 23, 2004
Revision Date: October 23, 2004
Renewal Date: October 22, 2007

S. Joe Shatta
S. Joe Shatta
Executive Vice President, International

Certificate Number 0028621





ZERTIFIKAT

Die
DQS GmbH
Deutsche Gesellschaft zur Zertifizierung von Managementsystemen
bescheinigt hiermit, dass das Unternehmen

GGB GERMANY GMBH & CO. KG
Ochsenbunnenstraße 9
D-74078 Heilbronn

für den Geltungsbereich
Herstellung und Vertrieb von Getrieben für die Automobilindustrie
und andere industrielle Anwendungsbereiche mit Entwicklung bei
GGB France E.U.R.L. in Anney, Frankreich.

ein
Umweltmanagementsystem
eingeführt hat und anwendet.

Durch ein Audit, dokumentiert in einem Bericht, wurde der Nachweis erbracht, dass dieses Umweltmanagementsystem die Forderungen der folgenden Norm erfüllt:

DIN EN ISO 14001 : 2005
Ausgabe November 2004


Dieses Zertifikat ist gültig bis 2007-03-11

Zertifikat-Registrier-Nr. 062772 UM

Frankfurt am Main 2005-03-03

Anw. Nr. M. Dreier *M. Dreier* Dir. Ing. S. Henning *S. Henning*
GESCHÄFTSFÜHRER

D-60433 Frankfurt am Main, August Solano Straße 21
(Tel.: +49 69 95 42 70)



CERTIFICATION

N° ENV/2003/21538

Le Système de Management Environnemental adopté par:
The Environmental Management System developed by:

GLACIER GARLOCK BEARINGS

pour les activités suivantes:
for the following activities:

**INDUSTRIALISATION, FABRICATION ET VENTE
DE SYSTEMES ANTI-FRICTION.**

**INDUSTRIALIZATION, MANUFACTURING AND SALES
OF ANTI-FRICTION SYSTEMS.**

exercées sur le site(s) suivant(s):
exercised on the following location(s):

65, chemin de la prairie BP n°2074 F-74009 ANNECY
22/28, rue Henri Barbusse F-62110 CLICHY

a été évalué et jugé conforme aux exigences de la norme:
has been assessed and found to conform to the requirements of the standard:

ISO 14001 (1996)


2003-12-29

2006-12-28

Le Président du Comité de Certification *P. Schwartzmann* Le Directeur Général d'AF AQ *O. Peyrat* Le Responsable du Bureau *J. Zattaj*

P. SCHWARTZMANN O. PEYRAT J. ZATTAJ

AF AQ - 116, AVENUE INDUSTRIELLE BRUNO - BP 441 - 14000 METROPOLITAIN CESSY FRANCE



GGB LLC

P.O. Box 189
700 Mid-Atlantic Parkway
Thorofare, NJ 08086

Web Site: 1451 Metropolitan Avenue
Thorofare, New Jersey 08086
U.S.A.

Underwriters Laboratories Inc.® (UL) issues this certificate to the Firm named above, after assessing the Firm's environmental management system and finding it in compliance with ISO 14001:1996.

ISO 14001:1996
ENVIRONMENTAL MANAGEMENT SYSTEM

for the following scope of registration


The environmental management system of GGB LLC associated with the design and manufacture of self-lubricated metal back bearings at 700 Mid-Atlantic Parkway, Thorofare, New Jersey, U.S.A.

The remote location at 1451 Metropolitan Avenue, Thorofare, New Jersey, U.S.A., performs the following primary functions: the manufacture of filament-wound self-lubricating bearings.

This environmental management system registration is included in UL's Directory of Registered Firms and applies to the operations of the address(es) shown above. By issuance of this certificate the firm represents that it will maintain its registration in accordance with the applicable requirements. This certificate is not transferable and remains the property of Underwriters Laboratories Inc.®.

File Number: A12129
Volume: 1
Original Certification Date: October 31, 2003
ISO 14001 Issue Date: October 31, 2003
Revision Date: October 6, 2004
Renewal Date: October 30, 2008

S. Joe Shatta
S. Joe Shatta
Executive Vice President, International



Formula Symbols and Designations

Formula Symbol	Unit	Designation
a_B	-	Bearing size factor
a_E	-	High load factor
a_Q	-	Speed/Load factor
a_S	-	Surface finish factor
a_T	-	Temperature application factor
B	mm	Nominal bush width
C	1/min	Dynamic load frequency
C_D	mm	Installed diametral clearance
C_{Dm}	mm	Diametral clearance machined
C_T	-	Total number of dynamic load cycles
C_i	mm	ID chamfer length
C_o	mm	OD chamfer length
D_H	mm	Housing Diameter
D_i	mm	Nominal bush/thrust washer ID
$D_{i,a}$	mm	Bush ID when assembled in housing
$D_{i,a,m}$	mm	Bush ID assembled and machined
D_J	mm	Shaft diameter
D_o	mm	Nominal bush/thrust washer OD
d_D	mm	Dowel hole diameter
d_L	mm	Oil hole diameter
d_p	mm	Pitch circle diameter for dowel hole
F	N	Bearing load
F_i	N	Insertion force
f	-	Friction
H_a	mm	Depth of Housing Recess (e.g. for thrust washers)
H_d	mm	Diameter of Housing Recess (thrust washers)
L	mm	Strip length
L_H	h	Bearing service life
L_{RG}	h	Relubrication interval
N	1/min	Rotational speed
N_{osz}	1/min	Oscillating movement frequency

Formula Symbol	Unit	Designation
\bar{p}	N/mm ²	Specific load
\bar{p}_{lim}	N/mm ²	Specific load limit
$\bar{p}_{sta,max}$	N/mm ²	Maximum static load
$\bar{p}_{dyn,max}$	N/mm ²	Maximum dynamic load
Q	-	Total number of cycles
R	-	Number of lubrication intervals
R_a	μm	Surface roughness (DIN 4768, ISO/DIN 4287/1)
s_3	mm	Bush wall thickness
s_S	mm	Strip thickness
s_T	mm	Thrust washer thickness
T	°C	Temperature
T_{amb}	°C	Ambient temperature
T_{max}	°C	Maximum temperature
T_{min}	°C	Minimum temperature
U	m/s	Sliding speed
u	-	speed factor
W	mm	Strip width
W_u	mm	Maximum usable strip width
α_1	1/10 ⁶ K	Coefficient of linear thermal expansion parallel to surface
α_2	1/10 ⁶ K	Coefficient of linear thermal expansion normal to surface
σ_c	N/mm ²	Compressive Yield strength
λ	W/mK	Thermal conductivity
ϕ	°	Angular displacement
η	Ns/mm ²	Dynamic Viscosity
Z_T	-	Total number of oscillating movements

Content

Quality	I	6 Data Sheet	21
Formula Symbols and Designations	II	6.1 Data for bearing design calculations	21
1 Introduction	4	7 Bearing Assembly	22
1.1 Characteristics and Advantages	4	7.1 Dimensions and Tolerances ..	22
2 Structure	5	7.2 Tolerances for minimum clearance	22
2.1 Basic Forms	5	Grease lubrication	22
3 Properties	6	Fluid Lubrication	24
3.1 Physical Properties	6	Allowance for Thermal Expansion	24
3.2 Chemical Properties	6	7.3 Counterface Design	25
4 Lubrication	7	7.4 Installation	26
4.1 Choice of Lubricant	7	Fitting of Bushes	26
4.2 Friction	9	Insertion Forces	26
4.3 Lubricated Environments	9	Alignment	27
Lubrication	9	Sealing	27
4.4 Characteristics of Fluid Lubricated DX Bearings	10	Axial Location	27
4.5 Design Guidance for Fluid Lubricated Applications	10	Fitting of Thrust Washers	27
4.6 Wear Rate and Relubrication Intervals with Grease lubrication	12	Slideways	28
Fretting Wear	12	8 Machining	29
5 Design Factors	13	8.1 Machining Practice	29
5.1 Specific Load	13	8.2 Boring	29
Specific Load Limit	13	8.3 Reaming	30
5.2 Sliding Speed	14	8.4 Broaching	30
Continuous Rotation	14	8.5 Vibrobroaching	31
Oscillating Movement	14	8.6 Modification of components ..	31
5.3 pU Factor	15	8.7 Drilling Oil Holes	31
5.4 Load	15	8.8 Cutting Strip Material	31
Type of Load	15	9 Electroplating	32
5.5 Temperature	17	DX Components	32
5.6 Mating Surface	17	Mating Surfaces	32
5.7 Bearing Size	18	10 Standard Products	33
5.8 Estimation of Bearing Service Life with Grease Lubrication ..	18	10.1 PM-DX cylindrical bushes	33
Calculation Parameters	18	10.2 MB-DX cylindrical bushes	40
Estimate Bearing Life	19	10.3 Inch DX cylindrical bushes ...	45
Estimate Re-greasing Interval ..	19	10.4 DX Thrust Washers - metric ..	48
Oscillating Motion	19	10.5 DX Thrust Washers - inch	49
Dynamic Loads	19	10.6 DX Strip - metric	50
5.9 Worked Examples	20	10.7 DX Strip - inch	50

1 Introduction

The purpose of this handbook is to provide comprehensive technical information on the characteristics of DX bearings. The information given, permits designers to establish the correct size of bearing required and the expected life and performance. GGB Research and Development services are available to assist with unusual design problems.

Complete information on the range of DX standard stock products is given together with details of other DX products.

GGB is continually refining and extending its experimental and theoretical knowledge and, therefore, when using this brochure it is always worthwhile to contact the Company should additional information be required.

Customers are advised to carry out prototype testing wherever possible.

1.1 Characteristics and Advantages

- **DX provides maintenance free operation**
- **DX has a high pU capability**
- **DX exhibits low wear rate**
- **Seizure resistant**
- **Suitable for temperatures from -40 to +120 °C**
- **High static and dynamic load capacity**
- **Good frictional properties**
- **No water absorption and therefore dimensionally stable**
- **Compact and light**
- **Suitable for rotating, oscillating, reciprocating and sliding movements**
- **DX bearings are prefinished and require no machining after assembly**

2 Structure

DX is a composite bearing material developed specifically to operate with marginal lubrication and consists of three bonded layers: a steel backing strip and a sintered porous bronze matrix, impregnated and overlaid with a pigmented acetal copolymer bearing material.

The steel backing provides mechanical strength and the bronze interlayer provides a strong mechanical bond for the lining. This construction promotes dimensional stability and improves thermal conductivity, thus reducing the temperature at the bearing surface.

DX is designed for use with grease lubrication and the bearing surface is normally

provided with a uniform pattern of indents. These serve as a reservoir for the grease and are designed to provide the optimum distribution of the lubricant over the bearing surface.



Fig. 1: DX-microsection

2.1 Basic Forms

Standard Components available from stock

These products are manufactured to International, National or GGB standard designs.

Metric and Imperial Sizes

- Cylindrical Bushes
 - PM pre finished metric range, not machinable in situ, for use with standard journals finished to h6-h8 limits.
 - MB machinable metric range, with an allowance for machining in situ.
- Machinable inch range for use as supplied or after machining in situ.
- Thrust Washers
- Strip Material



Fig. 2: Standard components

Non Standard Components not available from stock

These products are manufactured to customers' requirements with or without GGB recommendations, and include for example

- Modified Standard Components
- Half Bearings
- Flat Components
- Pressings
- Stampings



Fig. 3: Non standard components

3 Properties

3.1 Physical Properties

	Characteristic	Symbol	Value DX	Unit	Comments
Physical Properties	Thermal Conductivity	λ	52	W/mK	
	Coefficient of linear thermal expansion :				
	parallel to surface	α_1	11	1/10 ⁶ K	
	normal to surface	α_2	29	1/10 ⁶ K	
	Maximum Operating Temperature	T_{max}	120	°C	
	Minimum Operating Temperature	T_{min}	-40	°C	
Mechanical Properties	Compressive Yield Strength	σ_c	380	N/mm ²	measured on disc 5 mm diameter x 2.45 mm thick.
	Maximum Load				
	Static	$\bar{\rho}_{sta,max}$	140	N/mm ²	
	Dynamic	$\bar{\rho}_{dyn,max}$	70	N/mm ²	
Electrical Properties	Volume resistivity of acetal lining		10 ¹⁵	Ω cm	

Table 1: Properties of DX

3.2 Chemical Properties

The following table provides an indication of the resistance of DX to various chemical media. It is recommended that the chemi-

cal resistance is confirmed by testing if possible.

+	Satisfactory: Corrosion damage is unlikely to occur.
o	Acceptable: Some corrosion damage may occur but this will not be sufficient to impair either the structural integrity or the tribological performance of the material.
-	Unsatisfactory: Corrosion damage will occur and is likely to affect either the structural integrity and/or the tribological performance of the material.

	Chemical	%	°C	Rating
Strong Acids	Hydrochloric Acid	5	20	-
	Nitric Acid	5	20	-
	Sulphuric Acid	5	20	-
Weak Acids	Acetic Acid	5	20	-
	Formic Acid	5	20	-
Bases	Ammonia	10	20	o
	Sodium Hydroxide	5	20	o
Solvents	Acetone		20	+
	Carbon Tetrachloride		20	+
Lubricants and fuels	Paraffin		20	+
	Gasolene		20	+
	Kerosene		20	+
	Diesel fuel		20	+
	Mineral Oil		70	o
	HFA-ISO46 High Water fluid		70	o
	HFC-Water-Glycol		70	o
	HFD-Phosphate Ester		70	+
	Water		20	o
	Sea Water		20	-

Table 2: Chemical resistance of DX

4 Lubrication

4.1 Choice of Lubricant

DX must be lubricated. The choice of lubricant depends upon μ U and the sliding speed and the stability of the lubricant under the operating conditions.

+	Recommended
o	Satisfactory
-	Not recommended
NA	Data not available

Manufacturer	Grade	Type		Rating
BP	Energrease LS2	Mineral	Lithium Soap	+
	Energrease LT2	Mineral	Lithium Soap	+
	Energrease FGL	Mineral	Non Soap	o
	Energrease GSF	Synthetic	NA	o
Century	Lacerta ASD	Mineral	Lithium/Polymer	o
	Lacerta CL2X	Mineral	Calcium	-
Dow Corning	Molykote 55M	Silicone	Lithium Soap	o
	Molykote PG65	PAO	Lithium Soap	+
	Molykote PG75	Synthetic/Mineral	Lithium Soap	+
	Molykote PG602	Mineral	Lithium Soap	o
Elf	Rolexa.1	Mineral	Lithium Soap	+
	Rolexa.2	Mineral	Lithium Soap	o
	Epexelf.2	Mineral	Lithium/Calcium Soap	o
Esso	Andok C	Mineral	Sodium Soap	o
	Andok 260	Mineral	Sodium Soap	o
	Cazar K	Mineral	Calcium Soap	-
Mobil	Mobilplex 47	Mineral	Calcium Soap	o
	Mobiltemp 1	Mineral	Non Soap	+
Rocol	BG622	White Mineral	Calcium Soap	o
	Sapphire	Mineral	Lithium Complex	o
	White Food Grease	White Oil	Clay	-
Shell	Albida R2	Mineral	Lithium Complex	+
	Axinus S2	Mineral	Lithium	o
	Darina R2	Mineral	Inorganic Non Soap	+
	Stamina U2	Mineral	Polyurea	o
	Tivela A	Synthetic	NA	+
Sovereign	Omega 77	Mineral	Lithium	o
	Omega 85	Mineral	Polyurea	-
Tom Pac	Tom Pac	NA	NA	o
Total	Aerogrease	Synthetic	NA	+
	Multis EP2	NA	Lithium	-

Table 3: Performance of greases

Grease

Grease lubrication is the recommended method of lubrication. The performance ratings of different types of grease are indicated in Table 3. For environmental temperatures above 50 °C the grease should

contain an anti-oxidant additive. Greases containing EP additives or significant additions of graphite or MoS₂ are not generally recommended for use with DX.

Oil

DX is not generally suitable for use with hydrocarbon oils operating above 115 °C. At these temperatures oxidation of the oil may produce a low concentration of labile residues, acid or free radical, which will cause depolymerisation of the DX acetal copolymer bearing lining. Such oxidation

can also occur after prolonged periods at lower temperatures. In practice, this means that DX is not recommended for use with recirculating oil systems or bath systems where sump temperatures of 70 °C or greater are possible.

Non lubricating fluids

Care must be taken when using DX with non lubricating fluids as indicated below.

Water

DX is only suitable for operation in water when the load and speed permit full hydro-

dynamic conditions to be established (see Fig. 7).

Water-Oil Emulsion

DX is suitable for use with 95/5 water/oil emulsions, however initial operation with

pure oil or grease is recommended before transferring to emulsion.

Shock-Absorber Oils

DX is not compatible with shock-absorber oils at operating temperature.

Petrol

With petrol as a lubricant at a $\bar{p}U$ factor of 0.21 N/mm² x m/s the wear rate of DX has been found to be about 4-5 times greater

than that of an initially greased bearing under the same $\bar{p}U$ conditions.

Kerosene and Polybutene

The wear rate of DX with these fluids has been found to be equivalent to that obtained with a light hydrocarbon oil.

Other Fluids

Polyester, polyethylene glycol and polyglycol lubricants give similar wear rates with DX to light hydrocarbon oil. With the glycol fluids however the operating temperature must not exceed 80 °C because the acetal lining of DX could then be attacked by these fluids.

In general, the fluid will be acceptable if it does not chemically attack the acetal lining or the porous bronze interlayer. Chemical resistance data are given in Table 2.

Where there is doubt about the suitability of a fluid, a simple test is to submerge a

sample of DX material in the fluid for two to three weeks at 15-20 °C above the operating temperature. The following will usually indicate that the fluid is not suitable for use with DX.

- A significant change in the thickness of the DX material,
- A visible change in the bearing surface from polished to matt.
- A visible change in the microstructure of the bronze interlayer

4.2 Friction

Lubricated DX bearings show negligible 'stick-slip' and provide smooth sliding between adjacent surfaces. The coefficient of friction of lubricated DX depends upon

the actual operating conditions as indicated in section 4.3. Where frictional characteristics are critical to a design they should be established by prototype testing.

4.3 Lubricated Environments

The following sections describe the basics of lubrication and provide guidance on the application of DX in such environments.

Lubrication

There are three modes of lubricated bearing operation which relate to the thickness of the developed lubricant film between the bearing and the mating surface.

These three modes of operation depend upon:

- Bearing dimensions
- Clearance
- Load and Speed
- Lubricant Viscosity and Flow

Hydrodynamic lubrication

Characterised by:

- Complete separation of the shaft from the bearing by the lubricant film.
- Very low friction and no wear of the bearing or shaft since there is no contact.
- Coefficients of friction of 0.001 to 0.01.

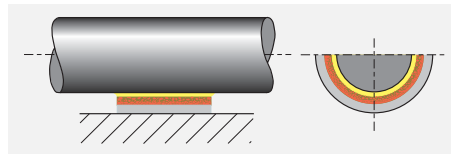


Fig. 4: Hydrodynamic lubrication

Hydrodynamic conditions occur when

$$(4.3.1) \quad \bar{p} \leq \frac{U \cdot \eta}{7.5} \cdot \frac{B}{D_i} \quad [\text{N/mm}^2]$$

Mixed film lubrication

Characterised by:

- Combination of hydrodynamic and boundary lubrication.
- Part of the load is carried by localised areas of self pressurised lubricant and the remainder supported by boundary lubrication.
- Coefficients of friction of 0.01 to 0.10.
- Friction and wear depend upon the degree of hydrodynamic support developed.

- DX provides low friction and high wear resistance to support the boundary lubricated element of the load.

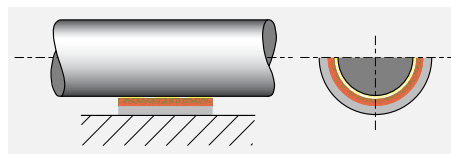


Fig. 5: Mixed film lubrication

Boundary lubrication

Characterised by:

- Rubbing of the shaft against the bearing with virtually no lubricant separating the two surfaces.
- Bearing material selection is critical to performance.
- Shaft wear is likely due to contact between bearing and shaft.
- The excellent properties of DX material minimises wear under these conditions.
- The dynamic coefficient of friction with DX is typically 0.02 to 0.1 under boundary lubrication conditions.

- The static coefficient of friction with DX is typically 0.03 to 0.15 under boundary lubrication conditions.

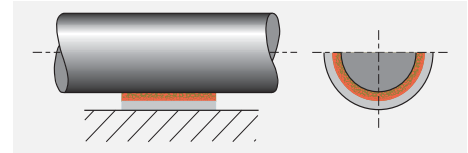


Fig. 6: Boundary lubrication

4.4 Characteristics of Fluid Lubricated DX Bearings

DX is particularly effective in the most demanding of lubricated applications

where full hydrodynamic operation cannot be maintained, for example:

• High load conditions

In highly loaded applications operating under boundary or mixed film conditions DX shows excellent wear resistance and low friction.

• Start up and shut down under load

With insufficient speed to generate a hydrodynamic film the bearing will operate under boundary or mixed film conditions.

- DX minimises wear
- DX requires less start up torque than conventional metallic bearings.

• Sparse lubrication

Many applications require the bearing to operate with less than the ideal lubricant supply, typically with splash or mist lubrication only. DX requires significantly less lubricant than conventional metallic bearings.

4.5 Design Guidance for Fluid Lubricated Applications

Fig. 7, Page 11 shows the three lubrication regimes discussed above plotted on a

graph of sliding speed vs the ratio of specific load to lubricant viscosity.

In order to use Fig. 7

- Using the formulae in Section 5
 - Calculate the specific load \bar{p}
 - Calculate the shaft surface speed (U)

- Using the viscosity temperature relationships presented in Table 4.
 - Determine the viscosity in centipoise of the lubricant.

Note:

Viscosity is a function of the operating temperature. If the operating temperature of

the fluid is unknown, a provisional temperature of 25 °C above ambient can be used.

Area 1 of Fig. 7

- The bearing will operate with boundary lubrication.
- The $\bar{p}U$ factor will be the major determinant of bearing life.

If $e\bar{p}U/\eta \leq 0.2$ then

$$(4.5.1) \quad L_H = \frac{2000}{\left(\frac{e\bar{p}U}{\eta}\right)^{0.5}} \cdot a_Q \cdot a_T \cdot a_S \quad [h]$$

If $0.2 < e\bar{p}U/\eta \leq 1.0$ then

$$(4.5.2) \quad L_H = \frac{1000}{\left(\frac{e\bar{p}U}{\eta}\right)} \cdot a_Q \cdot a_T \cdot a_S \quad [h]$$

Area 2 of Fig. 7

- The bearing will operate with mixed film lubrication.
- $\bar{p}U$ factor is no longer a significant parameter in determining the bearing life.

Area 3 of Fig. 7

- The bearing will operate with hydrodynamic lubrication.

Area 4 of Fig. 7

- These are the most demanding operating conditions.
- The bearing is operated under either high speed or high bearing load to viscosity ratio, or a combination of both.
- These conditions may cause
 - excessive operating temperature
 - and/or high wear rate.

- DX bearing performance can be estimated from the following equations.
- The effective $\bar{p}U$ Factor $e\bar{p}U$ can be estimated from Section 5.8.

If $e\bar{p}U/\eta > 1.0$ then

$$(4.5.3) \quad L_H = \frac{1000}{\left(\frac{e\bar{p}U}{\eta}\right)^2} \cdot a_Q \cdot a_T \cdot a_S \quad [h]$$

$e\bar{p}U$ see (5.8), page 18

- DX bearing performance will depend upon the nature of the fluid and the actual service conditions.

- Bearing wear will be determined only by the cleanliness of the lubricant and the frequency of start up and shut down.

- The bearing performance may be improved:
 - by use of unindented DX lining
 - by the addition of one or more grooves to the bearing
 - by shaft surface finish $R_a < 0.05 \mu m$.

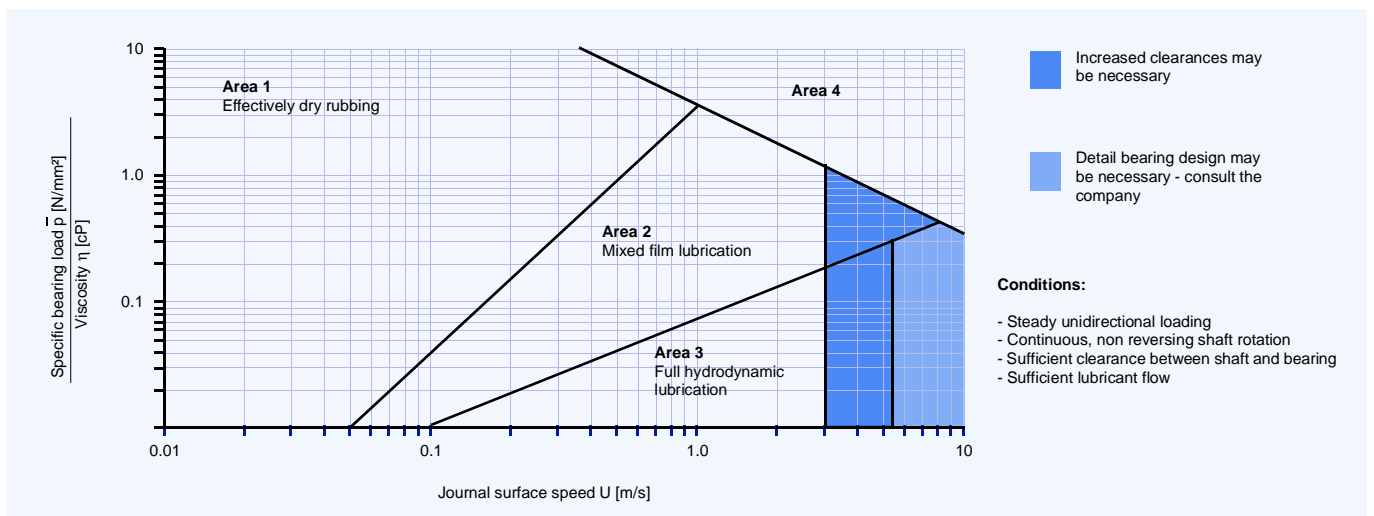


Fig. 7: Design guide for lubricated application

Temperature [°C]	cP														
	0	10	20	30	40	50	60	70	80	90	100	110	120	130	140
Lubricant															
ISO VG 32	310	146	77	44	27	18	13	9.3	7.0	5.5	4.4	3.6	3.0	2.5	2.2
ISO VG 46	570	247	121	67	40	25	17	12	9.0	6.9	5.4	4.4	3.6	3.0	2.6
ISO VG 68	940	395	190	102	59	37	24	17	12	9.3	7.2	5.8	4.7	3.9	3.3
ISO VG 100	2110	780	335	164	89	52	33	22	15	11.3	8.6	6.7	5.3	4.3	3.6
ISO VG 150	3600	1290	540	255	134	77	48	31	21	15	11	8.8	7.0	5.6	4.6
Diesel oil	4.6	4.0	3.4	3.0	2.6	2.3	2.0	1.7	1.4	1.1	0.95				
Petrol	0.6	0.56	0.52	0.48	0.44	0.40	0.36	0.33	0.31						
Kerosene	2.0	1.7	1.5	1.3	1.1	0.95	0.85	0.75	0.65	0.60	0.55				
Water	1.79	1.30	1.0	0.84	0.69	0.55	0.48	0.41	0.34	0.32	0.28				

Table 4: Viscosity data

4.6 Wear Rate and Relubrication Intervals with Grease lubrication

At specific bearing loads below 100 N/mm² a grease lubricated DX bearing shows only small bedding-in wear of about 0.0025 mm. This is followed by little wear during the early part of the bearing life until the lubricant becomes exhausted and the wear rate increases. If the bearing is regreased before the rate of wear starts to increase rapidly the material will continue to function satisfactorily with little wear. Fig. 8 shows the typical wear pattern.

Under specific loads above 100 N/mm² the initial bedding-in wear is greater, typically about 0.025 mm, followed by a decreasing wear rate until the bearing exhibits a similar wear/life relationship to that shown in Fig. 8.

The useful life of the bearing is limited by wear in the loaded area. If this wear exceeds 0.15 mm the grease capacity of the indents is reduced and more frequent regreasing of the bearing will be required.

Fretting Wear

Oscillating movements of less than the dimensions of the indent pattern may cause localised wear of the mating surface after prolonged usage. This will result in the indent pattern becoming transferred

onto the mating surface in contact with the DX bearing and may also give rise to fretting corrosion damage. In this situation DSTM material should be considered as an alternative to DX.

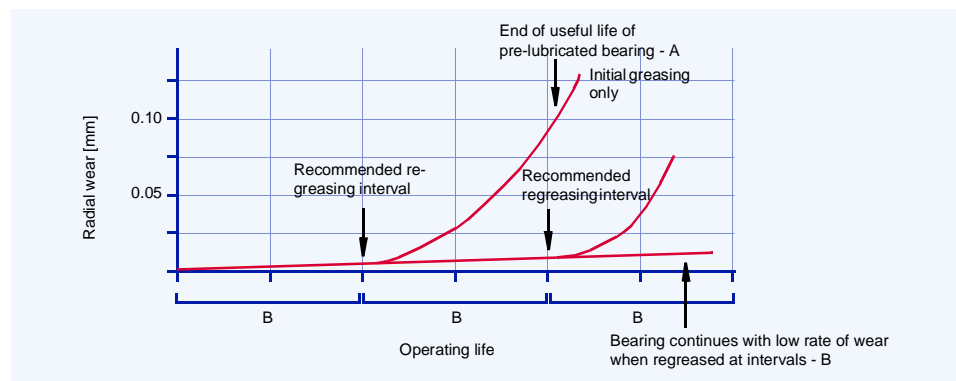


Fig. 8: Typical wear of DX

5 Design Factors

The main parameters when determining the size or calculating the service life for a DX bearing are:

- Specific Load Limit \bar{p}_{lim} [N/mm²]
- $\bar{p}U$ Factor [N/mm² x m/s]
- Mating surface roughness R_a [μ m]
- Mating surface material
- Temperature T [$^{\circ}$ C]
- Other environmental factors eg. housing design, dirt, lubrication.

5.1 Specific Load

The specific load \bar{p} is defined as the working load divided by the projected area of the bearing and is expressed in N/mm².

Bushes

$$(5.1.1) \quad \bar{p} = \frac{F}{D_i \cdot B} \quad [\text{N/mm}^2]$$

Slide Plates

$$(5.1.3) \quad \bar{p} = \frac{F}{L \cdot W} \quad [\text{N/mm}^2]$$

Thrust Washers

$$(5.1.2) \quad \bar{p} = \frac{4F}{\pi \cdot (D_o^2 - D_i^2)} \quad [\text{N/mm}^2]$$

Specific Load Limit

The maximum load which can be applied to a DX bearing can be expressed in terms of the Specific Load Limit, which depends on the type of the loading and lubrication. It is highest under steady loads. The values of Specific Load Limit specified in Table 5 assume good alignment between the bearing and mating surface.

The Specific Load Limit for DX reduces for bearing operating temperatures in excess

of 40 $^{\circ}$ C, falling to about half the values given in Table 5 for temperatures above 100 $^{\circ}$ C.

Conditions of dynamic load or oscillating movement which produce fatigue stress in the bearing result in a reduction in the permissible Specific Load Limit (Fig. 9, Page 14).

Load	Operating condition	Lubrication	\bar{p}_{lim}
Steady	Intermittent or very slow (below 0.01 m/s) continuous rotation or oscillating motion	Grease or oil	140
Steady	Continuous rotation or oscillating motion	Grease or oil (boundary lubrication)	70
Steady or dynamic	Continuous rotation or oscillating motion	Oil (hydrodynamic lubrication)	45

Table 5: Specific load limit \bar{p}_{lim} for DX

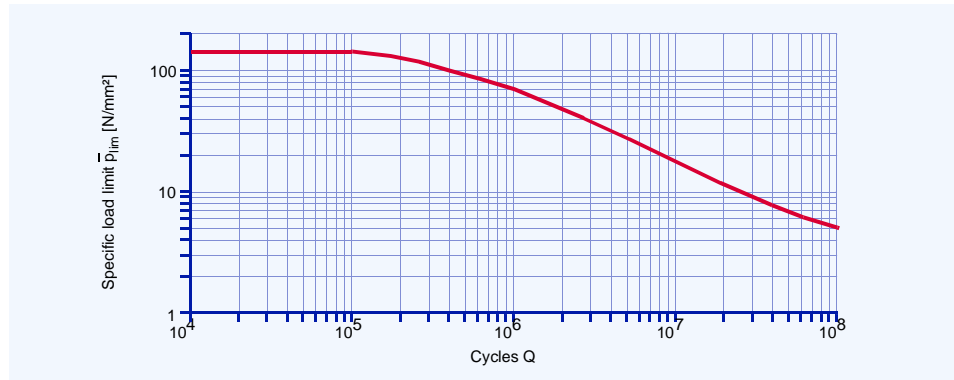


Fig. 9: DX specific load limits \bar{p}_{lim} under dynamic loads or oscillating conditions

5.2 Sliding Speed

The sliding speed U [m/s] is calculated as follows:

Continuous Rotation

Bushes

$$(5.2.1) \quad U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} \quad [\text{N/mm}^2]$$

Thrust Washers

$$(5.2.2) \quad U = \frac{D_o + D_i}{2} \cdot \pi \cdot N \quad [\text{N/mm}^2]$$

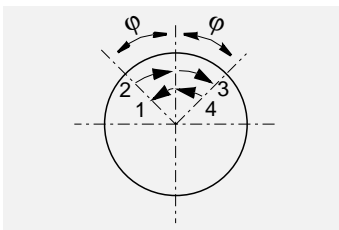


Fig. 10: Oscillating cycle φ

Oscillating Movement

Bushes

$$(5.2.3) \quad U = \frac{D_i \cdot \pi}{60 \cdot 10^3} \cdot \frac{4\varphi \cdot N_{osz}}{360} \quad [\text{N/mm}^2]$$

Thrust Washers

$$(5.2.4) \quad U = \frac{D_o + D_i}{2} \cdot \pi \cdot \frac{4\varphi \cdot N_{osz}}{360} \quad [\text{N/mm}^2]$$

The maximum permissible effective $\bar{p}U$ factor ($\bar{e}pU$ factor) for grease lubricated DX bearings is dependent upon the sliding

speed as shown in Fig. 11. For sliding speeds in excess of 2.5 m/s continuous oil lubrication is recommended.

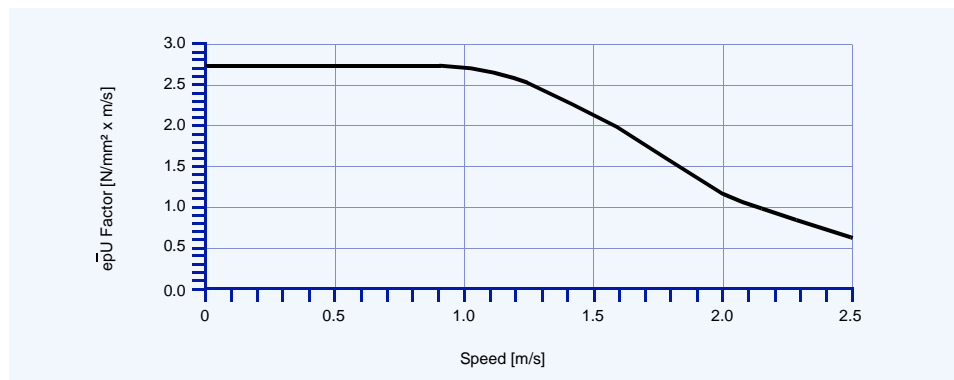


Fig. 11: Maximum $\bar{e}pU$ factor for grease lubrication

5.3 $\bar{p}U$ Factor

The useful operating life of a DX bearing is governed by the $\bar{p}U$ factor, which is calculated as follows:

$$(5.3.1) \quad \bar{p}U = \bar{p} \cdot U \quad [\text{N/mm}^2 \times \text{m/s}]$$

5.4 Load

In addition to its contribution to the $\bar{p}U$ factor the type and direction of the applied load also affects the performance of a DX bearing. This is accommodated in the calcu-

lation of the bearing service life by the speed/load application factor a_Q shown in Figs. 15-17.

Type of Load

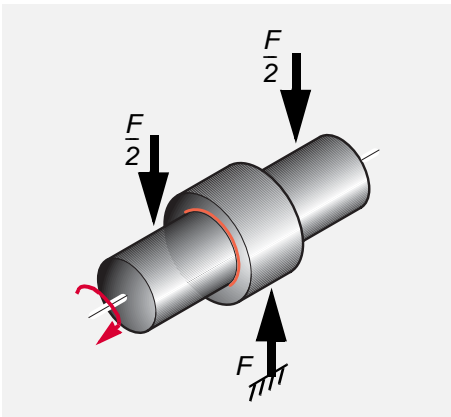


Fig. 12: Steady load, vertically downwards, bush stationary, shaft rotating. Lubricant drains to loaded area

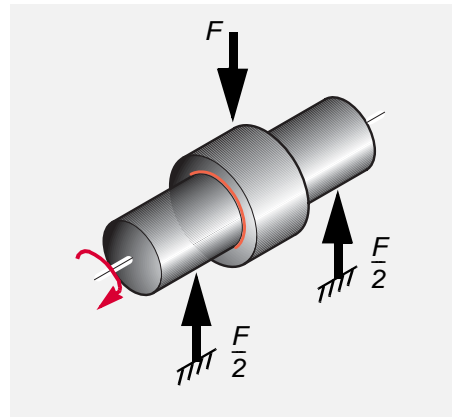


Fig. 13: Steady load, vertically upwards, bush stationary, shaft rotating. Lubricant drains away from loaded area

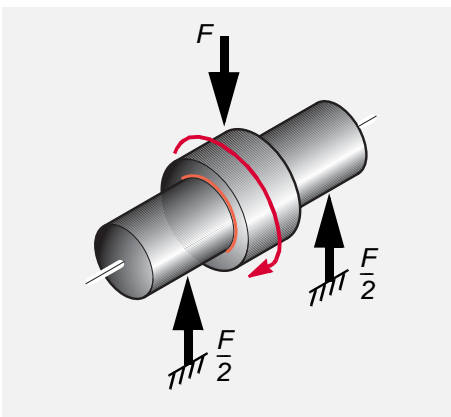


Fig. 14: Rotating load, shaft stationary, bush rotating

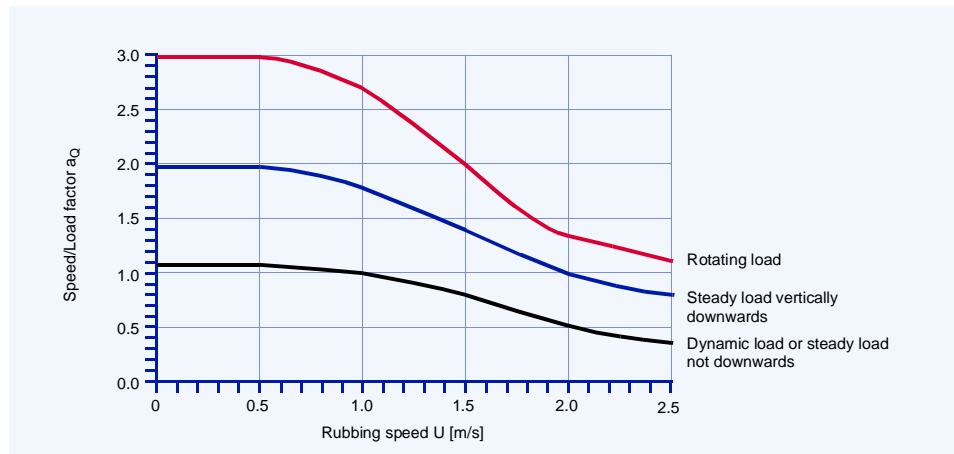


Fig. 15: Speed/Load factor a_Q for MB range bushes - unmachined

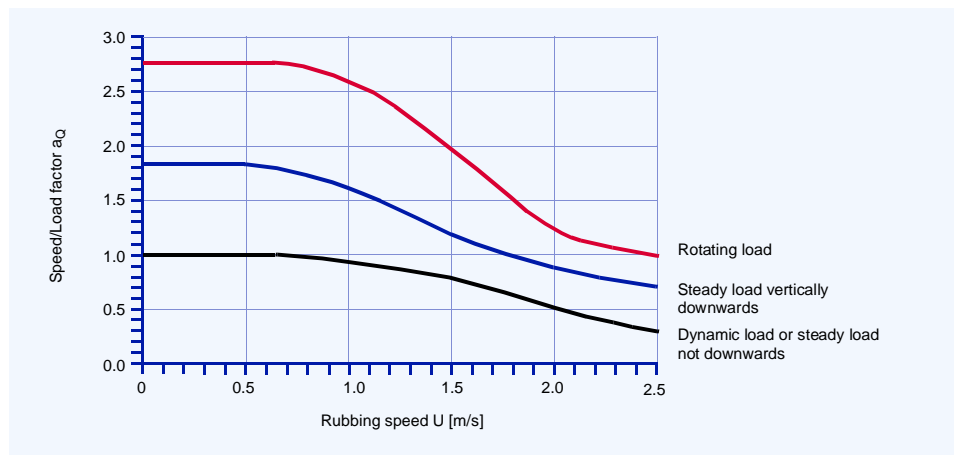


Fig. 16: Speed/Load factor a_Q for PM range and MB range bushes - machined

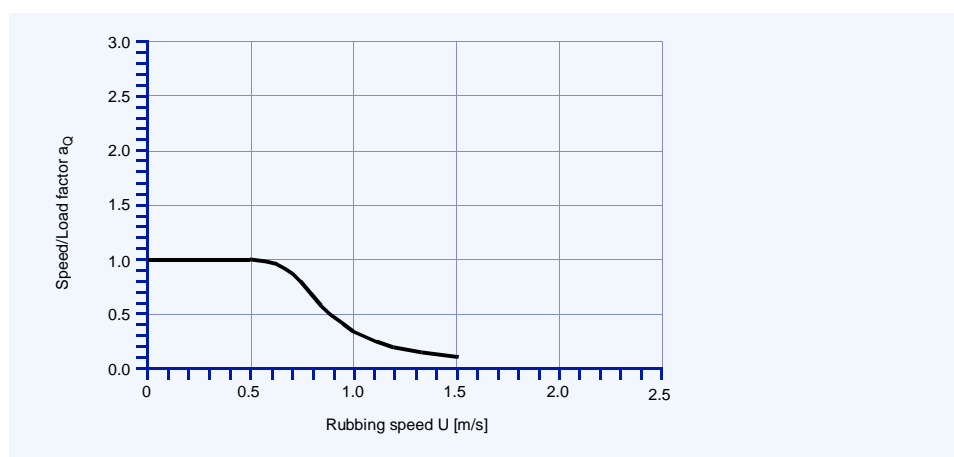


Fig. 17: Speed/Load factor a_Q for thrust washers

Note: $a_Q = 1$ for slideways

5.5 Temperature

The useful life of a DX bearing depends upon the operating temperature. The performance of grease lubricated DX decreases at bearing temperatures above 40 °C. This loss of performance is related to both material and lubricant effects.

For a given $\bar{p}U$ Factor the operating temperature of the bearing depends upon the

temperature of the surrounding environment and the heat dissipation properties of the housing.

In calculating the service life of DX these effects are accommodated by the application factor a_T shown in Fig. 18.

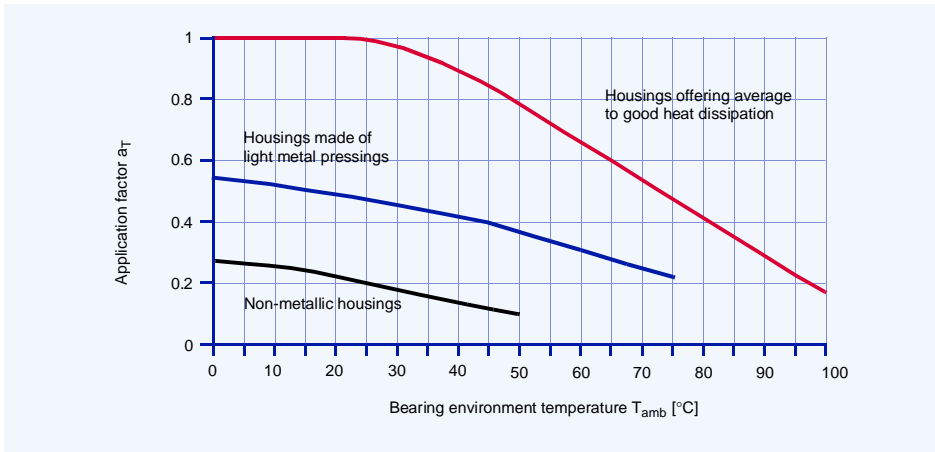


Fig. 18: DX application factor a_T

5.6 Mating Surface

The wear rate of DX is strongly dependent upon the roughness of the mating counterface. For optimum bearing performance the mating surface should be ground to

better than $0.4 \mu\text{m } R_a$. This effect is accommodated by the mating surface finish application factor a_S shown in Fig. 19.

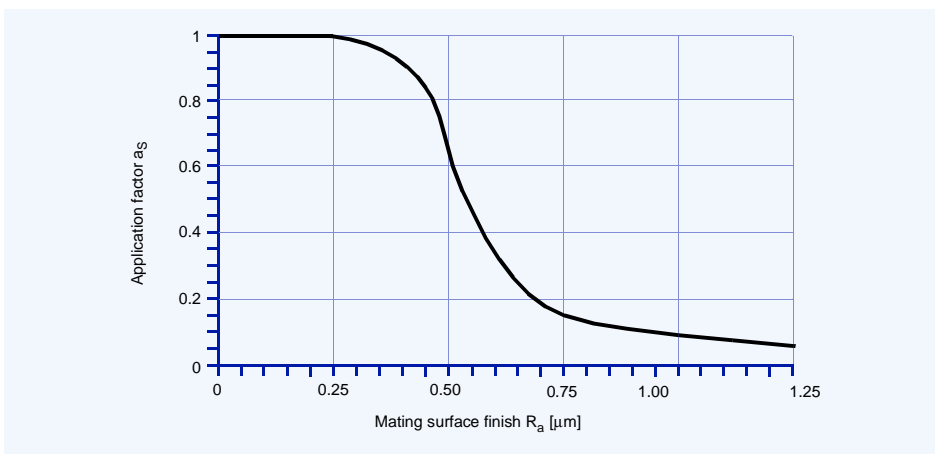


Fig. 19: DX application factor a_S

5.7 Bearing Size

Frictional heat generated at the bearing surface and dissipated through the shaft and housing depends both on the operating conditions (i.e. $\bar{p}U$ factor) and the bearing size.

For a give $\bar{p}U$ condition a large bearing will run hotter than a smaller bearing. The bearing size factor a_B shown in Fig. 20 takes account of this effect.

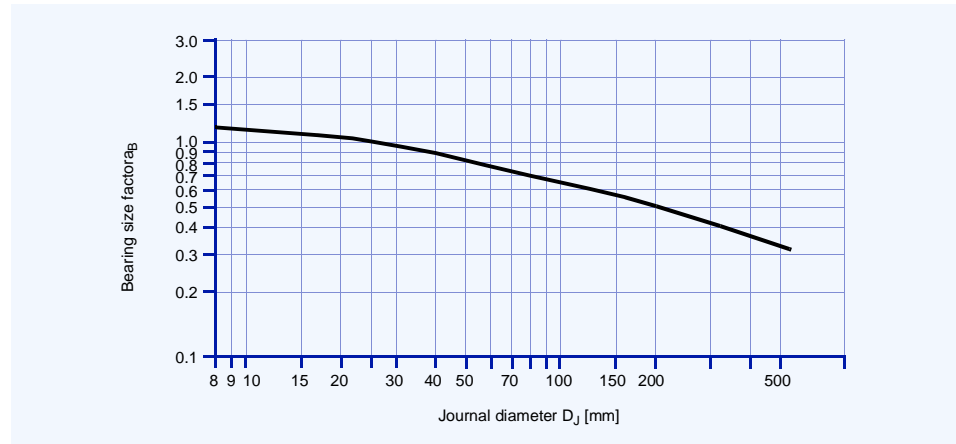


Fig. 20: Bearing size factor a_B

Note: $a_B = 1$ for slideways

5.8 Estimation of Bearing Service Life with Grease Lubrication

Calculation Parameters

Bushes		Thrust Washers		Slide Plates		Unit
Bearing diameter	D_i	Bearing outside diameter	D_o	Strip Length	L	[mm]
Bearing width	B	Bearing inside diameter	D_i	Strip Width	W	[mm]

Operating Conditions

Load	F	[N]
Rotational Speed (Continuous)	N	[1/min]
Oscillating Frequency	N_{osz}	[1/min]
Angular movement about mean position	φ	[°]
Specific Load Limit	see Table 5, Page 13	[N/mm ²]
Application Factor a_Q	see Fig. 15-17, Page 16	[-]
Application Factor a_T	see Fig. 18, Page 17	[-]
Application Factor a_S	see Fig. 19, Page 17	[-]
Bearing Size Factor a_B	see Fig. 20, Page 18	[-]

Calculate \bar{p} from the equations in 5.1 on Page 13.

Calculate \bar{U} from the equations in 5.2 on Page 14.

Calculate \bar{pU} from the equation in 5.3 on Page 15.

Calculate High Load Factor a_E

$$(5.8.1) \quad a_E = \frac{\bar{p}_{lim}}{\bar{p}_{lim} - \bar{p}} \quad [-]$$

\bar{p}_{lim} see Table 5, Page 13

Note:

If $a_E > 10000$, or $a_E < 0$, the bearing is overloaded.

Calculate Effective \bar{pU} Factor $e\bar{pU}$

$$(5.8.2) \quad e\bar{pU} = \frac{a_E \cdot \bar{pU}}{a_B} \quad [-]$$

Note:

Check that $e\bar{pU}$ is less than the limit for the sliding speed U set in Fig. 11. If NOT,

increase the bearing length or use continuous lubrication.

Estimate Bearing Life

If $e\bar{pU} < 1.0$ then

$$(5.8.3) \quad L_H = \frac{3000}{e\bar{pU}} \cdot a_Q \cdot a_T \cdot a_S \quad [h]$$

If $e\bar{pU} > 1.0$ then

$$(5.8.4) \quad L_H = \frac{3000}{(e\bar{pU})^{2.4}} \cdot a_Q \cdot a_T \cdot a_S \quad [h]$$

Estimate Re-greasing Interval

$$(5.8.5) \quad L_{RG} = \frac{L_H}{2} \quad [h]$$

Oscillating Motion and Dynamic Loads

Oscillating Motion

Calculate number of cycles

$$(5.8.6) \quad Z_T = L_{RG} \cdot N_{osz} \cdot 60 \cdot (R + 2) \quad [-]$$

where R = Number of times bearing is regreased during total life required.

Check that Z_T (or C_T) is less than the total number of cycles Q given in Fig. 9 for actual bearing specific load \bar{p} .

If Z_T (or C_T) $> Q$ then life will be limited by fatigue after Q cycles.

Dynamic Loads

Calculate number of cycles

$$(5.8.7) \quad C_T = L_{RG} \cdot C \cdot 60 \cdot (R + 2) \quad [-]$$

If Z_T (or C_T) $< Q$ then life will be limited by wear after Z_T cycles.

If the estimated life or total cycles are insufficient or the regreasing intervals are too frequent, increase the bearing length or diameter, or consider drip feed or continuous oil lubrication, the quantity to be established by test.

5.9 Worked Examples

PM cylindrical Bush

Given			
Load Details	Steady Load	Inside Diameter D_i	40 mm
	Direction: down	Length B	30 mm
Shaft	Steel	Bearing Load F	15000 N
	ambient Temperature	Rotational Speed N	30 1/min
	good heat conditions	R_a	0.3 μm

Calculation Constants and Application Factors			
Specific Load Limit \bar{p}_{lim}	70 N/mm ²	(Table 5, Page 13)	
Application Factor a_T	1.0	(Fig. 18, Page 17)	
Mating Surface Application Factor a_S	0.98	(Fig. 19, Page 17)	
Bearing Size Factor a_B for $\phi 40$	0.98	(Fig. 20, Page 18)	
Application Factor for PM bush a_Q	1.8	(Fig. 16, Page 16)	

Calculation	Ref	Value
Specific Load \bar{p} [N/mm ²]	(5.1.1), page 13	$\bar{p} = \frac{F}{D_i \cdot B} = \frac{15000}{40 \cdot 30} = 12.5$
Sliding Speed U [m/s]	(5.2.1), page 14	$U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} = \frac{40 \cdot \pi \cdot 30}{60000} = 0.063$
High Load Factor a_E [-] (must be >0)	(5.8.1), page 19	$a_E = \frac{\bar{p}_{lim}}{\bar{p}_{lim} - \bar{p}} = \frac{70}{70 - 12.5} = 1.22$
epU Factor [-]	(5.8.3), page 19	$epU = \frac{a_E \cdot \bar{p}U}{a_B} = \frac{1.22 \cdot 12.5 \cdot 0.063}{0.98} = 0.98$
Life L_H [h] for $epU < 1$	(5.8.3), page 19	$L_H = \frac{3000}{epU} \cdot a_Q \cdot a_T \cdot a_S = \frac{3000}{0.98} \cdot 1.8 \cdot 1.0 \cdot 0.98 = 5400$
L_{RG} [h]	(5.8.3), page 19	$L_{RG} = \frac{L_H}{2} = \frac{5400}{2} = 2700$

PM cylindrical Bush

Given			
Load Details	Steady Load	Inside Diameter D_i	90 mm
	Direction: up	Length B	60 mm
Shaft	Steel	Bearing Load F	45000 N
	Temperature 80° C	Rotational Speed N	20 1/min
	good heat conditions	R_a	0.3 μm

Calculation Constants and Application Factors			
Specific Load Limit \bar{p}_{lim} at 80° C	46.7 N/mm ²	(Table 5, Page 13)	
Application Factor a_T	0.4	(Fig. 18, Page 17)	
Mating Surface Application Factor a_S	0.98	(Fig. 19, Page 17)	
Bearing Size Factor a_B for $\phi 40$	0.70	(Fig. 20, Page 18)	
Application Factor for PM bush a_Q	1.0	(Fig. 16, Page 16)	

Calculation	Ref	Value
Specific Load \bar{p} [N/mm ²]	(5.1.1), page 13	$\bar{p} = \frac{F}{D_i \cdot B} = \frac{45000}{90 \cdot 60} = 8.33$
Sliding Speed U [m/s]	(5.2.1), page 14	$U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} = \frac{90 \cdot \pi \cdot 20}{60000} = 0.094$
High Load Factor a_E [-] (must be >0)	(5.8.1), page 19	$a_E = \frac{\bar{p}_{lim}}{\bar{p}_{lim} - \bar{p}} = \frac{46.7}{46.7 - 8.33} = 1.22$
epU Factor [-]	(5.8.3), page 19	$epU = \frac{a_E \cdot \bar{p}U}{a_B} = \frac{1.22 \cdot 8.33 \cdot 0.094}{0.70} = 1.36$
Life L_H [h] for $epU > 1$	(5.8.3), page 19	$L_H = \frac{3000}{(epU)^{2.4}} \cdot a_Q \cdot a_T \cdot a_S = \frac{3000}{1.36^{2.4}} \cdot 1.0 \cdot 0.4 \cdot 0.98 = 562$
L_{RG} [h]	(5.8.3), page 19	$L_{RG} = \frac{L_H}{2} = \frac{562}{2} = 281$

Thrust washer

Given			
Load Details	Steady Load	Inside Diameter D_i	26 mm
	Direction: down	Outside Diameter D_o	44 mm
Shaft	Steel	Bearing Load F	10000 N
	ambient Temperature	Rotational Speed N	10 1/min
	good heat conditions	R_a	0.3 μm

Calculation Constants and Application Factors			
Specific Load Limit \bar{p}_{lim}	70 N/mm ²	(Table 5, Page 13)	
Application Factor a_T	1.0	(Fig. 18, Page 17)	
Mating Surface Application Factor a_S	0.98	(Fig. 19, Page 17)	
Bearing Size Factor a_B for $\phi 35$	0.90	(Fig. 20, Page 18)	
Application Factor for Thrust washers a_Q	1.0	(Fig. 17, Page 16)	

Calculation	Ref	Value
Specific Load \bar{p} [N/mm ²]	(5.1.2), page 13	$\bar{p} = \frac{4 \cdot F}{\pi \cdot (D_o^2 - D_i^2)} = \frac{4 \cdot 10000}{\pi \cdot (44^2 - 26^2)} = 10.11$
Sliding Speed U [m/s]	(5.2.2), page 14	$U = \frac{D_o + D_i}{2} \cdot \pi \cdot N \cdot \frac{44 + 26}{2} \cdot \pi \cdot 10}{60 \cdot 10^3} = \frac{60 \cdot 10^3}{60 \cdot 10^3} = 0.018$
High Load Factor a_E [-] (must be >0)	(5.8.1), page 19	$a_E = \frac{\bar{p}_{lim}}{\bar{p}_{lim} - \bar{p}} = \frac{70}{70 - 10.11} = 1.169$
epU Factor [-]	(5.8.2), page 19	$epU = \frac{a_E \cdot \bar{p}U}{a_B} = \frac{1.169 \cdot 10.11 \cdot 0.018}{0.90} = 0.236$
Life L_H [h] for $epU < 1$	(5.8.3), page 19	$L_H = \frac{3000}{epU} \cdot a_Q \cdot a_T \cdot a_S = \frac{3000}{0.236} \cdot 1.0 \cdot 1.0 \cdot 0.98 = 12460$
L_{RG} [h]	(5.8.3), page 19	$L_{RG} = \frac{L_H}{2} = \frac{12460}{2} = 6230$

Slideways

Given			
Load Details	Steady Load	Length L	50 mm
	Direction: down	Width W	20 mm
Mating Surface	Steel ($R_a = 0.3 \mu\text{m}$)	Bearing Load F	20000 N
	Temperature 80° C	Stroke	15 mm
	good heat conditions	Frequency	10 1/min


Calculation Constants and Application Factors			
Specific Load Limit \bar{p}_{lim} at 80° C	93 N/mm ²	(Table 5, Page 13)	
Application Factor a_T	0.4	(Fig. 18, Page 17)	
Mating Surface Application Factor a_S	0.98	(Fig. 19, Page 17)	
Bearing Size Factor a_B	1.0	(Fig. 20, Page 18)	
Application Factor for Slideways a_Q	1.0	(Fig. 17, Page 16)	

Calculation	Ref	Value
Specific Load \bar{p} [N/mm ²]	(5.1.3), page 13	$\bar{p} = \frac{F}{L \cdot W} = \frac{20000}{50 \cdot 20} = 20$
Sliding Speed U [m/s]		$U = \frac{15 \cdot 2 \cdot 10}{60 \cdot 10^3} = 0.005$
High Load Factor a_E [-] (must be >0)	(5.8.1), page 19	$a_E = \frac{\bar{p}_{lim}}{\bar{p}_{lim} - \bar{p}} = \frac{93}{93 - 20} = 1.27$
epU Factor [-]	(5.8.2), page 19	$epU = \frac{a_E \cdot \bar{p}U}{a_B} = \frac{1.27 \cdot 20 \cdot 0.005}{1.0} = 0.127$
Life L_H [h] for $epU < 1$	(5.8.3), page 19	$L_H = \frac{3000}{epU} \cdot a_Q \cdot a_T \cdot a_S = \frac{3000}{0.127} \cdot 1.0 \cdot 0.4 \cdot 0.98 = 9260$
L_{RG} [h]	(5.8.3), page 19	$L_{RG} = \frac{L_H}{2} = \frac{9260}{2} = 4630$

6 Data Sheet

Application: _____

6.1 Data for bearing design calculations

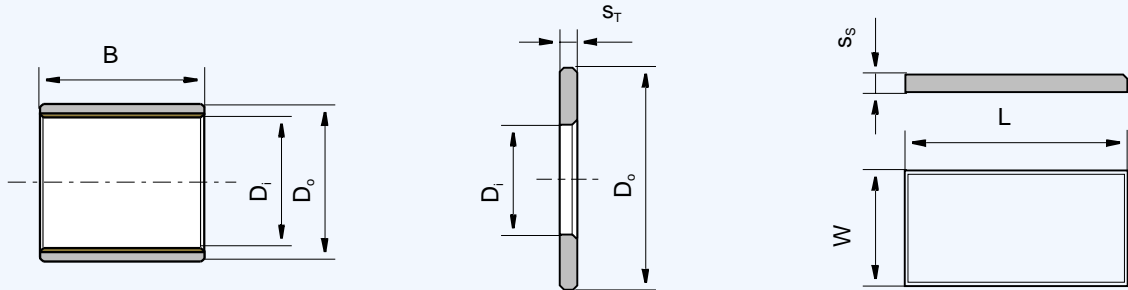

- Cylindrical Bush
 Thrust Washer
 Slideplate
 Special (Sketch)

- Rotational movement
 Steady load
 Rotating load
 Oscillating movement
 Linear movement

- Existing Design
 New Design

Quantity

Dimensions in mm

Inside Diameter D_i
 Outside Diameter D_o
 Width B
 Length of slideplate L
 Width of slideplate W
 Thickness of slideplate s_s

Load

Radial load or specific load F [N]
 \bar{p} [N/mm²]

Axial load or specific load F [N]
 \bar{p} [N/mm²]

Movement

Rotational speed N [1/min]
 Speed U [m/s]
 Length of Stroke L_s [mm]
 Frequency of Stroke [1/min]
 Oscillating cycle φ [°]
 Oscillating frequency N_{osz} [1/min]

Service hours per day

Continuous operation
 Intermittent operation
 Operating time
 Days per year

Fits and Tolerances

Shaft D_J
 Bearing Housing D_H

Operating Environment

Ambient temperature T_{amb} [°]
 Housing with good heat transfer properties
 Light pressing or insulated housing with poor heat transfer properties
 Non metal housing with poor heat transfer properties
 Alternate operation in water and dry

Mating surface

Material
 Hardness HB/HRC
 Surface finish R_a [µm]

Lubrication

Dry
 Continuous lubrication
 Process fluid lubrication
 Initial lubrication only
 Hydrodynamic conditions
 Process Fluid
 Lubricant
 Dynamic viscosity η

Service life

Required service life L_H [h]

Customer Data
 Company:
 Street:

City:
 Post Code:

Project:
 Name:
 Tel.:

Date:
 Signature:
 Fax:

7 Bearing Assembly

7.1 Dimensions and Tolerances

For optimum performance it is essential that the correct running clearance is used and that both the diameter of the shaft and the bore of the housing are finished to the limits given in the tables.

If the bearing housing is unusually flexible the bush will not close in by the calculated

amount and the running clearance will be more than the optimum. In these circumstances the housing should be bored slightly undersize or the journal diameter increased, the correct size being determined by experiment.

7.2 Tolerances for minimum clearance

Grease lubrication

The minimum clearance required for satisfactory performance of DX depends upon the $\bar{p}U$ factor, the sliding speed and the environmental temperature, any one or combination of which may reduce the diametral clearance in operation due to inward thermal expansion of the DX polymer lining. It is therefore necessary to compensate for this.

Fig. 21 shows the minimum diametral clearance plotted stepped against journal diameter at an ambient 20 °C. Where the stepped lines show a change of clearance for a given journal diameter, the lower value is used.

The superimposed straight lines indicate the minimum permissible diametral clear-

ance for various values of $\bar{p}Uu$ (Fig. 21), where $\bar{p}U$ is calculated as in 5.3 on Page 15, and u is a sliding speed factor for speeds in excess of 0.5 m/s given in Fig. 22.

If the clearance indicated for a $\bar{p}Uu$ factor lies below the stepped lines the recommended standard shaft may be used. If above, the shaft size must be reduced to obtain the clearance indicated on the vertical axis of the relevant figure.

Under slow speed and high load conditions it may be possible to achieve satisfactory performance with diametral clearances less than those indicated. But adequate prototype testing is recommended in such cases.

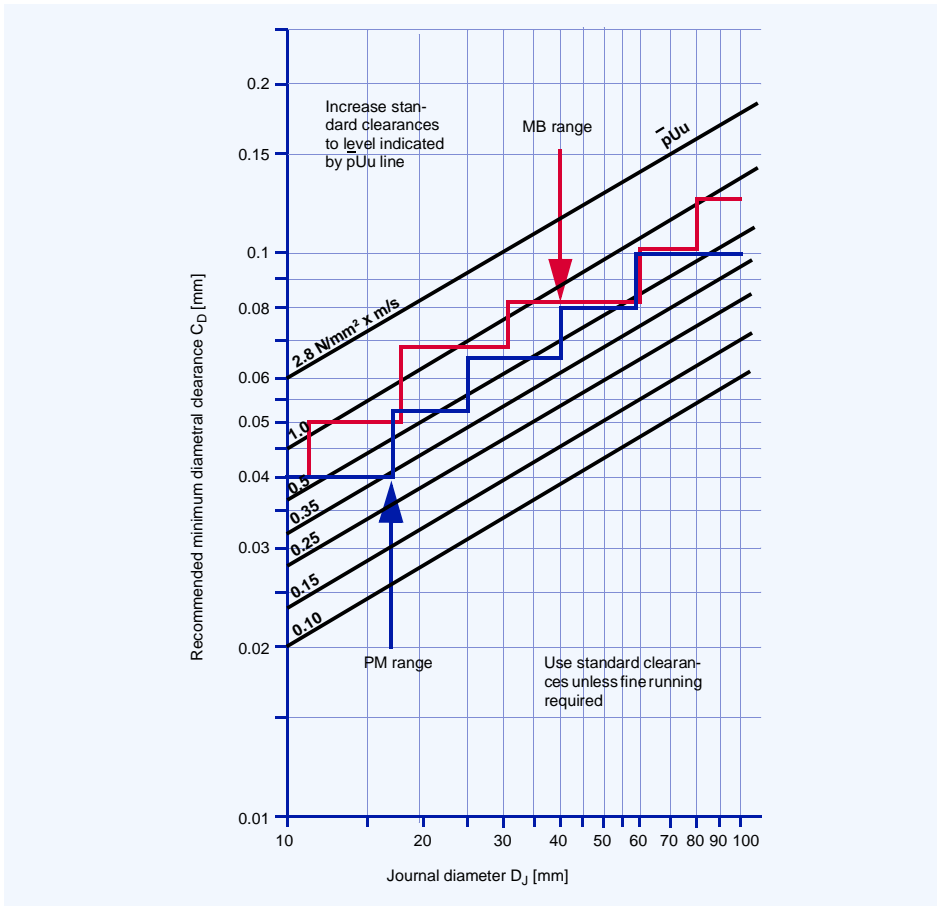


Fig. 21: Minimum clearance for PM prefinished and MB machinable metric range machined to H7 bore

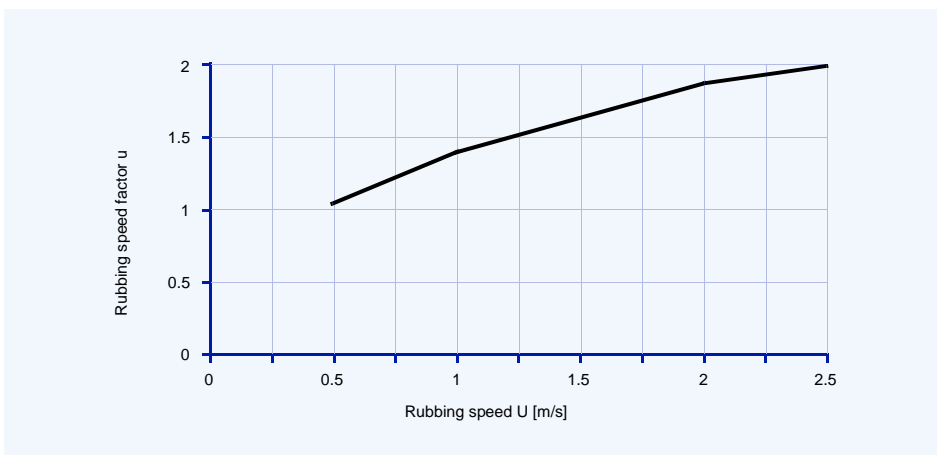


Fig. 22: Rubbing speed factor u

Fluid Lubrication

The minimum clearance required for journal bearings operating under hydrodynamic or mixed film conditions for a range of shaft rotational speeds and diameters is

shown in Fig. 23. It is recommended that the bearing performance under minimum clearance conditions be confirmed by testing if possible.

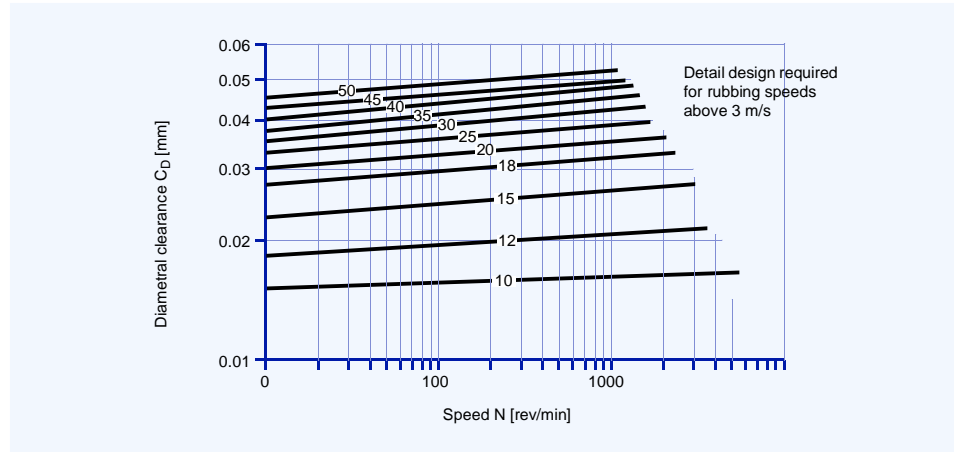


Fig. 23: DX minimum clearances - bush diameters D_i 10-50 mm

Allowance for Thermal Expansion

For operation in high temperature environments the clearance should be increased by the amounts indicated by Fig. 24 to

compensate for the inward thermal expansion of the bearing lining.

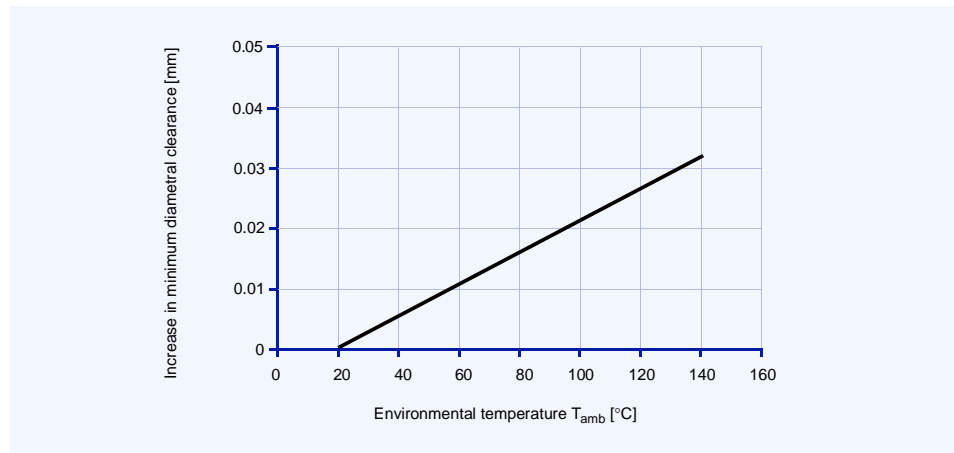


Fig. 24: Recommended increase in diametral clearance

If the housing is non-ferrous then the bore should be reduced by the amounts given in Table 6, in order to give an increased inter-

ference fit to the bush, with a similar reduction in the journal diameter additional to that indicated by Fig. 24.

Housing material	Reduction in housing diameter per 100°C rise	Reduction in shaft diameter per 100°C rise
Aluminium alloys	0.1%	0.1% + values from Fig. 24
Copper base alloys	0.05%	0.05% + values from Fig. 24
Steel and cast iron	Nil	values from Fig. 24
Zinc base alloys	0.15%	0.15% + values from Fig. 24

Table 6: Allowance for high temperature

7.3 Counterface Design

DX bearings may be used with all conventional mating surface materials. Hardening of steel journals is not required unless abrasive dirt is present or if the projected bearing life is in excess of 2000 hours, in which cases a minimum shaft hardness of 350 HB is recommended.

A ground surface finish of better than $0.4\mu\text{m } R_a$ is recommended. The final direction of machining of the mating surface should preferably be the same as the direction of motion relative to the bearing in service.

DX is normally used in conjunction with ferrous journals and thrust faces, but in damp or corrosive surroundings stainless steel or hard chromium plated mild steel, alterna-

tively WH shaft sleeves (Standard programme available) are recommended. When plated mating surfaces are specified the plating should possess adequate strength and adhesion, particularly if the bearing is to operate with high fluctuating loads.

The shaft or thrust collar used in conjunction with the DX bush or thrust washer must extend beyond the bearing surface in order to avoid cutting into it. The mating surface must also be free from grooves or flats, the end of the shaft should be given a lead-in chamfer and all sharp edges or projections which may damage the soft polymer lining of the DX must be removed.

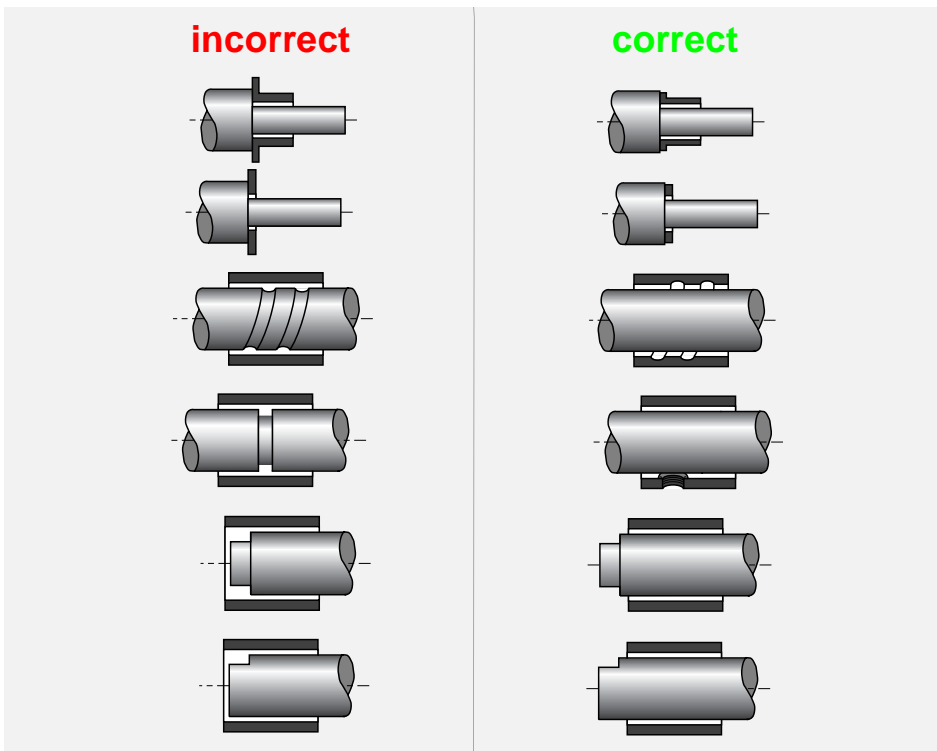


Fig. 25: Counterface design

7.4 Installation

Important Note

Care must be taken to ensure that the DX lining material is not damaged during the installation.

Fitting of Bushes

The bush is inserted into its housing with the aid of a stepped mandrel, preferably made from case hardened mild steel, as shown in Fig. 26. The following should be noted to avoid damage to the bearing:

- Housing diameter is as recommended
- 15-30° lead-in chamfer on housing
- edges of lead-in chamfer are deburred
- The bush must be square to the housing
- Light smear of oil on bush OD

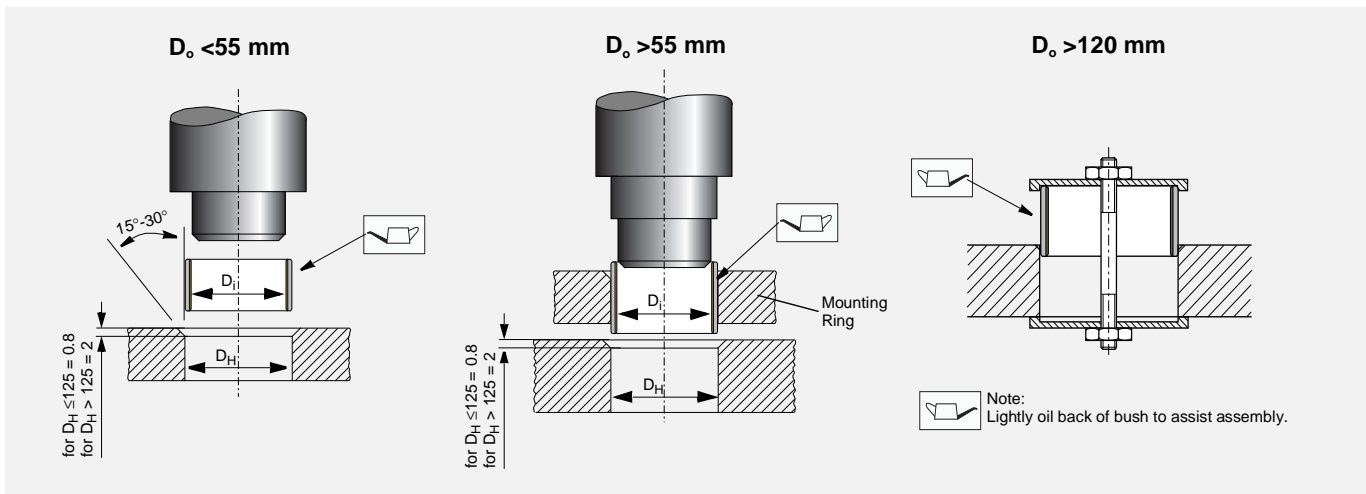


Fig. 26: Fitting of bushes

Insertion Forces

Fig. 27 gives an indication of the maximum insertion force required to correctly install standard DX bushes.

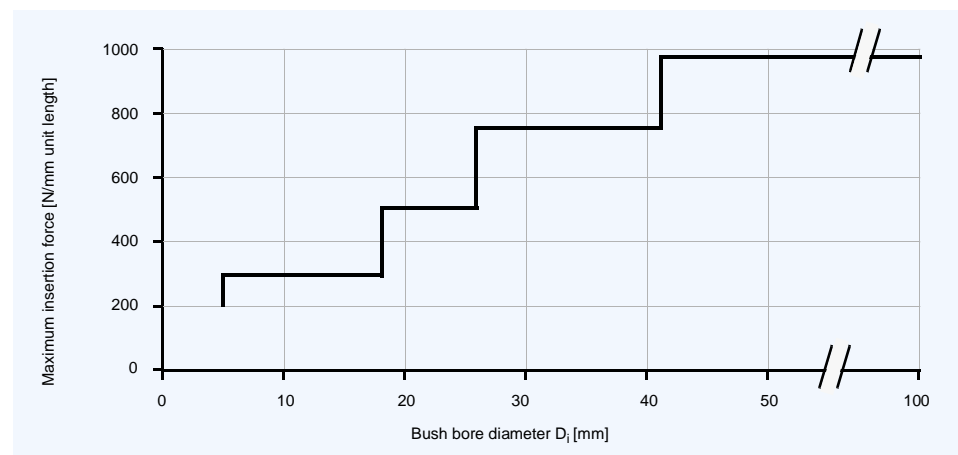


Fig. 27: Maximum insertion force F_i

Alignment

Accurate alignment is an important consideration for all bearing assemblies. With DX bearings misalignment over the length of a

bush (or pair of bushes), or over the diameter of a thrust washer should not exceed 0.020 mm as illustrated in Fig. 28.

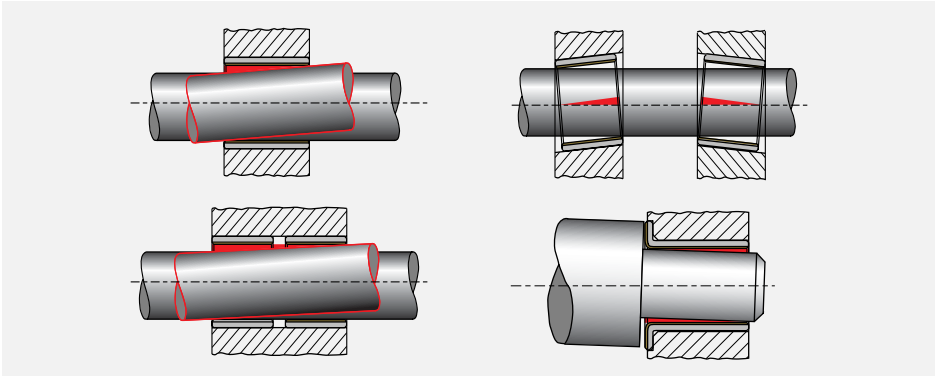


Fig. 28: Alignment

Sealing

While DX can tolerate the ingress of some contaminant materials into the bearing without loss of performance, where there is the possibility of highly abrasive material

entering the bearing, a suitable sealing arrangement, as illustrated in Fig. 29 should be provided.

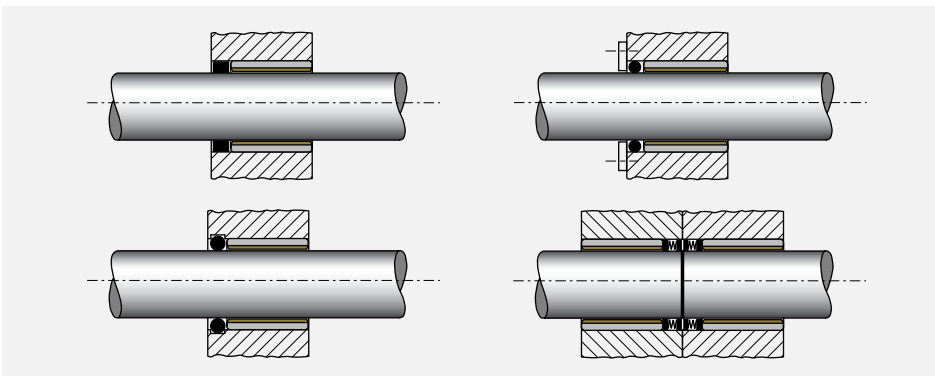


Fig. 29: Recommended sealing arrangements

Axial Location

Where axial location is necessary, it is generally advisable to fit DX thrust washers in conjunction with DX bushes, even when the axial loads are low. Experience has

shown that fretting debris from unsatisfactory locating surfaces can enter an adjacent DX bush and adversely affect the bearing life and performance.

Fitting of Thrust Washers

DX thrust washers should be located on the outside diameter in a recess as shown in Fig. 30. The inside diameter must be clear of the shaft in order to prevent contact with the steel backing of the DX material. The recess diameter should be 0.125 mm larger than the washer diameter and the depth as given in the product tables.

If there is no recess for the thrust washer one of the following methods of fixing may be used:

- two dowel pins
- two screws
- adhesive.

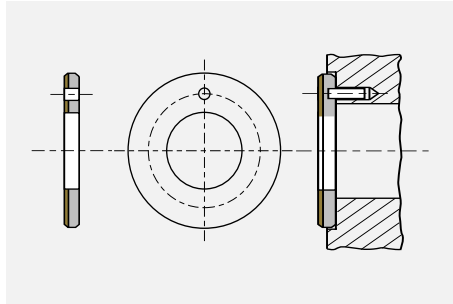


Fig. 30: Installation of Thrust-Washer

Important Note

- Dowel pins should be recessed 0.25 mm below the bearing surface
- Screws should be countersunk 0.25 mm below the bearing surface
- DX must not be heated above 130 °C
- Contact adhesive manufacturers for guidance on the selection of suitable adhesives
- Protect the bearing surface to prevent contact with adhesive
- Ensure the washer ID does not touch the shaft after assembly
- Ensure that the washer is mounted with the steel backing to the housing.

Slideways

DX strip material for use as slideway bearings should be installed using one of the following methods:

- countersunk screws
- adhesives
- mechanical location.

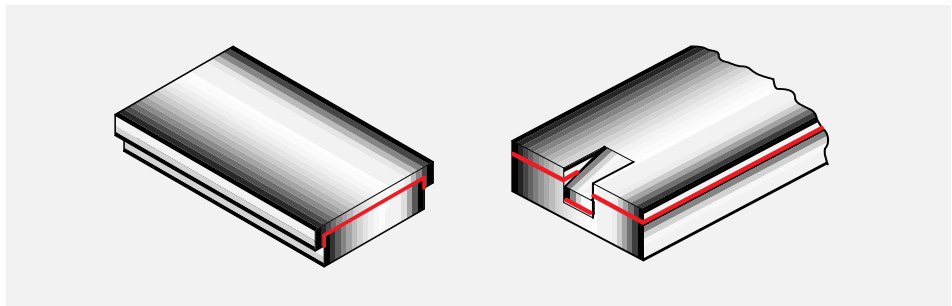


Fig. 31: Mechanical location of DX slideways

8 Machining

8.1 Machining Practice

The acetal copolymer lining of DX has good machining characteristics and can be treated as a free cutting brass in most respects. The indents in the bearing surface may lead to the formation of burrs or whiskers due to the resilience of the lining material, but this can be avoided by using machining methods which remove the lining as a ribbon, rather than a narrow thread.

When machining DX it is recommended that not more than 0.125 mm is removed from the lining thickness in order to ensure that the lubricant capacity of the indents remaining after machining is not significantly reduced.

Boring, reaming and broaching are all suitable machining methods for use with DX. The recommended tool material is high speed steel or tungsten carbide.

8.2 Boring

Fig. 32 illustrates a recommended boring tool which should be mounted with its axis at right angles to the direction of feed.

The essential characteristic required in the boring tool is a tip radius greater than 1.5 mm, which combined with a side rake of 30° will produce the ribbon effect required.

Cutting speeds should be high, the optimum between 2.0 and 4.5 m/s. The feed should be low, in the range 0.05/0.025 mm for cuts of 0.125 mm, the lower feeds being used with the higher cutting speeds.

Satisfactory finishes can usually be obtained machining dry and an air blast may facilitate swarf removal. The use of coolant is not detrimental.

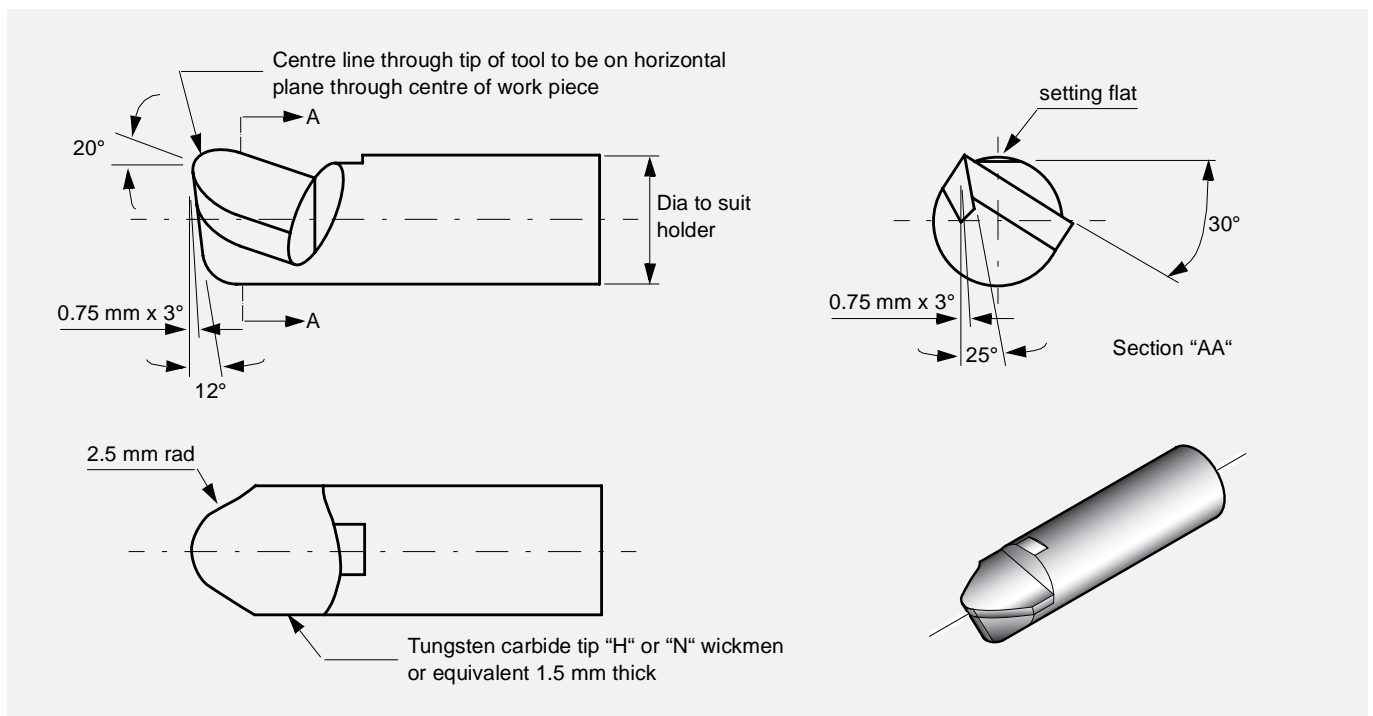


Fig. 32: Boring tool for DX

8.3 Reaming

MB-DX-bushes can be reamed satisfactorily by hand with a straight-fluted expanding reamer. For best results the reamer should be sharp, the cut 0.025-0.050 mm

and the feed slow. Where hand reaming is not desired machining speeds of about 0.05 m/s are recommended with the cuts and feeds as for boring.

8.4 Broaching

Fig. 33 shows broaches suitable for finishing MB-DX-bushes up to 65 mm diameter.

The broach should be used dry, at a speed of 0.1-0.5 m/s.

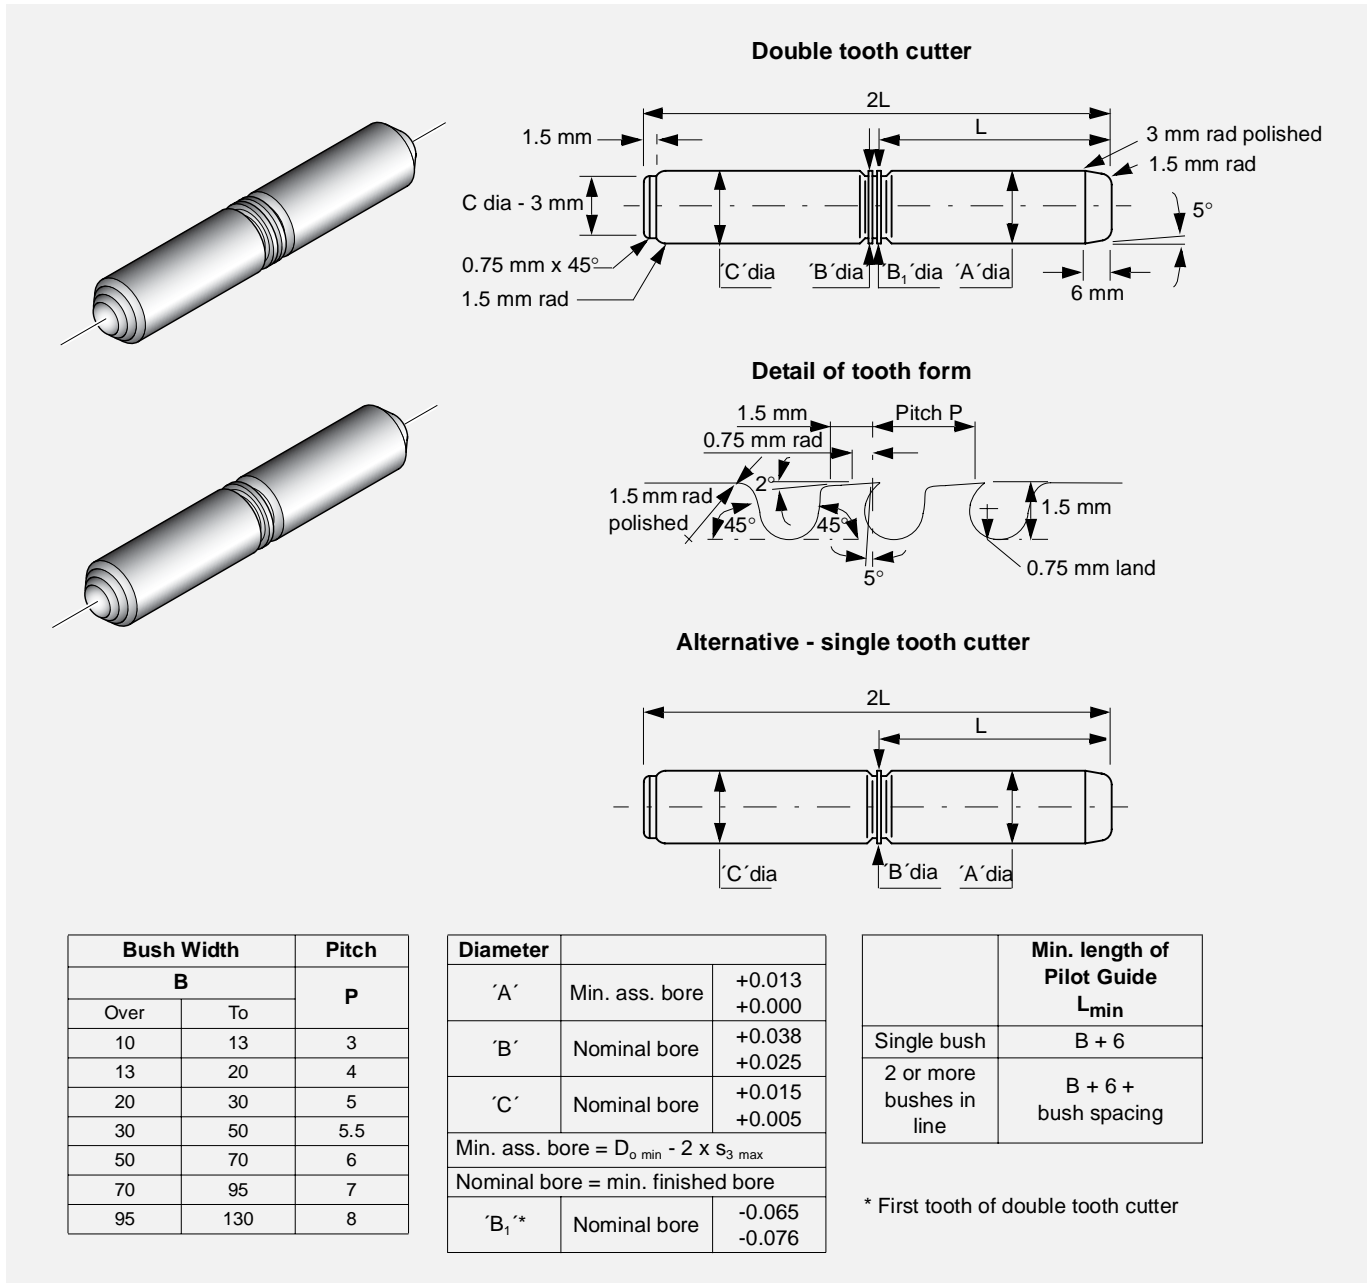


Fig. 33: Suitable broaches for MB-DX

Use the single tooth version where the bush is less than 25 mm long, and the double tooth broach for longer bushes or for two or more bushes together.

If it is necessary to make up a special form of broach the following points should be noted:

- Adequate provision should be made for locating the bush by providing a pilot to suit the bore of the bush when pressed home. A rear support shoulder should locate in the broached bore of the bush after cutting. Alternatively, special guides may be provided external to the work-piece.
- If two bushes are to be broached in line, then the pilot guide and rear support should be longer than the distance between the two bushes.
- For large bushes it may be necessary to provide axial relief along the length of the pilot guide and rear support, in order to reduce the broaching forces.
- Unless a guided broach is used, the tool will follow the initial bore alignment of the bush, broaching cannot improve concentricity and parallelism unless external guides are used.

In general owing to the variation in wall thickness of large diameter bushes, broaching is not suitable for finishing bores

of more than 60 mm diameter unless external guides are used.

8.5 Vibrobroaching

This technique may also be used. A single cutter is propelled with progressive reciprocating motion with a vibration frequency of typically 50 Hz. The cutter should have a primary rake of 1.5° for 0.5 mm. A cut of

0.25 mm on diameter may be made at an average cutting speed of 0.15 m/s to give a surface finish of better than 0.8 μm R_a , which is acceptable.

8.6 Modification of components

The modification of DX bearing components requires no special procedures. In general it is more satisfactory to perform machining or drilling operations from the polymer lining side in order to avoid burrs. When cutting is done from the steel side,

the minimum cutting pressure should be used and care taken to ensure that any steel or bronze particles protruding into the remaining bearing material, and all burrs, are removed.

8.7 Drilling Oil Holes

Bushes should be adequately supported during the drilling operation to ensure that

no distortion is caused by the drilling pressure.

8.8 Cutting Strip Material

DX strip material may be cut to size by any one of the following methods. Care must be taken to protect the bearing surface from damage and to ensure that no deformation of the strip occurs.

- Using side and face cutter, or slitting saw, with the strip held flat and securely on a horizontal milling machine.
- Cropping
- Guillotine (For widths less than 90 mm only)
- Water-jet cutting, Laser cutting

9 Electroplating

DX Components

To provide corrosion protection the mild steel backing of DX may be electroplated with most of the conventional electroplating metals including the following:

- zinc ISO 2081-2
- cadmium ISO 2081-2
- nickel ISO 1456-8
- hard chromium ISO 1456-8.

For the harder materials if the specified plating thickness exceeds approximately 5 μm then the housing diameter should be increased by twice the plating thickness in order to maintain the correct assembled bearing bore size.

Where electrolytic attack is possible tests should be conducted to ensure that all the materials in the bearing environment are mutually compatible.


Mating Surfaces

DX can be used against hard chrome plated materials and care should be taken to ensure that the recommended shaft

sizes and surface finish are achieved after the plating process.

10 Standard Products

10.1 PM-DX cylindrical bushes

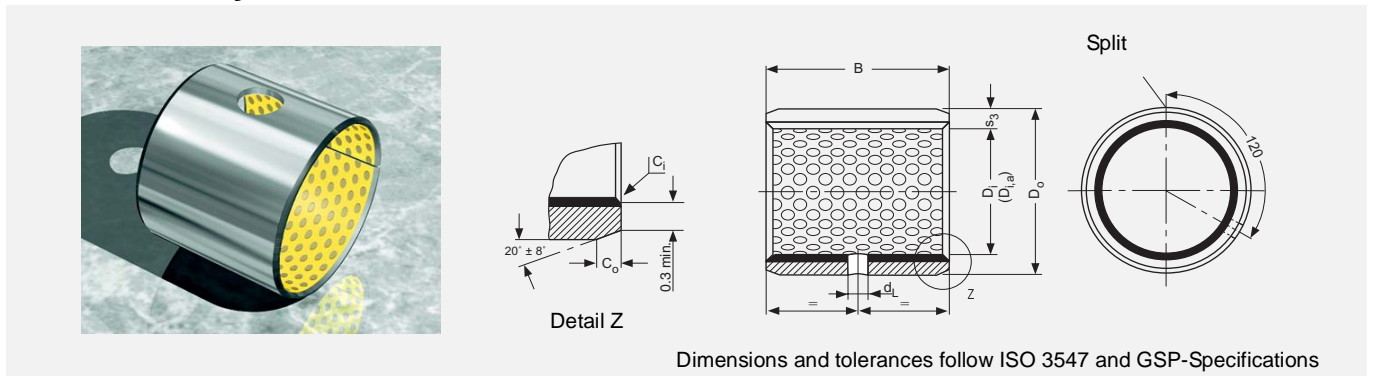

Dimensions and tolerances follow ISO 3547 and GSP-Specifications

All dimensions in mm

ID and OD chamfers

s ₃	C _o	C _i	s ₃	C _o	C _i
1	0.6 ± 0.4	-0.1 to -0.5	2	1.2 ± 0.4	-0.1 to -0.7
1.5	0.6 ± 0.4	-0.1 to -0.7	2.5	1.6 ± 0.8	-0.2 to -1.0

* alternatively rounded

Part No.	Nominal size		Width B	Wall thickness s ₃	Shaft-ø D _J [h8]	Housing-ø D _H [H7]	Bush i-ø D _{i,a} assembled in [H7] housing	Clearance C _D	Oil hole -ø d _L
	D _i	D _o							
PM 0808 DX	8	10	8.25	0.980 0.955	8.000 7.978	10.015 10.000	8.105 8.040	0.127 0.040	No hole
PM 0810 DX			7.75						
PM 0812 DX			10.25 9.75						
PM 1010 DX	10	12	12.25		10.000 9.978	12.018 12.000	10.108 10.040	0.130 0.040	3
PM 1012 DX			11.75						
PM 1015 DX			15.25 14.75						
PM 1020 DX			20.25 19.75						
PM 1210 DX	12	14	10.25		12.000 11.973	14.018 14.000	12.108 12.040	0.135 0.040	3
PM 1212 DX			9.75						
PM 1215 DX			12.25 11.75						
PM 1220 DX			15.25 14.75						
PM 1225 DX	20.25 19.75	14	25.25 24.75		14.000 13.973	16.018 16.000	14.108 14.040	0.135 0.040	4
PM 1415 DX	15.25 14.75								
PM 1420 DX	20.25 19.75								
PM 1425 DX	25.25 24.75	14	16		15.000 14.973	17.018 17.000	15.108 15.040	0.135 0.040	3
PM 1510 DX	10.25 9.75								
PM 1512 DX	15	17	12.25 11.75					4	

10 Standard Products

Part No.	Nominal size		Width B	Wall thickness s_3	Shaft- \varnothing D_J [h8]	Housing- \varnothing D_H [H7]	Bush i- \varnothing $D_{i,a}$ assembled in [H7] housing	Clearance C_D	Oil hole - \varnothing d_L			
	D_i	D_o								max. min.	max. min.	max. min.
PM 1515 DX	15	17	15.25	0.980 0.955	15.000 14.973	17.018 17.000	15.108 15.040	0.135 0.040	4			
PM 1525 DX			14.75							25.25 24.75		
PM 1615 DX	16	18	15.25		16.000 15.973	18.018 18.000	16.108 16.040					
PM 1620 DX			14.75							20.25 19.75		
PM 1625 DX			25.25 24.75									
PM 1815 DX	18	20	15.25		18.000 17.973	20.021 20.000	18.111 18.040					
PM 1820 DX			14.75							20.25 19.75		
PM 1825 DX			25.25 24.75									
PM 2010 DX	20	23	10.25		1.475 1.445	20.000 19.967	23.021 23.000			20.131 20.050	0.164 0.050	6
PM 2015 DX			9.75									
PM 2020 DX			20.25 19.75									
PM 2025 DX			25.25 24.75									
PM 2030 DX			30.25 29.75									
PM 2215 DX	22	25	15.25	22.000 21.967		25.021 25.000	22.131 22.050					
PM 2220 DX			14.75					20.25 19.75				
PM 2225 DX			25.25 24.75									
PM 2230 DX			30.25 29.75									
PM 2415 DX	24	27	15.25	24.000 23.967		27.021 27.000	24.131 24.050					
PM 2420 DX			14.75		20.25 19.75							
PM 2425 DX			25.25 24.75									
PM 2430 DX			30.25 29.75									
PM 2515 DX	25	28	15.25	25.000 24.967	28.021 28.000	25.131 25.050						
PM 2520 DX			14.75				20.25 19.75					
PM 2525 DX			25.25 24.75									
PM 2530 DX			30.25 29.75									
PM 283130 DX	28	31	30.25	1.970 1.935	28.000 27.967	31.025 31.000	28.135 28.050	0.188 0.060				
PM 2820 DX		32	29.75							20.25 19.75		
PM 2825 DX			25.25 24.75									
PM 2830 DX			30.25 29.75									
PM 3020 Dx	30	34	20.25	30.000 29.967	34.025 34.000	30.155 30.060						
PM 3030 DX			19.75				30.25 29.75					
PM 3040 DX			40.25 39.75									

Part No.	Nominal size		Width B	Wall thickness S_3	Shaft- \varnothing D_J [h8]	Housing- \varnothing D_H [H7]	Bush i- \varnothing $D_{i,a}$ assembled in [H7] housing	Clearance C_D	Oil hole - \varnothing d_L									
	D_i	D_o								max. min.	max. min.	max. min.	max. min.	max. min.				
PM 3220 DX	32	36	20.25	1.970 1.935	32.000 31.961	36.025 36.000	32.155 32.060	0.194 0.060	6									
PM 3230 DX			19.75							30.25								
PM 3235 DX			29.75							35.25								
PM 3240 DX			34.75							40.25								
PM 3520 DX	35	39	20.25		1.970 1.935	35.000 34.961	39.025 39.000			35.155 35.060	0.194 0.060	6						
PM 3530 DX			19.75										30.25					
PM 3535 DX			29.75										35.25					
PM 3550 DX			34.75										50.25					
PM 3635 DX	36	40	49.75			1.970 1.935	35.25			40.025			36.155	0.194 0.060	6			
			34.75				40.000			36.060								
PM 3720 DX	37	41	20.25				37.000			41.025			37.155					
			19.75				36.961			41.000			37.060					
PM 4020 DX	40	44	20.25	1.970 1.935			40.000 39.961	44.025 44.000	40.155 40.060	0.194 0.060			6					
PM 4030 DX			19.75													30.25		
PM 4040 DX			29.75													40.25		
PM 4050 DX			39.75													50.25		
PM 4520 DX	45	50	49.75		1.970 1.935		45.000 44.961	50.025 50.000	45.195 45.080		0.234 0.080	8						
PM 4530 DX			20.25													30.25		
PM 4540 DX			19.75													40.25		
PM 4545 DX			29.75													45.25		
PM 4550 DX			44.75			1.970 1.935								0.234 0.080	8			
PM 5040 DX	50	55	49.75				50.000 49.961	55.030 55.000	50.200 50.080							0.239 0.080	8	
PM 5050 DX			40.25															39.75
PM 5060 DX			50.25															60.25
			49.75	59.75														
PM 5520 DX	55	60	20.25	2.460 2.415			55.000 54.954	60.030 60.000	55.200 55.080	0.246 0.080			8					
PM 5525 DX			19.75															25.25
PM 5530 DX			24.75															30.25
PM 5540 DX			29.75		40.25													
PM 5550 DX			39.75		2.460 2.415				0.246 0.080		8							
PM 5560 DX	50.25	60.25																
	49.75	59.75																
PM 6030 DX	60	65	69.75			60.000 59.954	65.030 65.000	60.200 60.080				0.246 0.080		8				
PM 6040 DX			30.25												40.25			
PM 6060 DX			29.75												60.25			
PM 6070 DX			39.75												70.25			

10 Standard Products

Part No.	Nominal size		Width B	Wall thickness s_3	Shaft- \varnothing D_J [h8]	Housing- \varnothing D_H [H7]	Bush i- \varnothing $D_{i,a}$ assembled in [H7] housing	Clearance C_D	Oil hole - \varnothing d_L					
	D_i	D_o								max. min.	max. min.	max. min.	max. min.	max. min.
PM 6540 DX	65	70	40.25	2.450 2.384	65.000 64.954	70.030 70.000	65.262 65.100	0.308 0.100	8					
PM 6550 DX			39.75							50.25				
PM 6560 DX			49.75							60.25				
PM 6570 DX			59.75							70.25				
PM 7040 DX			69.75							80.25				
PM 7050 DX	40.25	75	39.75		70.000 69.954	75.030 75.000	70.262 70.100							
PM 7065 DX	50.25		65.25											
PM 7070 DX	49.75		64.75											
PM 7080 DX	70.25		69.75											
PM 7540 DX	80.25		79.75											
PM 7560 DX	75	80	40.25		2.450 2.384	75.000 74.954	80.030 80.000	75.262 75.100	0.313 0.100	9.5				
PM 7560 DX			39.75								60.25			
PM 7580 DX			59.75								80.25			
PM 8040 DX	79.75	80.25												
PM 8060 DX	40.50	85	39.50			80.000 79.954	85.035 85.000	80.267 80.100						
PM 8060 DX	60.50		60.50											
PM 8080 DX	59.50		80.50											
PM 8080 DX	79.50		79.50											
PM 80100 DX	100.50		99.50											
PM 8530 DX	85	90	30.50			2.450 2.384	85.000 84.946	90.035 90.000			85.267 85.100	0.321 0.100	9.5	
PM 8530 DX			29.50	40.50										
PM 8540 DX			39.50	60.50										
PM 8560 DX			59.50	59.50										
PM 8580 DX			80.50	79.50										
PM 85100 DX	100.50	99.50												
PM 9040 DX	90	95	40.50	2.450 2.384	90.000 89.946		95.035 95.000	90.267 90.100	0.321 0.100	9.5				
PM 9040 DX			39.50								60.50			
PM 9060 DX			59.50								80.50			
PM 9080 DX			79.50								79.50			
PM 9090 DX			90.50								89.50			
PM 90100 DX	100.50	99.50												
PM 9560 DX	95	100	60.50		95.000 94.946		100.035 100.000	95.267 95.100			0.321 0.100			9.5
PM 95100 DX			59.50											
PM 95100 DX			99.50											


Part No.	Nominal size		Width B		Wall thickness S ₃	Shaft-ø D _J [h8]	Housing-ø D _H [H7]	Bush i-ø D _{i,a} assembled in [H7] housing	Clearance C _D	Oil hole -ø d _L
	D _i	D _o	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.		
PM 10050 DX	100	105	50.50	2.450	2.384	100.000	105.035	100.267	0.321	9.5
PM 10060 DX			49.50							
PM 10080 DX			60.50							
PM 10095 DX			59.50							
PM 100115DX			80.50							
PM 10560 DX	105	110	79.50	2.450	2.384	105.000	110.035	105.267	0.321	9.5
PM 105110 DX			95.50							
PM 105115 DX			94.50							
PM 11060 DX	110	115	115.50	2.450	2.384	110.000	115.035	110.267	0.321	9.5
PM 110110 DX			114.50							
PM 110115 DX			60.50							
PM 11550 DX	115	120	59.50	2.450	2.384	115.000	120.035	115.267	0.321	9.5
PM 11570 DX			110.50							
PM 12060 DX			109.50							
PM 120100 DX	120	125	115.50	2.450	2.384	120.000	125.040	120.272	0.326	9.5
PM 120110 DX			114.50							
PM 12560 DX			109.50							
PM 125100 DX	125	130	100.50	2.450	2.384	125.000	130.040	125.272	0.335	9.5
PM 125110 DX			99.50							
PM 13050 DX			110.50							
PM 13060 DX	130	135	109.50	2.435	2.380	130.000	135.040	130.280	0.343	-
PM 13080 DX			60.50							
PM 130100 DX			59.50							
PM 13560 DX			80.50							
PM 13580 DX	135	140	79.50	2.435	2.380	135.000	140.040	135.280	0.343	-
PM 14050 DX			100.50							
PM 14060 DX			99.50							
PM 14080 DX	140	145	100.50	2.435	2.380	140.000	145.040	140.280	0.343	-
PM 140100 DX			99.50							
PM 15050 DX			80.50							
PM 15060 DX			79.50							
PM 15080 DX	150	155	100.50	2.435	2.380	150.000	155.040	150.280	0.343	-
PM 150100 DX			99.50							
PM 15080 DX			80.50							
PM 150100 DX	150	155	79.50	2.435	2.380	150.000	155.040	150.280	0.343	-
PM 15060 DX			100.50							
PM 15080 DX			99.50							

10 Standard Products

Part No.	Nominal size		Width B	Wall thickness s_3	Shaft- \varnothing D_J [h8]	Housing- \varnothing D_H [H7]	Bush i- \varnothing $D_{i,a}$ assembled in [H7] housing	Clearance C_D	Oil hole - \varnothing d_L
	D_i	D_o							
PM 16050 DX	160	165	50.50	2.435 2.380	160.000 159.937	165.040 165.000	160.280 160.130	0.343 0.130	
PM 16060 DX			49.50						
PM16080 DX			60.50						
PM 160100 DX			59.50						
PM 17050 DX			80.50						
PM 17060 DX	79.50								
PM 17080 DX	100.50								
PM 170100 DX	99.50								
PM 18050 DX	170	175	50.50						
PM 18060 DX			49.50						
PM 18080 DX			60.50						
PM 180100 DX			59.50						
PM 19050 DX			80.50						
PM 19060 DX	79.50								
PM 19080 DX	180	185	100.50						
PM 190100 DX			99.50						
PM 190120 DX			120.50						
PM 20050 DX			19.50						
PM 20060 DX			50.50						
PM 20080 DX	49.50								
PM 200100 DX	190	195	60.50						
PM 200120 DX			59.50						
PM 22050 DX			80.50						
PM 22060 DX			79.50						
PM 22080 DX			100.50						
PM 220100 DX	99.50								
PM 220120 DX	200	205	120.50						
PM 24050 DX			119.50						
PM 24060 DX			50.50						
PM 24080 DX			49.50						
PM 240100 DX			60.50						
PM 240120 DX	59.50								
PM 22050 DX	220	225	80.50						
PM 22060 DX			79.50						
PM 24050 DX			100.50						
PM 24060 DX			99.50						
PM 24080 DX			120.50						
PM 240100 DX	119.50								
PM 240120 DX	240	245	50.50						
PM 24060 DX			49.50						
PM 24080 DX			60.50						
PM 240100 DX			59.50						
PM 240120 DX			80.50						
PM 240120 DX	79.50								
PM 240100 DX	100.50								
PM 240120 DX	99.50								
PM 240120 DX	120.50								
PM 240120 DX	119.50								

Part No.	Nominal size		Width B		Wall thickness S_3	Shaft- ϕ D_J [h8]	Housing- ϕ D_H [H7]	Bush i- ϕ $D_{i,a}$ assembled in [H7] housing	Clearance C_D	Oil hole - ϕ d_L							
	D_i	D_o	max. min.	max. min.							max. min.	max. min.	max. min.	max. min.			
PM 25050 DX	250	255	50.50	2.435 2.380		250.000 249.928	255.052 255.000	250.292 250.130	0.364 0.130								
PM 25060 DX			49.50								60.50						
PM 25080 DX			59.50								80.50						
PM 250100 DX			79.50								100.50						
PM 250120 DX			99.50								120.50						
PM 26050 DX	260	265	50.50			2.435 2.380		260.000 259.919	265.052 265.000		260.292 260.130	0.373 0.130					
PM 26060 DX			49.50											60.50			
PM 26080 DX			59.50											80.50			
PM 260100 DX			79.50											100.50			
PM 260120 DX			99.50											120.50			
PM 28050 DX	280	285	50.50					2.435 2.380			280.000 279.919	285.052 285.000		280.292 280.130	0.373 0.130		
PM 28060 DX			49.50														60.50
PM 28080 DX			59.50														80.50
PM 280100 DX			79.50														100.50
PM 280120 DX			99.50														120.50
PM 30050 DX	300	305	50.50	2.435 2.380						300.000 299.919	305.052 305.000	300.292 300.130		0.373 0.130			
PM 30060 DX			49.50														60.50
PM 30080 DX			59.50														80.50
PM 300100 DX			79.50														100.50
PM 300120 DX			99.50														120.50

10.2MB-DX cylindrical bushes

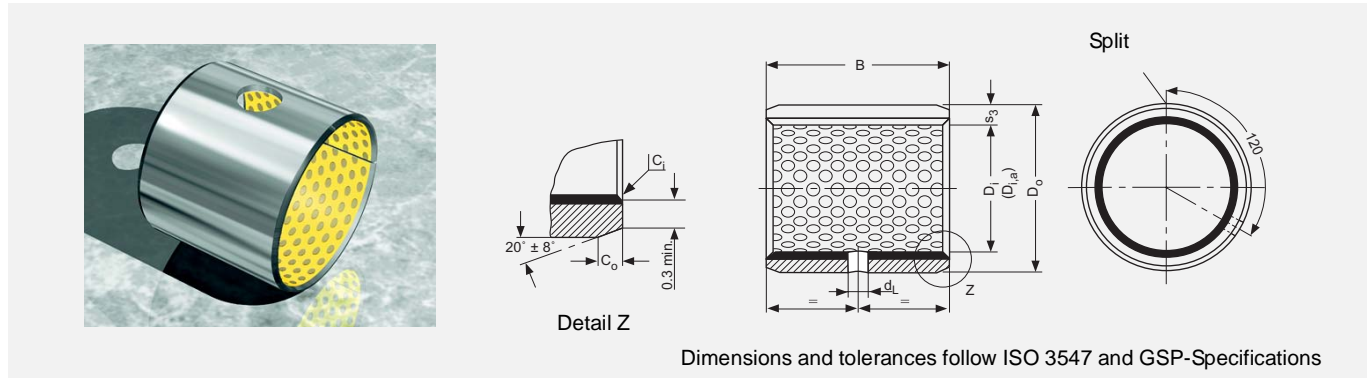

Dimensions and tolerances follow ISO 3547 and GSP-Specifications

All dimensions in mm

ID and OD chamfers

s_3	C_o	C_i	s_3	C_o	C_i
1	0.6 ± 0.4	-0.1 to -0.5	2	1.2 ± 0.4	-0.1 to -0.7
1.5	0.6 ± 0.4	-0.1 to -0.7	2.5	1.6 ± 0.8	-0.2 to -1.0

* alternatively rounded

Part No.	Nominal size		Width B	Wall thickness s_3	Shaft- \varnothing D_J [d8]	Housing- \varnothing D_H [H7]	Bush i- \varnothing $D_{i,a,m}$ machined to [H7]	Clearance C_D	Oil hole - \varnothing d_L	
	D_i	D_o								max. min.
MB 0808 DX	8	10	8.25	1.108 1.082	7.960 7.938	10.015 10.000	8.015 8.000	0.077 0.040	No hole	
MB 0810 DX			7.75							
MB 0812 DX			10.25 9.75							
MB 1010 DX	10	12	12.25		11.950 9.923	12.018 12.000	10.018 10.000	0.080 0.040	3 4	
MB 1012 DX			9.75							
MB 1015 DX			15.25 14.75							
MB 1020 DX			20.25 19.75							
MB 1210 DX	12	14	10.25		1.108 1.082	11.950 11.923	14.018 14.000	12.018 12.000	0.095 0.050	3 4
MB 1212 DX			9.75							
MB 1215 DX			12.25 11.75							
MB 1220 DX			15.25 14.75							
MB 1225 DX			20.25 19.75							
MB 1415 DX	14	16	25.25 24.75			13.950 13.923	16.018 16.000	14.018 14.000	0.095 0.050	4
MB 1420 DX			15.25 14.75							
MB 1425 DX			20.25 19.75							
MB 1510 DX	15	17	10.25	14.950 14.923		17.018 17.000	15.018 15.000	0.095 0.050	3 4	
MB 1512 DX			9.75							
MB 1515 DX			12.25 11.75							
MB 1525 DX			15.25 14.75							

Part No.	Nominal size		Width B		Wall thickness S_3		Shaft- \varnothing D_J [d8]		Housing- \varnothing D_H [H7]		Bush i- \varnothing $D_{i,a,m}$ machined to [H7]		Clearance C_D		Oil hole - \varnothing d_L
	D_i	D_o	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.				
MB 1615 DX	16	18	15.25	1.108	15.950	18.018	16.018	0.095	0.050	4					
MB 1620 DX			14.75								20.25	15.923	18.000	16.000	
MB 1625 DX			19.75								25.25	15.25	18.018	16.000	
MB 1815 DX	18	20	14.75	1.082	17.950	20.021	18.018	0.095	0.050	4					
MB 1820 DX			19.75								20.25	17.923	20.000	18.000	
MB 1825 DX			24.75								25.25	15.25	18.018	18.000	
MB 2010 DX	20	23	9.75	1.608	19.935	23.021	20.021	0.119	0.065	6					
MB 2015 DX			14.75								19.75	19.902	23.000	20.000	
MB 2020 DX			19.75								20.25	19.902	23.000	20.000	
MB 2025 DX			24.75								25.25	21.935	25.021	22.021	
MB 2030 DX			29.75								30.25	21.902	25.000	22.000	
MB 2215 DX	22	25	14.75	1.608	21.935	25.021	22.021	0.119	0.065	6					
MB 2220 DX			19.75								20.25	21.902	25.000	22.000	
MB 2225 DX			24.75								25.25	21.902	25.000	22.000	
MB 2230 DX			29.75								30.25	23.935	27.021	24.021	
MB 2415 DX	24	27	14.75	1.608	23.935	27.021	24.021	0.119	0.065	6					
MB 2420 DX			19.75								20.25	23.902	27.000	24.000	
MB 2425 DX			24.75								25.25	23.902	27.000	24.000	
MB 2430 DX			29.75								30.25	24.935	28.021	25.021	
MB 2515 DX	25	28	14.75	1.608	24.935	28.021	25.021	0.119	0.065	6					
MB 2520 DX			19.75								20.25	24.902	28.000	25.000	
MB 2525 DX			24.75								25.25	24.902	28.000	25.000	
MB 2530 DX			29.75								30.25	27.935	32.025	28.021	
MB 2820 DX	28	32	19.75	2.108	27.935	32.025	28.021	0.119	0.065	6					
MB 2825 DX			24.75								27.902	32.000	28.000		
MB 2830 DX			29.75								30.25	32.000	28.000		
MB 3020 Dx	30	34	19.75	2.072	30.000	34.025	30.021	0.119	0.065	6					
MB 3030 DX			29.75								29.967	34.000	30.000		
MB 3040 DX			39.75								40.25	34.000	30.000		
			39.75								39.75	34.000	30.000		

10 Standard Products





Part No.	Nominal size		Width B	Wall thickness s_3	Shaft- \varnothing D_J [d8]	Housing- \varnothing D_H [H7]	Bush i- \varnothing $D_{i,a,m}$ machined to [H7]	Clearance C_D	Oil hole - \varnothing d_L	
	D_i	D_o								max. min.
MB 3220 DX	32	36	20.25	2.108 2.072	31.920 31.881	36.025 36.000	32.025 32.000	0.144 0.080	6	
MB 3230 DX			19.75							30.25
MB 3235 DX			29.75							35.25
MB 3240 DX			34.75							40.25
MB 3520 DX	35	39	20.25		34.920 34.881	39.025 39.000	35.025 35.000			
MB 3530 DX			19.75							30.25
MB 3550 DX			29.75							50.25
MB 3720 DX	37	41	20.25		36.920 36.881	41.025 41.000	37.025 37.000			
MB 4020 DX	40	44	20.25		39.920 39.881	44.025 44.000	40.025 40.000			
MB 4030 DX			19.75							30.25
MB 4040 DX			29.75							40.25
MB 4050 DX			39.75							50.25
MB 4520 DX	45	50	20.25		44.920 44.881	50.025 50.000	45.025 45.000			
MB 4530 DX			19.75							30.25
MB 4540 DX			29.75							40.25
MB 4545 DX			39.75							45.25
MB 4550 DX			44.75	50.25						
MB 5040 DX	50	55	40.25	49.920 49.881	55.030 55.000	50.025 50.000				
MB 5060 DX			39.75				60.25			
MB 5520 DX	55	60	20.25	2.634 2.588	54.900 54.854	60.030 60.000	55.030 55.000			
MB 5525 DX			19.75					25.25		
MB 5530 DX			24.75					30.25		
MB 5540 DX			29.75					40.25		
MB 5550 DX			39.75					50.25		
MB 5560 DX			49.75					60.25		
MB 6030 DX	60	65	30.25	59.900 59.854	65.030 65.000	60.030 60.000				
MB 6040 DX			29.75				40.25			
MB 6060 DX			39.75				60.25			
MB 6070 DX			59.75				70.25			
MB 6070 DX			69.75				69.75			

Part No.	Nominal size		Width B		Wall thickness S_3	Shaft- \varnothing D_J [d8]		Housing- \varnothing D_H [H7]		Bush i- \varnothing $D_{i,a,m}$ machined to [H7]		Clearance C_D		Oil hole - \varnothing d_L										
	D_i	D_o	max. min.	max. min.		max. min.	max. min.	max. min.	max. min.	max. min.	max. min.													
MB 6540 DX	65	70	40.25	2.634 2.568		64.900	70.030	65.030	0.176 0.100	8														
MB 6550 DX			39.75										50.25	64.854	70.000	65.000								
MB 6560 DX			49.75										60.25											
MB 6570 DX			59.75										70.25											
MB 7040 DX	70	75	40.25			2.634 2.568		69.900	75.030	70.030	0.176 0.100	8												
MB 7050 DX			39.75												50.25	69.854	75.000	70.000						
MB 7065 DX			49.75												65.25									
MB 7070 DX			59.75												64.75									
MB 7080 DX	69.75	70.25																						
MB 7540 DX	75	80	40.25					2.634 2.568		74.900	80.030	75.030	0.176 0.100	8										
MB 7560 DX			39.75														60.25	74.854	80.000	75.000				
MB 7580 DX			59.75														80.25							
MB 8040 DX			79.75														80.25							
MB 8060 DX	80	85	40.50							2.634 2.568		79.900	85.035	80.030	0.176 0.100	8								
MB 8080 DX			39.50																60.50	79.854	85.000	80.000		
MB 80100 DX			59.50																80.50					
MB 8530 DX			79.50																100.50					
MB 8540 DX	85	90	30.50									2.634 2.568		84.880	90.035	85.035	0.209 0.120	9.5						
MB 8560 DX			29.50																		40.50	84.826	90.000	85.000
MB 8580 DX			39.50																		60.50			
MB 85100 DX			59.50	80.50																				
MB 9040 DX	90	95	40.50	2.634 2.568										89.880	95.035	90.035	0.209 0.120	9.5						
MB 9060 DX			39.50																		60.50	89.826	95.000	90.000
MB 9090 DX			59.50																		90.50			
MB 90100 DX			89.50			100.50																		
MB 9560 DX	95	100	60.50			2.634 2.568								94.880	100.035	95.035	0.209 0.120	9.5						
MB 95100 DX			59.50																		100.50	94.826	100.000	95.000
MB 10050 DX			99.50																		50.50			
MB 10060 DX			49.50																		60.50			
MB 10080 DX	100	105	80.50					2.634 2.568						99.880	105.035	100.035	0.209 0.120	9.5						
MB 10095 DX			79.50																		95.50	99.826	105.000	100.000
MB 100115DX			94.50																		115.50			
			114.50																					

10 Standard Products

Part No.	Nominal size		Width B	Wall thickness s_3	Shaft- \varnothing D_J [d8]	Housing- \varnothing D_H [H7]	Bush i- \varnothing $D_{i,a,m}$ machined to [H7]	Clearance C_D	Oil hole - \varnothing d_L			
	D_i	D_o								max. min.	max. min.	max. min.
MB 10560 DX	105	110	60.50	2.634 2.568	104.880 104.826	110.035 110.000	105.035 105.000	0.209 0.120	9.5			
MB 105110 DX			59.50							110.50	115.50	
MB 105115 DX			109.50							114.50	114.50	
MB 11060 DX	110	115	60.50		109.880 109.826	115.035 115.000	110.035 105.000					
MB 110115 DX			59.50							115.50	114.50	
MB 11550 DX			115							120	50.50	114.880 114.826
MB 11570 DX	49.50	70.50	69.95									
MB 12060 DX	120	125	60.50		119.880 119.826	125.040 125.000	120.035 120.000					
MB 120100 DX	59.50	100.50	99.50									
MB 125100 DX	125	130	100.50							124.855 124.792	130.040 130.000	125.040 125.000
MB 13050 DX	130	135	99.50		50.50	129.855 129.792	135.040 135.000					
MB 13060 DX			49.50		60.50							
MB 130100 DX			59.50		100.50					99.50		
MB 13560 DX	135	140	60.50		2.619 2.564	134.855 134.792	140.040 140.000			135.040 135.000	0.248 0.145	-
MB 13580 DX			59.50									
MB 14060 DX			140	145				60.50	139.855 139.792			
MB 140100 DX	59.50	100.50	99.50									
MB 15060 DX	150	155	60.50	149.855 149.792		155.040 155.000	150.040 150.000					
MB 15080 DX			59.50					80.50	79.50			
MB 150100 DX			100.50					99.50				

10.3Inch DX cylindrical bushes

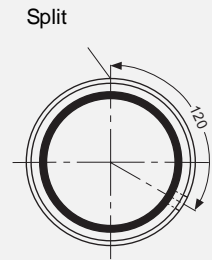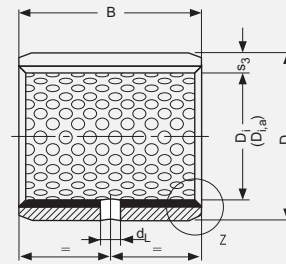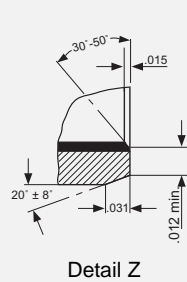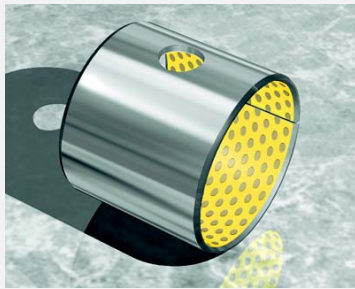

All dimensions in inch

Part Nr.	Nominal size		Wall thick-ness s_3	Width B $\pm 0.010''$	Housing- ϕ D_H	Shaft- ϕ D_J	Bush i- ϕ $D_{i,a}$ as supplied	Shaft for machined bush i- ϕ $D_{J,m}$	Bush i- ϕ $D_{i,a}$ mahined to [H7]	Oil hole- ϕ d_L	Running Clearance C_D as supplied	Running Clearance C_D machined
	D_i	D_o									max. min.	max. min.
06DX06	$3/8$	$15/32$	0.0510 0.0500	0.385	0.4694 0.4687	0.3648 0.3639	0.3694 0.3667	0.3734 0.3725	0.3756 0.3750	No hole	0.0055 0.0019	0.0031 0.0016
06DX08				0.510								
06DX12				0.490								
07DX08	$7/16$	$17/32$		0.760	0.5319 0.5312	0.4273 0.4263	0.4319 0.4292	0.4355 0.4345	0.4382 0.4375		0.0056 0.0019	
07DX12				0.740								
08DX06				0.510								
08DX08	$1/2$	$19/32$		0.490	0.5944 0.5937	0.4897 0.4887	0.4944 0.4917	0.4980 0.4970	0.5007 0.5000		0.0057 0.0020	
08DX10				0.635								
08DX14				0.615								
09DX08				0.885								
09DX12	$9/16$	$21/32$		0.865	0.6569 0.6562	0.5522 0.5512	0.5569 0.5542	0.5605 0.5595	0.5632 0.5625		$5/32$	0.0037 0.0020
10DX08				0.510								
10DX10			0.490									
10DX12	$5/8$	$23/32$	0.635	0.7195 0.7187	0.6146 0.6136	0.6195 0.6167	0.6230 0.6220	0.6257 0.6250	0.0059 0.0021			
10DX14			0.615									
11DX14			0.760									
12DX08	$3/4$	$7/8$	0.740	0.8758 0.8750	0.7390 0.7378	0.7444 0.7412	0.7475 0.7463	0.7508 0.7500	0.0066 0.0022	0.0045 0.0025		
12DX12			1.010									
12DX16			0.990									



10 Standard Products

Part Nr.	Nominal size		Wall thick-ness s_3	Width B $\pm 0.010''$	Housing- \varnothing D_H	Shaft- \varnothing D_J	Bush i- \varnothing $D_{i,a}$ as supplied	Shaft for machined bush i- \varnothing $D_{j,m}$	Bush i- \varnothing $D_{i,a}$ mahined to [H7]	Oil hole- \varnothing d_L	Running Clearance C_D as supplied	Running Clearance C_D machined				
	D_i	D_o									max. min.	max. min.	max. min.	max. min.	max. min.	
14DX12	$7/8$	1	0.0669 0.0657	0.760	1.0008	0.8639	0.8694	0.8725	0.8758	$1/4$	0.0067	0.0045				
14DX14				0.740									0.865	0.8627	0.8713	0.8750
14DX16				1.010									0.990			
16DX12	1	$1 1/8$		0.760	1.1258	0.9888	0.9944	0.9975	1.0008		0.0068					
16DX16				0.740									1.010	0.9876	0.9912	1.0000
16DX24				1.510									1.490			
18DX12	$1 1/8$	$19/32$	0.760	1.2822	1.1138	1.1202	1.1225	1.1258	0.0076							
18DX16			0.740								1.010		1.1126	1.1213	1.2500	
20DX12	$1 1/4$	$1 13/32$	0.760	1.4072	1.2387	1.2452	1.2470	1.2510	0.0081							
20DX16			0.740								1.010		1.2371	1.2454	1.2500	
20DX20			1.260								1.240					
20DX28			1.760								1.740					
22DX16			1.010							0.990						
22DX22	$1 3/8$	$1 17/32$	1.385	1.5322	1.3635	1.3702	1.3720	1.3760	0.0083							
22DX28			0.0824 0.0810							0.365	1.3619	1.3704	1.3750	0.0029		
24DX16	$1 1/2$	$1 21/32$	1.760	1.6572	1.4884	1.4952	1.4970	1.5010	0.0084							
24DX20			1.010							0.990	1.4868	1.4914	1.4954	1.5000		
24DX24			1.260							1.240						
24DX32			1.510							1.490						
26DX16	$1 5/8$	$1 25/32$	2.010	1.7822	1.6133	1.6202	1.6220	1.6260	0.0085							
26DX24			0.0980 0.0962							1.990	1.7812	1.6117	1.6204	1.6250	0.0031	
28DX16	$1 3/4$	$1 15/16$	1.010	1.9385	1.7383	1.7461	1.7470	1.7510	0.0094							
28DX24			0.990							1.510	1.7367	1.7415	1.7454	1.7500		
28DX28			1.510							1.490						
28DX32			1.760							1.740						
30DX16			2.010							1.990						
30DX30	$1 7/8$	$2 1/16$	1.510	2.0637	1.8632	1.8713	1.8720	1.8760	0.0097							
30DX36			0.0980 0.0962							1.490	1.865	1.8616	1.8665	1.8704	1.8750	0.0033
32DX16	2	$2 3/16$	2.260	2.1887	1.9881	1.9963	1.9960	2.0012	0.0100							
32DX24			2.240							2.010	1.9863	1.9915	1.9942	2.0000		
32DX32			1.010							0.990						
32DX40			1.510							1.490						

Part Nr.	Nominal size		Wall thickness s_3	Width B $\pm 0.010''$	Housing- \varnothing D_H	Shaft- \varnothing D_J	Bush i- \varnothing $D_{i,a}$ as supplied	Shaft for machined bush i- \varnothing D_{Jm}	Bush i- \varnothing $D_{i,a}$ machined to [H7]	Oil hole- \varnothing d_L	Running Clearance C_D as supplied	Running Clearance C_D machined	
	D_i	D_o									max. min.	max. min.	max. min.
36DX32	2 ¹ / ₄	2 ⁷ / ₁₆	0.0980 0.0962	2.010	2.4387 2.4375	2.2378 2.2360	2.2463 2.2415	2.2460 2.2442	2.2512 2.2500	5/16	0.0103 0.0037	0.0070 0.0040	
36DX36				1.990									2.260
36DX40				2.240									
40DX32	2 ¹ / ₂	2 ¹¹ / ₁₆		2.510	2.6887 2.6875	2.4875 2.4857	2.4963 2.4915	2.4960 2.4942			2.5012 2.5000		0.0106 0.0040
40DX40				1.990									
44DX32	2 ³ / ₄	2 ¹⁵ / ₁₆		2.490	2.9387 2.9375	2.7351 2.7333	2.7457 2.7393	2.7460 2.7442			2.7512 2.7500		0.0124 0.0042
44DX40			2.010	3.010									
44DX48			1.990	2.990									
44DX56			2.510	3.010									
48DX32	3	3 ³ / ₁₆	3.740	3.1889 3.1875	2.9849 2.9831	2.9959 2.9893	2.9960 2.9942	3.0012 3.0000	0.0128 0.0044				
48DX48			2.010							3.010			
48DX60			1.990							2.990			
56DX40	3 ¹ / ₂	3 ¹¹ / ₁₆	3.740	3.6889 3.6875	3.4844 3.4822	3.4959 3.4893	3.4950 3.4928	3.5014 3.5000	0.0137 0.0049				
56DX48			2.510							3.010			
56DX60			2.490							2.990			
64DX48	4	4 ³ / ₁₆	4.740	4.1889 4.1875	3.9839 3.9817	3.9959 3.9893	3.9950 3.9928	4.0014 4.0000	0.0142 0.0054				
64DX60			3.010							3.760			
64DX76			2.990							3.740			

10 Standard Products



10.4DX Thrust Washers - metric

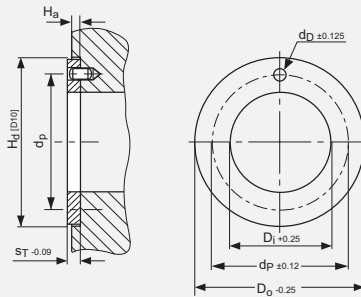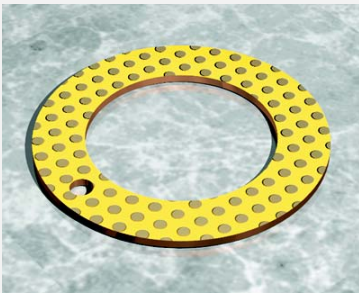

All dimensions in mm

Part No.	Inside- ϕ D_i	Outside- ϕ D_o	Thickness s_T	Dowel hole PCD- ϕ d_p	Dowel hole- ϕ d_D	Recess depth H_a
	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.
WC10DX	12.25 12.00	24.00 23.75	1.577 1.487	18.12 17.88	1.875 1.625	1.20 0.95
WC12DX	14.25 14.00	26.00 25.75		20.12 19.88	2.375 2.125	
WC14DX	16.25 16.00	30.00 29.75		22.12 21.88		
WC16DX	18.25 18.00	32.00 31.75		25.12 24.88		
WC18DX	20.25 20.00	36.00 35.75		28.12 27.88	3.375 3.125	
WC20DX	22.25 22.00	38.00 37.75		30.12 29.88		
WC22DX	24.25 24.00	42.00 41.75		33.12 32.88		
WC24DX	26.25 26.00	44.00 43.75		35.12 34.88		
WC25DX	28.25 28.00	48.00 47.75		38.12 37.88	4.375 4.125	
WC30DX	32.25 32.00	54.00 53.75		43.12 42.88		
WC35DX	38.25 38.00	62.00 61.75		50.12 49.88		
WC40DX	42.25 42.00	66.00 65.75		54.12 53.88		
WC45DX	48.25 48.00	74.00 73.75		61.12 60.88	1.70 1.45	
WC50DX	52.25 52.00	78.00 77.75		65.12 64.88		

10.5DX Thrust Washers - inch

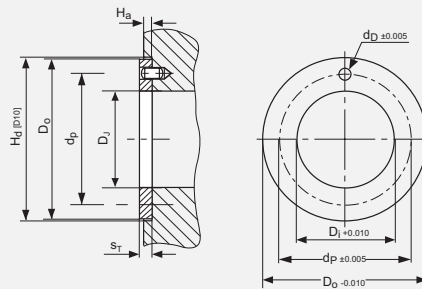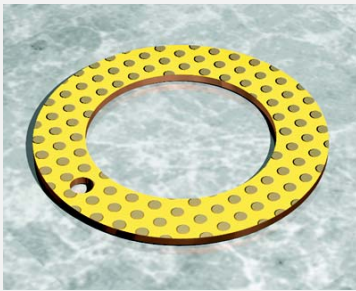


All dimensions in inch

Part No.	Inside-ø D _i	Outside-ø D _o	Thickness S _T	Dowel hole PCD-ø d _p	Dowel hole-ø d _D	Recess depth H _a
	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.
DX06	0.5100 0.5000	0.8750 0.8650	0.0660 0.0625	0.6920 0.6820	0.0770 0.0670	0.0500 0.0400
DX07	0.5720 0.5620	1.0000 0.9900		0.7860 0.7760		
DX08	0.6350 0.6250	1.1250 1.1150		0.8800 0.8700	0.1090 0.0990	
DX09	0.6970 0.6870	1.1870 1.1770		0.9420 0.9320		
DX10	0.7600 0.7500	1.2500 1.2400		1.0050 0.9950		
DX11	0.8220 0.8120	1.3750 1.3650		1.0990 1.0890	0.1400 0.1300	
DX12	0.8850 0.8750	1.5000 1.4900		1.1920 1.1820		
DX14	1.0100 1.0000	1.7500 1.7400		1.3800 1.3700	0.1710 0.1610	
DX16	1.1350 1.1250	2.0000 1.9900		1.5670 1.5570		
DX18	1.2600 1.2500	2.1250 2.1150		1.6920 1.6820		
DX20	1.3850 1.3750	2.2500 2.2400		1.8170 1.8070	0.2020 0.1920	
DX22	1.5100 1.5000	2.5000 2.4900		2.0050 1.9950		
DX24	1.6350 1.6250	2.6250 2.6150		2.1300 2.1200		
DX26	1.7600 1.7500	2.7500 2.7400		2.2550 2.2450		
DX28	2.0100 2.0000	3.0000 2.9900		2.5050 2.4950		
DX30	2.1350 2.1250	3.1250 3.1150		2.6300 2.6200		
DX32	2.2600 2.2500	3.2500 3.2400		2.7550 2.7450	0.0800 0.0700	

10 Standard Products

10.6DX Strip - metric

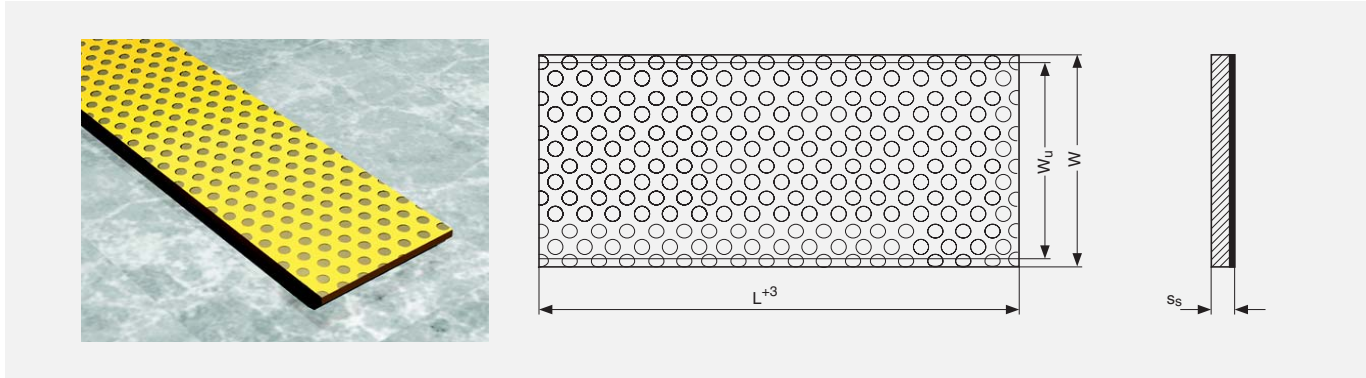

All dimensions in mm

Group No.	Length L	Usable Width W_u	Thickness s_s	
			max.	min.
S100 90 DX	500	93	1.07	1.03
S152 00 DX		200	1.56	1.52
S202 00 DX		218	2.05	2.01
S252 00 DX			2.57	2.52

10.7DX Strip - inch

All dimensions in inch

Group No.	Length L	Usable Width W_u	Thickness s_s	
			max.	min.
B	18	2.75 ± 0.010	0,0492	0,0480
C		4 ± 0.010	0,0642	0,0630
D		4 ± 0.012	0,0795	0,0783
E			0,0949	0,0937

GGB warrants that products described in this brochure are free from defects in workmanship and material but unless expressly agreed in writing GGB gives no warranty that these products are suitable for any particular purpose or for use under any specific conditions notwithstanding that such purpose would appear to be covered by this publication. GGB accepts no liability for any loss, damage, or expense whatsoever arising directly or indirectly from use of its products. All business undertaken by GGB is subject to its standard Conditions of Sale, copies of which are available upon request. GGB products are subject to continual development and GGB reserves the right to make changes in the specification and design of its products without prior notice.

GLACIER™ is a Trademark of GGB.

DX™ is a Trademark of GGB.

DS™ is a Trademark of GGB.