

Hi-eX Marginally lubricated



Designer's Handbook

Quality

All the products described in this handbook are manufactured under DIN ISO 9001/2 or QS 9000 approved quality management systems.



T

Formula Symbols and Designations

Formula Symbol	Unit	Designation
a _B	-	Bearing size factor
a _E	-	High load factor
a _Q	-	Speed/Load factor
a _s	-	Surface finish factor
a _T	-	Temperature application factor
В	mm	Nominal bush width
с	1/min	Dynamic load frequency
CD	mm	Installed diametral clearance
C _{Dm}	mm	Diametral clearance machined
C _T	-	Total number of dynamic load cycles
Ci	mm	ID chamfer length
C _o	mm	OD chamfer length
D _H	mm	Housing Diameter
Di	mm	Nominal bush/thrust washer ID
D _{i,a}	mm	Bush ID when assembled in housing
D _{i,a,m}	mm	Bush ID assembled and machined
DJ	mm	Shaft diameter
Do	mm	Nominal bush/thrust washer OD
d _D	mm	Dowel hole diameter
dL	mm	Oil hole diameter
d _P	mm	Pitch circle diameter for dowel hole
F	N	Bearing load
F _i	N	Insertion force
f	-	friction
L	mm	Strip length
L _H	h	Bearing service life
L _{RG}	h	Relubrication interval
N	1/min	Rotational speed
N _{osz}	1/min	Oscillating movement frequency

Formula Symbol	Unit	Designation
p	N/mm ²	Specific load
p _{lim}	N/mm ²	Specific load limit
p _{sta,max}	N/mm ²	Maximum static load
p _{dyn,max}	N/mm ²	Maximum dynamic load
Q	-	Total number of cycles
R	-	Number of lubrication intervals
R _a	μ m	Surface roughness (DIN 4768, ISO/DIN 4287/1)
S ₃	mm	Bush wall thickness
S _S	mm	Strip thickness
S _T	mm	Thrust washer thickness
τ	°C	Temperature
T _a	mm	Depth of Housing Recess
T _{amb}	°C	Ambient temperature
T _{max}	°C	Maximum temperature
T _{min}	°C	Minimum temperature
U	m/s	Sliding speed
u	-	speed factor
W	mm	Strip width
<i>W</i> _u	mm	Maximum usable strip width
α1	1/10 ⁶ K	Coefficient of linear thermal expansion parallel to surface
α2	1/10 ⁶ K	Coefficient of linear thermal expansion normal to surface
σ _c	N/mm ²	Compressive Yield strength
λ	W/mK	Thermal conductivity
φ	0	Angular displacement
η	Ns/mm ²	Dynamic Viscosity
ZT	-	Total number of osscillating movements

Content

	Quality Formula Symbols and	
	Designations	II
1	Introduction	4
1.1	Characteristics and Advantages	4
2	Structure	4
2.1	Basic Forms	5
3	Properties	6
3.1	Physical Properties	6
3.2	Chemical Properties	6
4	Lubrication and Friction .	7
4.1	Dry operation	7
4.2	Choice of Lubricant	7 7
	Grease	7
	Non lubricating fluids	7
4.3	Friction	9
4.4	Lubricated Environments	9 9
4.5	Characteristics of Fluid Lubricated Hi-eX Bearings	10
4.6	Design Guidance for Fluid Lubricated Applications	10
4.7		12 12
5	Design Factors 1	3
5.1	Specific Load	13 13
5.2	Continuous Rotation	14 14 14
5.3	pU Factor	15
5.4		15 15
5.5	Temperature	17
5.6	J	17
5.7	Bearing Size	18

5.8	Estimation of Bearing Service Life	
		18
		18 19
	3	19
	Oscillating Motion	
	and Dynamic Loads	19
5.9	Worked Examples	20
6.1	Data for bearing design calculations	21
7.1	Dimensions and Tolerances	22
7.2	Tolerances for	
		22
		22
	Fluid Lubrication	24
		24
7.3		25
7.4	•	26
		26
		26
	5	27 27
	5	27
		27
	Fitting of Thrust Washers	
8	Fitting of Thrust Washers Slideways	27
8 8.1	Fitting of Thrust Washers Slideways Machining	27 28
•	Fitting of Thrust Washers Slideways Machining Machining Practice	27 28 29
8.1	Fitting of Thrust Washers Slideways Machining Machining Practice Boring	27 28 29 29
8.1 8.2	Fitting of Thrust Washers Slideways Machining Machining Practice Boring Reaming	27 28 29 29 29 29
8.1 8.2 8.3	Fitting of Thrust Washers Slideways Machining Machining Practice Boring Reaming Broaching	27 28 29 29 29 30
8.1 8.2 8.3 8.4	Fitting of Thrust Washers Slideways Machining Machining Practice Boring Reaming Broaching Vibrobroaching	27 28 29 29 29 30 30
8.1 8.2 8.3 8.4 8.5	Fitting of Thrust Washers Slideways Machining Machining Practice Boring Reaming Broaching Vibrobroaching Modification of components	27 28 29 29 29 30 30 31
8.1 8.2 8.3 8.4 8.5 8.6	Fitting of Thrust Washers Slideways Machining Machining Practice Boring Reaming Broaching Vibrobroaching Modification of components	27 28 29 29 30 30 31 31 31
8.1 8.2 8.3 8.4 8.5 8.6 8.7	Fitting of Thrust Washers Slideways Machining Machining Practice Boring Reaming Broaching Vibrobroaching Modification of components Drilling Oil Holes	27 28 29 29 30 30 31 31 31 31
8.1 8.2 8.3 8.4 8.5 8.6 8.7 8.8	Fitting of Thrust Washers Slideways Machining Machining Practice Boring Reaming Broaching Vibrobroaching Modification of components Drilling Oil Holes Cutting Strip Material Hi-eX Components	27 28 29 29 30 30 31 31 31 31 31 31 31 32 32
8.1 8.2 8.3 8.4 8.5 8.6 8.7 8.8 9	Fitting of Thrust Washers Slideways Machining Practice Boring Reaming Broaching Vibrobroaching Modification of components Drilling Oil Holes Cutting Strip Material Electroplating Hi-eX Components Mating Surfaces	27 28 29 29 30 30 31 31 31 31 31 31 31 32 32
8.1 8.2 8.3 8.4 8.5 8.6 8.7 8.8 9	Fitting of Thrust Washers Slideways Machining Machining Practice Boring Boring Reaming Broaching Vibrobroaching Modification of components Drilling Oil Holes Cutting Strip Material Electroplating Hi-eX Components Mating Surfaces Standard Products	27 28 29 29 30 30 31 31 31 31 31 31 31 32 32
8.1 8.2 8.3 8.4 8.5 8.6 8.7 8.8 9 10	Fitting of Thrust Washers Slideways Machining Machining Practice Boring Reaming Broaching Vibrobroaching Modification of components Drilling Oil Holes Cutting Strip Material Electroplating Hi-eX Components Mating Surfaces Standard Products I PM-HX cylindrical bushes	27 28 29 29 30 30 31 31 31 31 31 32 32 32 33 33 33
8.1 8.2 8.3 8.4 8.5 8.6 8.7 8.8 9 10 10.1 10.2	Fitting of Thrust Washers Slideways Machining Machining Practice Boring Reaming Broaching Vibrobroaching Modification of components Drilling Oil Holes Cutting Strip Material Hi-eX Components Mating Surfaces Standard Products 2 MB-HX cylindrical bushes	27 28 29 29 30 30 31 31 31 31 31 32 32 33 33 40
8.1 8.2 8.3 8.4 8.5 8.6 8.7 8.8 9 10 10.1 10.2 10.3	Fitting of Thrust Washers Slideways Machining Machining Practice Boring Reaming Broaching Vibrobroaching Modification of components Drilling Oil Holes Cutting Strip Material Electroplating Hi-eX Components Mating Surfaces Standard Products I PM-HX cylindrical bushes	27 28 29 29 30 30 31 31 31 31 31 32 32 33 33 40 45

1 Introduction

The purpose of this handbook is to provide comprehensive technical information on the characteristics of Hi-eXTM bearings. The information given, permits designers to establish the correct size of bearing required and the expected life and performance. Glacier Garlock Bearings Research and Development services are available to assist with unusual design problems.

Complete information on the range of HieX standard products is given together with details of other HieX products.

Glacier Garlock Bearings is continually refining and extending its experimental and theoretical knowledge and, therefore, when using this brochure it is always worthwhile to contact the Company should additional information be required.

Customers are advised to carry out prototype testing wherever possible.

1.1 Characteristics and Advantages

- Hi-eX provides maintenance free operation
- Hi-eX has a high pU capability
- · Hi-eX exhibits low wear rate
- Seizure resistant
- Suitable for temperatures from -150 °C to +250 °C
- · High static and dynamic load capacity
- Hi-eX polymer bearing lining has good chemical resistance

2 Structure

Hi-eX is a composite bearing material developed specifically to operate with marginal lubrication and consists of three bonded layers: a steel backing strip and a sintered porous bronze matrix, impregnated and overlaid with a PEEK (polyether ether ketone) polymer bearing material, containing fillers including PTFE (polytertafluorethylene).

The steel backing provides mechanical strength and the bronze interlayer provides a strong mechanical bond for the lining. This construction promotes dimensional stability and improves thermal conductivity, thus reducing the temperature at the bearing surface.


For grease lubricated applications Hi-eX is manufactured with a polymer overlay thickness above the bronze sinter layer of 0.30 mm nominal, and the bearing surface is provided with a uniform pattern of indents. These serve as a reservoir for the grease • No water absorption and therefore dimensionally stable

- · Compact and light
- Suitable for rotating, oscillating, reciprocating and sliding movements
- Hi-eX bearings are prefinished and require no machining after assembly
- Suitable for use with low viscosity and low lubricant fluids.

and are designed to provide the optimum distribution of the lubricant over the bearing surface (e.g. PM2020HX).

For fluid lubricated applications where the bearing surface may be required to be machined subsequent to assembly, Hi-eX is manufactured with a polymer overlay thickness above the bronze sinter layer of 0.30 mm nominal, and the indent pattern omitted from the bearing surface (e.g. PM2020 HX (U)).





2

2.1 Basic Forms

Hi-eX is **not** available from stock and is manufactured only to order as follows:

Standard Components

These products are manufactured to International, National or Glacier Garlock Bearings standard designs.

- · Cylindrical Bushes
 - **PM** pre finished **metric** range, not machinable in situ, for use with stan-
- dard journals finished to h6-h8 limits. - **MB** machinable **metric** range, with an
- allowance for machining in situ. • Thrust Washers
- Strip Material







Fig. 2: Standard components

Non Standard Components

These products are manufactured to customers' requirements with or without Glacier Garlock Bearings recommendations, and include for example

- Half Bearings
- Flat Components
- Pressings Stampings
- · Modified Standard Components

Fig. 3: Non standard components

3 Properties

3.1 Physical Properties

	Characteristic	Symbol	Value Hi-eX	Unit	Comments
Physical	Thermal Conductivity	λ	52	W/mK	
Properties	Coefficient of linear thermal expansion :				
	parallel to surface	α ₁	11	1/10 ⁶ K	
	normal to surface	α2	29	1/10 ⁶ K	
	Maximum Operating Temperature	7 _{max}	250	°C	
	Minimum Operating Temperature	⁷ min	-150	°C	
Mechanical Properties	Compressive Yield Strength	σ _c	380	N/mm ²	measured on disc 5 mm dia- meter x 2.45 mm thick.
	Maximum Load				
	Static	p _{sta,max}	140	N/mm ²	
	Dynamic	p _{dyn,max}	140	N/mm ²	
Electrical Properties	Volume resistivity of PEEK lining		>10 ⁹	Ω cm	

Table 1: Physical, mechanical and electrical properties of Hi-eX

3.2 Chemical Properties

The following table provides an indication of the resistance of Hi-eX to various chemical media. It is recommended that the chemical resistance is confirmed by testing if possible.

	Chemical	%	°C	Rating
Strong Acids	Hydrochloric Acid	5	20	-
	Nitric Acid	5	20	-
	Sulphuric Acid	5	20	-
Weak Acids	Acetic Acid	5	20	-
	Formic Acid	5	20	-
Bases	Ammonia	10	20	ο
	Sodium Hydroxide	5	20	ο
Solvents	Acetone		20	+
	Carbon Tetrachloride		20	+
Lubricants and fuels	Paraffin		20	+
	Gasolene		20	+
	Kerosene		20	+
	Diesel fuel		20	+
	Mineral Oil		70	+
	HFA-ISO46 High Water fluid		70	+
	HFC-Water-Glycol		70	+
	HFD-Phosphate Ester		70	+
	Water		20	ο
	Sea Water		20	-

Table 2: Chemical resistance of Hi-eX

-	+	Corrosion damage is unlikely to occur.
(0	Acceptable: Some corrosion damage may occur but this will not be suf- ficient to impair either the structural integrity or the tribo- logical performance of the material.
	-	Unsatisfactory: Corrosion damage will occur and is likely to affect either the structural integrity and/or the tribological performance of the material.

Satisfactory:

4 Lubrication and Friction

4.1 Dry operation

Hi-eX will operate satisfactorily without lubrication under light duty running conditions at $\overline{p}U$ factors below 0.01 N/mm² x m/s and

4.2 Choice of Lubricant

Hi-eX will generally be lubricated, the choice of lubricant depending upon:

sliding speeds below 2.5 m/s. The wear performance should be confirmed by testing if possible.

- pU and sliding speed
- the stability of the lubricant under the operating conditions.

Grease

The performance ratings of different types of grease are indicated in Table 3. Greases containing EP additives or significant additions of graphite or MoS_2 are not generally recommended for use with Hi-eX.

Hi-eX is able to withstand environmental temperatures beyond those generally suitable for grease lubrication and the performance is therefore likely to be limited by

Oil

Hi-eX is recommended for use with oil lubrication. Hi-eX is compatible with mineral oils up to 150 °C and is resistant to the oxidation products which may occur with mineral oils at temperatures above 115 °C.

Non lubricating fluids

Hi-eX has been found to perform satisfactorily with low viscosity and non lubricating fluids such as polyethylene glycol and polyglycol lubricants, water-oil emulsion, shock-absorber oils, kerosene and water.

In general, the fluid will be acceptable if it does not chemically attack the PEEK lining or the porous bronze interlayer. Chemical resistance data are given in Table 2.

Where there is doubt about the suitability of a fluid, a simple test is to submerge a

the lubricant and not by the bearing material. For environmental temperatures above 80°C suitability of the grease should be established by test and a silicone oil base or high temperature grease is recommended. For applications above 150 °C \overline{pU} values should be limited to below 1.0 N/mm² x m/s and re-lubrication intervals should not exceed 500 hours.

Degradation of oils is likely to occur following extended exposure to high temperatures and synthetic lubricants are recommended under these circumstances.

sample of Hi-eX material in the fluid for two to three weeks at 15-20 °C above the operating temperature. The following will usually indicate that the fluid is not suitable for use with Hi-eX.

- A significant change in the thickness of the Hi-eX material,
- A visible change in the bearing surface from polished to matt.
- A visible change in the microstructure of the bronze interlayer

4 Lubrication and Friction

+	Recommended
0	Satisfactory
-	Not recommended
NA	Data not available

Manufacturer	Grade		Туре		
Manulacturer	Grade	Oil	Thickener	Rating	
BP	Energrease LS2	Mineral	Lithium Soap	+	
	Energrease LT2	Mineral	Lithium Soap	+	
	Energrease FGL	Mineral	Non Soap	0	
	Energrease GSF	Synthetic	NA	0	
Century	Lacerta ASD	Mineral	Lithium/Polymer	0	
	Lacerta CL2X	Mineral	Calcium	-	
Dow Corning	Molykote 55M	Silicone	Lithium Soap	0	
	Molykote PG65	PAO	Lithium Soap	+	
	Molykote PG75	Synthetic/Mineral	Lithium Soap	0	
	Molykote PG602	Mineral	Lithium Soap	0	
Elf	Rolexa.1	Mineral	Lithium Soap	+	
	Rolexa.2	Mineral	Lithium Soap	0	
	Epexelf.2	Mineral	Lithium/Calcium Soap	-	
Esso	Andok C	Mineral	Sodium Soap	ο	
	Andok 260	Mineral	Sodium Soap	0	
	Cazar K	Mineral	Calcium Soap	-	
Mobil	Mobilplex 47	Mineral	Calcium Soap	-	
	Mobiltemp 1	Mineral	Non Soap	ο	
Rocol	BG622	White Mineral	Calcium Soap	0	
	Sapphire	Mineral	Lithium Complex	-	
	White Food Grease	White Oil	Clay	-	
Shell	Albida R2	Mineral	Lithium Complex	+	
	Axinus S2	Mineral	Lithium	0	
	Darina R2	Mineral	Inorganic Non Soap	+	
	Stamina U2	Mineral	Polyurea	-	
	Tivela A	Synthetic	NA	ο	
Total	Aerogrease	Synthetic	NA	+	
	Multis EP2	NA	Lithium	+	

Table 3: Performance of greases

4.3 Friction

The coefficient of friction of lubricated Hi-eX depends upon the actual operating conditions as indicated in section 4.4.

4.4 Lubricated Environments

The following sections describe the basics of lubrication and provide guidance on the

Lubrication

There are three modes of lubricated bearing operation which relate to the thickness of the developed lubricant film between the bearing and the mating surface.

- - · Lubricant Viscosity and Flow

Hydrodynamic lubrication

Characterised by:

(4.4.1)

- · Complete separation of the shaft from the bearing by the lubricant film
- · Very low friction and no wear of the bearing or shaft since there is no contact
- Coefficients of friction of 0.001 to 0.01

Hydrodynamic conditions occur when

· Combination of hydrodynamic

· Part of the load is carried by localised areas of self pressurised lubricant and the remainder supported by boundary

· Friction and wear depend upon the hydrodynamic

Mixed film lubrication

boundary lubrication.

of

Characterised by:


lubrication.


developed.

degree

 $\overline{p} \leq \frac{U \cdot \eta}{7.5} \cdot \frac{B}{D_i}$

· Hi-eX provides low friction and high wear resistance to support the boundary lubricated element of the load.





Mixed film lubrication Fig. 5:

Where frictional characteristics are critical


to a design they should be established by

application of Hi-eX in such environments.

These three modes of operation depend upon:

- · Bearing dimensions
- Clearance
- · Load and Speed

prototype testing.



Hydrodynamic lubrication Fig. 4:

and

support

[N/mm²]

Boundary lubrication

Characterised by:

- Rubbing of the shaft against the bearing with virtually no lubricant separating the two surfaces.
- Bearing material selection is critical to performance.
- Shaft wear is likely due to contact between bearing and shaft.
- The excellent properties of Hi-eX material minimises wear under these conditions.
- The dynamic coefficient of friction with Hi-eX is typically 0.02 to 0.15 under boundary lubrication conditions.

 The static coefficient of friction with HieX is typically 0.05 to 0.20 under boundary lubrication conditions.




Fig. 6: Boundary lubrication

4.5 Characteristics of Fluid Lubricated Hi-eX Bearings

Hi-eX is particularly effective in the most demanding of lubricated applications

· High load conditions

In highly loaded applications operating under boundary or mixed film conditions Hi-eX shows excellent wear resistance.

- Start up and shut down under load With insufficient speed to generate a hydrodynamic film the bearing will operate under boundary or mixed film conditions.
 - Hi-eX minimises wear

be maintained, for example:

where full hydrodynamic operation cannot

· Sparse lubrication

Many applications require the bearing to operate with less than the ideal lubricant supply, typically with splash or mist lubrication only.

The PEEK lining of Hi-eX has low thermal conductivity relative to conventional metallic bearings, and therefore depending upon the operating conditions may require a greater lubricant supply to remove the generated heat in the bearing.

- Hi-eX shows greater wear resistance than conventional metallic bearings.

4.6 Design Guidance for Fluid Lubricated Applications

Fig. 7, Page 11 shows the three lubrication regimes discussed above plotted on a

In order to use Fig. 7

- Using the formulae in Section 5
 - Calculate the specific load \overline{p}
 - Calculate the shaft surface speed U

Note:

Viscosity is a function of operating temperature. If the operating temperature of the fluid is unknown, a provisional temperature of 25 °C above ambient can be used. graph of sliding speed vs the ratio of specific load to lubricant viscosity.

- Using the viscosity temperature relationships presented in Table 4.
 - Determine the viscosity in centipoise of the lubricant.

Area 1 of Fig. 7

The bearing will operate with boundary lubrication.

The $\overline{p}U$ factor will be the major determinant of bearing life.

If
$$epU/\eta \le 0.2$$
 then

$$(4.6.1) \qquad [h] L_{H} = \frac{2250}{\left(\frac{e\bar{p}U}{\eta}\right)^{0.5}} \cdot a_{Q} \cdot a_{T} \cdot a_{S}$$

If 0.2 < $e\overline{p}U/\eta \leq 1.0$ then

$$L_{H} = \frac{1000}{\left(\frac{e\bar{p}U}{\eta}\right)} \cdot a_{Q} \cdot a_{T} \cdot a_{S}$$

[h]

Area 2 of Fig. 7

The bearing will operate with mixed film lubrication.

pU factor is no longer a significant parameter in determining the bearing life.

Area 3 of Fig. 7

The bearing will operate with hydrodynamic lubrication. Bearing wear will be determined only by the cleanliness of the

Area 4 of Fig. 7

- These are the most demanding operating conditions.
- The bearing is operated under either high speed or high bearing load to viscosity ratio, or a combination of both.
- These conditions may cause

Hi-eX bearing performance can be estimated from the following:

Calculate Effective $\overline{p}U$ Factor from Section 5.8.


If
$$e\overline{p}U/\eta > 1.0$$
 then
(4.6.3) [h]

$$L_{H} = \frac{1000}{\left(\frac{e\overline{p}U}{\eta}\right)^{2}} \cdot a_{Q} \cdot a_{T} \cdot a_{S}$$

Hi-eX bearing performance will depend upon the nature of the fluid and the actual service conditions.

lubricant and the frequency of start up and shut down.

- excessive operating temperature
- and/or high wear rate.
- Bearing performance may be improved:
 - by use of unindented Hi-eX lining
 - by the addition of one or more grooves to the bearing
 - by shaft surface finish < 0.05 [μ m R_a].

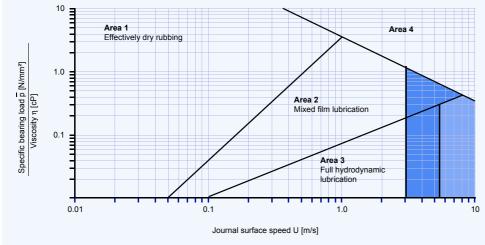

Increased clearances may be necessary

Detail bearing design may be necessary - consult the company

Conditions:

- Steady unidirectional loading

- Continuous, non reversing shaft rotation
 Sufficient clearance between shaft and bearing
- Sufficient lubricant flow

Fig. 7: Design guide for lubricated application

10													
	20	30	40	50	60	70	80	90	100	110	120	130	140
146	77	44	27	18	13	9.3	7.0	5.5	4.4	3.6	3.0	2.5	2.2
247	121	67	40	25	17	12	9.0	6.9	5.4	4.4	3.6	3.0	2.6
395	190	102	59	37	24	17	12	9.3	7.2	5.8	4.7	3.9	3.3
780	335	164	89	52	33	22	15	11.3	8.6	6.7	5.3	4.3	3.6
1290	540	255	134	77	48	31	21	15	11	8.8	7.0	5.6	4.6
4.0	3.4	3.0	2.6	2.3	2.0	1.7	1.4	1.1	0.95				
0.56	0.52	0.48	0.44	0.40	0.36	0.33	0.31						
1.7	1.5	1.3	1.1	0.95	0.85	0.75	0.65	0.60	0.55				
1.30	1.0	0.84	0.69	0.55	0.48	0.41	0.34	0.32	0.28				
	247 395 780 1290 4.0 0.56 1.7	247 121 395 190 780 335 1290 540 4.0 3.4 0.56 0.52 1.7 1.5 1.30 1.0	247 121 67 395 190 102 780 335 164 1290 540 255 4.0 3.4 3.0 0.56 0.52 0.48 1.7 1.5 1.3 1.30 1.0 0.84	2471216740395190102597803351648912905402551344.03.43.02.60.560.520.480.441.71.51.31.11.301.00.840.69	247121674025395190102593778033516489521290540255134774.03.43.02.62.30.560.520.480.440.401.71.51.31.10.951.301.00.840.690.55	24712167402517395190102593724780335164895233129054025513477484.03.43.02.62.32.00.560.520.480.440.400.361.71.51.31.10.950.851.301.00.840.690.550.48	2471216740251712395190102593724177803351648952332212905402551347748314.03.43.02.62.32.01.70.560.520.480.440.400.360.331.71.51.31.10.950.850.41	24712167402517129.0395190102593724171278033516489523322151290540255134774831214.03.43.02.62.32.01.71.40.560.520.480.440.400.360.330.311.71.51.31.10.950.850.750.651.301.00.840.690.550.480.410.34	24712167402517129.06.939519010259372417129.3780335164895233221511.3129054025513477483121154.03.43.02.62.32.01.71.41.10.560.520.480.440.400.360.330.31111.71.51.31.10.950.480.410.340.321.301.00.840.690.550.480.410.340.32	24712167402517129.06.95.439519010259372417129.37.2780335164895233221511.38.612905402551347748312115114.03.43.02.62.32.01.71.41.10.950.560.520.480.440.400.360.330.311.71.51.31.10.950.850.750.650.600.551.301.00.840.690.550.480.410.340.320.28	247 121 67 40 25 17 12 9.0 6.9 5.4 4.4 395 190 102 59 37 24 17 12 9.0 6.9 5.4 4.4 395 190 102 59 37 24 17 12 9.3 7.2 5.8 780 335 164 89 52 33 22 15 11.3 8.6 6.7 1290 540 255 134 77 48 31 21 15 11 8.8 4.0 3.4 3.0 2.6 2.3 2.0 1.7 1.4 1.1 0.95 . 0.56 0.52 0.48 0.40 0.36 0.33 0.31 . . . 1.7 1.5 1.3 1.1 0.95 0.85 0.75 0.65 0.60 0.55 . 1.30 1.0	247 121 67 40 25 17 12 9.0 6.9 5.4 4.4 3.6 395 190 102 59 37 24 17 12 9.3 7.2 5.8 4.7 780 335 164 89 52 33 22 15 11.3 8.6 6.7 5.3 1290 540 255 134 77 48 31 21 15 11 8.8 7.0 4.0 3.4 3.0 2.6 2.3 2.0 1.7 1.4 1.1 0.95 0.56 0.52 0.48 0.44 0.40 0.36 0.33 0.31 1.7 1.5 1.3 1.1 0.95 0.85 0.75 0.65 0.60 0.55 1.30 1.0 0.84 0.69 0.55 0.48 0.41 0.34 0.32	247 121 67 40 25 17 12 9.0 6.9 5.4 4.4 3.6 3.0 395 190 102 59 37 24 17 12 9.3 7.2 5.8 4.7 3.9 780 335 164 89 52 33 22 15 11.3 8.6 6.7 5.3 4.3 1290 540 255 134 77 48 31 21 15 11 8.8 7.0 5.6 4.0 3.4 3.0 2.6 2.3 2.0 1.7 1.4 1.1 0.95 5.6 4.0 3.4 3.0 2.6 2.3 2.0 1.7 1.4 1.1 0.95 0.56 0.52 0.48 0.40 0.36 0.33 0.31 1.7 1.5 1.3

Table 4: Viscosity data

4.7 Wear Rate and Re-lubrication Intervals with Grease lubrication

At specific bearing loads below 100 N/mm² a grease lubricated Hi-eX bearing shows only small bedding-in wear of about 0.0025 mm. This is followed by little wear during the early part of the bearing life until the lubricant becomes exhausted and the wear rate increases. If the bearing is regreased before the rate of wear starts to increase rapidly the material will continue to function satisfactorily with little wear. Fig. 8 shows the typical wear pattern. Under specific loads above 100 N/mm² the initial bedding-in wear is greater, typically about 0.025 mm, followed by a decreasing wear rate until the bearing exhibits a similar wear/life relationship to that shown in Fig. 8.

The useful life of the bearing is limited by wear in the loaded area. If this wear exceeds 0.15mm the grease capacity of the indents is reduced and more frequent regreasing of the bearing will be required.

Fretting Wear

Oscillating movements of less than the dimensions of the indent pattern may cause localised wear of the mating surface after prolonged usage. This will result in the indent pattern becoming transferred onto the mating surface in contact with the Hi-eX bearing and may also give rise to fretting corrosion damage. In this situation DSTM material should be considered as an alternative to Hi-eX.

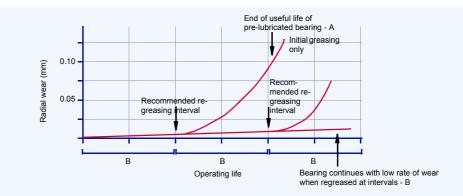


Fig. 8: Typical wear of Hi-eX

5 Design Factors

The main parameters when determining the size or calculating the service life for a Hi-eX bearing are:

- Specific Load Limit plim [N/mm²]
- pU Factor [N/mm² x m/s]

5.1 Specific Load

The specific load \overline{p} is defined as the working load devided by the projected area of

[N/mm²]

+ Mating surface roughness $R_a\left[\mu m\right]$

- · Mating surface material
- Temperature T [°C]
- Other environmental factors eg. housing design, dirt, lubrication.

the bearing and is expressed in N/mm².

Bushes (5.1.1)

$$\overline{p} = \frac{F}{D_i \cdot B}$$

Thrust Washers

(5.1.2)
$$\bar{p} = \frac{4F}{\pi \cdot (D_o^2 - D_i^2)}$$
 [N/mm²

p

$$=\frac{F}{L\cdot W}$$

[N/mm²]

Specific Load Limit

The maximum load which can be applied to a Hi-eX bearing can be expressed in terms of the Specific Load Limit, which depends on the type of the loading and lubrication. It is highest under steady loads. Conditions of dynamic load or oscillating movement which produce fatigue stress in the bearing result in a reduction in the specific load limit. The values of Specific Load Limit specified in Table 5 assume good alignment between the bearing and mating surface. The Specific Load Limit for Hi-eX reduces for bearing operating temperatures in excess of 70 $^{\circ}$ C, falling to about half the values given in Table 5 for temperatures above 150 $^{\circ}$ C.


Conditions of dynamic load or oscillating movement which produce fatigue stress in the bearing result in a reduction in the permissible Specific Load Limit (Fig. 9, Page 14).


Load	Operating condition	Lubrication	p _{lim}
Steady	Intermittent or very slow (below 0.01 m/s) continuous rotation or oscillating motion	Grease or oil	140
Steady	Continuous rotation or oscillating motion	Grease or oil (bound- ary lubrication)	90
Steady or dynamic	Continuous rotation or oscillating motion	Oil (hydrodynamic lub- rication)	60

Table 5: Specific load limit plim for Hi-eX

🔿 GLACIER GARLOCK BEARINGS

5 Design Factors

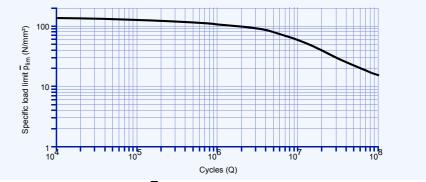



[N/mm²]

5.2 Sliding Speed

The sliding speed U [m/s] is calculated as follows:

Continuous Rotation

Bushes (5.2.1)

 $U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3}$

I hrust V	vashers	
(5.2.2)	$II = \frac{D_o + D_i}{2} \cdot \pi \cdot N$	[N/mm²]
	60.10^3	




Fig. 10: Oscillating cycle ϕ

Oscillating Movement

Bushes
(5.2.3) [N/mm²]
$$U = \frac{D_i \cdot \pi}{60 \cdot 10^3} \cdot \frac{4\varphi \cdot N_{osz}}{360}$$

The maximum permissible effective pU

factor (epU factor) for grease lubricated Hi-

eX bearings is dependent upon the sliding

Thrust Washers $U = \frac{\frac{D_o + D_i}{2} \cdot \pi}{60 \cdot 10^3} \cdot \frac{4\varphi \cdot N_{osz}}{360}$

speed as shown in Fig. 11. For sliding speeds in excess of 2.5 m/s continuous oil lubrication is recommended.

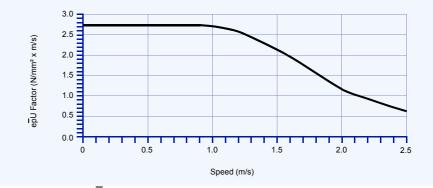


Fig. 11: Maximum epU factor for grease lubrication

5.3 pU Factor

The useful operating life of a Hi-eX bearing is governed by the pU factor, which is calculated as follows:

(5.3.1)1) $[N/mm^2 \times m/s]$ $\bar{p}U = \bar{p} \cdot U$

calculation of the bearing service life by

the speed/load application factor $a_{\mbox{\scriptsize Q}}$ shown

in Figs. 15-17.

5.4 Load

In addition to its contribution to the \overline{pU} factor the type and direction of the applied load also affects the performance of a Hiex bearing. This is accomoda- ted in the

Type of Load




Fig. 12: Steady load, vertically downwards, bush stationary, shaft rotating. Lubricant drains to loaded area




Fig. 14: Rotating load, shaft stationary, bush rotating




Fig. 13: Steady load, vertically upwards, bush stationary, shaft rotating. Lubricant drains away from loaded area

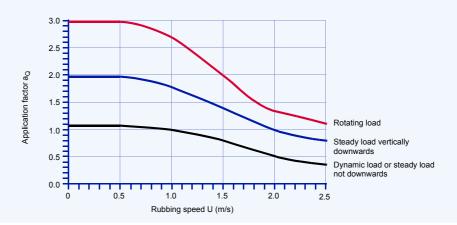


Fig. 15: Application factor a_Q for MB range bushes - unmachined

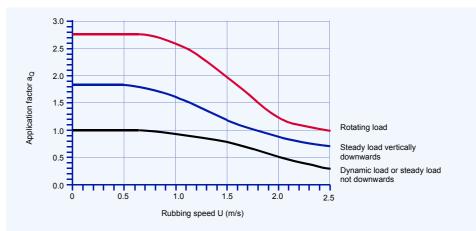


Fig. 16: Application factor $a_{\mbox{\scriptsize Q}}$ for PM range and MB range bushes - machined

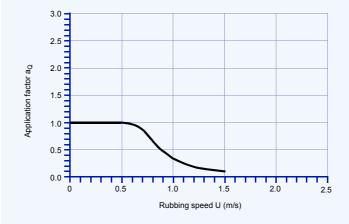


Fig. 17: Application factor a_Q for thrust washers Note: $a_Q = 1$ for slideways

5.5 Temperature

The useful life of a Hi-eX bearing depends upon the operating temperature. The performance of grease lubricated Hi-eX decreases at bearing temperatures above 40 °C. This loss of performance is related to both material and lubricant effects.

For a given $\overline{p}U$ Factor the operating tempe-rature of the bearing depends upon

the temperature of the surrounding environment and the heat dissipation properties of the housing.

In calculating the service life of Hi-eX these effects are accomodated by the application factor a_T shown in Fig. 18

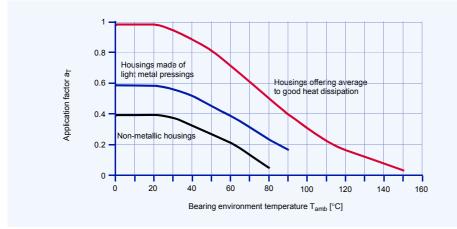


Fig. 18: Hi-eX application factor a_T

5.6 Mating Surface

The wear rate of Hi-eX is strongly dependent upon the roughness of the mating counterface. For optimum bearing performance the mating surface should be ground to better than 0.4 μm $R_a.$ This effect is accomodated by the mating surface finish application factor a_S shown in Fig. 19.

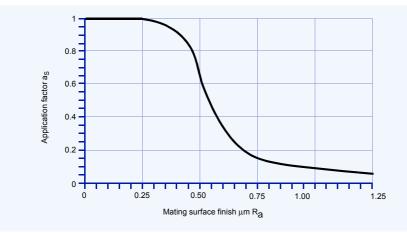


Fig. 19: Hi-eX application factor a_S

5.7 Bearing Size

Frictional heat generated at the bearing surface and dissipated through the shaft and housing depends both on the operating conditions (i.e. \overline{pU} factor) and the bearing size.

For a give \overline{pU} condition a large bearing will run hotter than a smaller bearing. The bearing size factor a_B shown in Fig. 20 takes account of this effect.

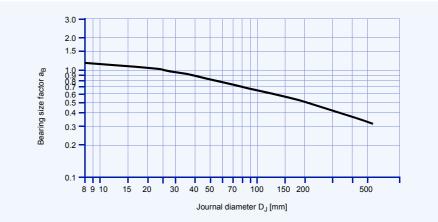


Fig. 20: Bearing size factor a_B

Note: a_B = 1 for slideways

5.8 Estimation of Bearing Service Life with Grease Lubrication

Calculation Parameters

Bushes		Thrust Washers	_	Slide Plates		Unit
Bearing diameter	D _i	Bearing outside dia- meter	Do	Bearing Length	L	[mm]
Bearing length	В	Bearing inside diameter	Di	Bearing Width	W	[mm]

Operating Conditions

Load	F	[N]
Rotational Speed (Continuous)	Ν	[1/min]
Oscillating Frequency	N _{osz}	[1/min]
Angular movement about mean position	φ	[°]
Specific Load Limit	see Table 5, Page 13	[N/mm²d]
Application Factor a _Q	see Fig. 15-17, Page 16	[-]
Application Factor a _T	see Fig. 18, Page 17	[-]
Application Factor a _S	see Fig. 19, Page 17	[-]
Bearing Size Factor a _B	see Fig. 20, Page 18	[-]

Calculate p from the equations in 5.1 on Page 13.

Calculate U from the equations in 5.2 on Page 14.

Calculate pU from the equation in 5.3 on Page 15.

[-]

[-]

[h]

Calculate High Load Factor a_E

Note:

 $a_E = rac{\overline{p}_{lim}}{\overline{p}_{lim} - \overline{p}}$

If a_E > 10000, or a_E < 0, the bearing is overloaded.

Calculate Effective pU Factor epU

Note:

 $e\overline{p}U = rac{a_E \cdot \overline{p}U}{a_B}$

Check that $e\overline{p}U$ is less than limit set in Fig. 11 for the sliding speed U. If NOT, increase the bearing length or use continuous lubrication.

Estimate Bearing Life

If $e\overline{p}U < 1.0$ then (5.8.3) [h] $L_H = \frac{3000}{e\overline{p}U} \cdot a_Q \cdot a_T \cdot a_S$

If
$$e\overline{p}U > 1.0$$
 then
(5.8.4) [h]
 $L_H = \frac{3000}{e\overline{p}U^{2_*4}} \cdot a_Q \cdot a_T \cdot a_S$

Estimate Re-greasing Interval

(5.8.5)

(5.8.6)

(5.8.1)

(5.8.2)

 $L_{RG} = \frac{L_H}{2}$

Oscillating Motion and Dynamic Loads

Oscillating Motion

Dynamic Loads

Calculate number of cycles

$$Z_T = L_{RG} \cdot N_{osz} \cdot 60 \cdot (R+2)$$

Calculate number of cycles
(5.8.7) [-]
$$C_T = L_{RG} \cdot C \cdot 60 \cdot (R+2)$$

where R = Number of times bearing is regreased during total life required.

Check that Z_T (or C_T) is less than the total number of cycles Q given in Fig. 9 for actual bearing specific load p.

If Z_T (or C_T) > Q then life will be limited by fatigue after Q cycles.

If Z_T (or C_T) < Q then life will be limited by wear after Z_T cycles.

If the estimated life or total cycles are insufficient or the regreasing intervals are too frequent, increase the bearing length or diameter, or consider drip feed or continuous oil lubrication, the quantity to be established by test.

C GLACIER GARLOCK BEARINGS

5.9 Worked Examples

PM cylindrical Bush

PM cylindrical Bush

Given:				Given:			
Steady Load	Inside Diameter D _i	40 mm	Load Details	Steady Load	Inside Diameter D _i	100 mm	
Direction: down	Length B	30 mm		Direction: up	Length B	60 mm	
Steel, R _a = 0.4 µm	Bearing Load F	20000 N	Shaft	Steel, R _a = 0.3 µm	Bearing Load F	45000 N	
Temperature 85 °C	Rotational Speed N	30 1/min		Temperature 80 °C	Rotational Speed N	35 1/min	
Light metal - poor heat dissipation				good heat dissipation			
	Direction: down Steel, $R_a = 0.4 \mu m$ Temperature 85 °C	Direction: down Length B Steel, R _a = 0.4 μm Bearing Load F Temperature 85 °C Rotational Speed N	Direction: down Length B 30 mm Steel, R _a = 0.4 μm Bearing Load F 20000 N Temperature 85 °C Rotational Speed N 30 1/min	Steady Load Inside Diameter D _i 40 mm Load Details Direction: down Length B 30 mm Steel, R _a = 0.4 μm Bearing Load F 20000 N Shaft Temperature 85 °C Rotational Speed N 30 1/min Shaft Stead Stead	Steady Load Inside Diameter Di 40 mm Load Details Steady Load Direction: down Length B 30 mm Direction: up Steel, Ra = 0.4 μm Bearing Load F 20000 N Shaft Steel, Ra = 0.3 μm Temperature 85 °C Rotational Speed N 30 1/min Temperature 80 °C	Steady Load Inside Diameter Di 40 mm Load Details Steady Load Inside Diameter Di Direction: down Length B 30 mm Direction: up Length B Steel, R _a = 0.4 µm Bearing Load F 20000 N Shaft Steel, R _a = 0.3 µm Bearing Load F Temperature 85 °C Rotational Speed N 30 1/min Temperature 80 °C Rotational Speed N	

Calculation Constants and Application Fa	ctors		Calculation Constants and Application Fac	ctors	
Specific Load Limit plim at 85 °C	81.5 N/mm ²	(Table 5, Page 13)	Specific Load Limit plim at 40 °C	90 N/mm ²	(Table 5, Page 13)
Application Factor a _T	0.2	(Fig. 18, Page 17)	Application Factor a _T	0.50	(Fig. 18, Page 17)
Mating Surface Application Factor a _S	0.85	(Fig. 19, Page 17)	Mating Surface Application Factor a _S	1.00	(Fig. 19, Page 17)
Bearing Size Factor a _B for ø 40	0.95	(Fig. 20, Page 18)	Bearing Size Factor a _B for ø 100	0.65	(Fig. 20, Page 18)
Application Factor for PM bush a _Q	1.8	(Fig. 16, Page 16)	Application Factor for PM bush a _Q	1.0	(Fig. 16, Page 16)

Calculation	Ref	Value	Calculation	Ref	Value
p [N/mm²]	(5.1.1), Page 13	$D_i \cdot B = 40 \cdot 30$			$\bar{p} = \frac{r}{D_i \cdot B} = \frac{45000}{100 \cdot 60} = 7,50$
Sliding Speed U [m/s]	(5.2.1), Page 14	$U = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} = \frac{40 \cdot \pi \cdot 30}{60000} = 0.063$	Sliding Speed U [m/s]	(5.2.1), Page 14	$U = \frac{D_{i} \cdot \pi \cdot N}{60 \cdot 10^{3}} = \frac{100 \cdot \pi \cdot 35}{60000} = 0.183$
	Page 19	$a_E = \frac{p_{lim}}{\bar{p}_{lim} - \bar{p}} = \frac{81.5}{81.5 - 16.67} = 1.25$	High Load Easter	(5 0 1)	
		$e\bar{p}U = \frac{a_E \cdot \bar{p}U}{a_B} = \frac{1.25 \cdot 16.67 \cdot 0.063}{0.95} = 1.382$	6		$e\bar{p}U = \frac{a_E \cdot p_B}{a_B} = \frac{1.091 \cdot 7.5 \cdot 0.185}{0.65} = 2.307$
Life L _H [h] for epU>1	(5.8.3), Page 19	$L_{H} = \frac{3000}{e\bar{\rho}U^{2,4}} \cdot a_{Q} \cdot a_{T} \cdot a_{S} = \frac{3000}{1.382^{2,4}} \cdot 1.8 \cdot 0.2 \cdot 0.85 = 434$	Life L _H [h] for epU>1	(5.8.3), Page 19	$L_{H} = \frac{3000}{e\bar{p}U^{2.4}} \cdot a_{0} \cdot a_{7} \cdot a_{8} = \frac{3000}{2.307^{2.4}} \cdot 1.0 \cdot 1.0 \cdot 0.5 = 202$
L _{RG} [h]	(5.8.3), Page 19	$L_{RG} = \frac{L_{H}}{2} = \frac{434}{2} = 217$	L _{RG} [h]	(5.8.3), Page 19	$L_{RG} = \frac{L_{H}}{2} = \frac{202}{2} = 101$

MB cylindrical bush

Given:							
Load Details	Steady Load, oscillating	Inside Diameter D _i	80 mm				
	Direction: down	Length B	40 mm				
Shaft	Steel, R _a = 0.3 µm	Bearing Load F	200000 N				
	ambient Temperature	Frequency Nosz	5 1/min				
Housing	Light metal - poor heat dissipation	Angle φ	20°				

Calculation Constants and Application Factors					
Specific Load Limit p _{lim} 140 N/mm ² (Table 5, Page 13)					
Application Factor a _T	0.60	(Fig. 18, Page 17)			
Mating Surface Application Factor aS	1.00	(Fig. 19, Page 17)			
Bearing Size Factor a _B for ø 80	0.75	(Fig. 20, Page 18)			
Application Factor for MB bush a _O	1.80	(Fig. 16, Page 16)			

Thrust washer

Given:			
Load Details	Steady Load	Inside Diameter D _i	40 mm
	Direction: down	Outside Diameter Do	78 mm
Counterface	Steel, R _a = 0.2 µm	Bearing Load F	50000 N
	Temperature 50 °C	25 1/min	
Housing	Light metal - poor heat d		

Calculation Constants and Application Factors					
Specific Load Limit plim	90 N/mm ²	(Table 5, Page 13)			
Application Factor a _T for 50 °C	0.50	(Fig. 18, Page 17)			
Mating Surface Application Factor a _S	1.00	(Fig. 19, Page 17)			
Bearing Size Factor a _B for ø 40	0.95	(Fig. 20, Page 18)			
Application Factor for Thrust washers aQ	1.00	(Fig. 17, Page 16)			

Calculation	Ref	Value
<u>Specific Load</u> p [N/mm²]	(5.1.1), Page 13	$\bar{p} = \frac{F}{D_i \cdot B} = \frac{200000}{80 \cdot 40} = 62,,5$
Sliding Speed U [m/s]	(5.2.3), Page 14	$U = \frac{D_i \cdot \pi}{60 \cdot 10^3} \cdot \frac{4 \phi \cdot N_{osz}}{360} = \frac{80 \cdot \pi}{60000} \cdot \frac{4 \cdot 20 \cdot 1.11}{360} = 0.001$
High Load Factor a _E [-] (must be >0)	(5.8.1), Page 19	$a_E = \frac{\overline{p}_{lim}}{\overline{p}_{lim} - \overline{p}} = \frac{140}{140 - 10.11} = 1.806$
epU Factor [-]	(5.8.2), Page 19	$e\bar{p}U = \frac{a_E \cdot \bar{p}U}{a_B} = \frac{1.806 \cdot 62.5 \cdot 0.001}{0.75} = 0.151$
Life L _H [h] for epU<1	(5.8.3), Page 19	$L_{H} = \frac{3000}{e\bar{p}U} \cdot a_{Q} \cdot a_{T} \cdot a_{S} = \frac{3000}{0.151} \cdot 1.8 \cdot 0.6 \cdot 1.0 = 21456$
L _{RG} [h]	(5.8.3), Page 19	$L_{RG} = \frac{L_H}{2} = \frac{21456}{2} = 10728$
Z _T [-]	(5.8.3), Page 19	$Z_{T} = L_{RG} \cdot N_{osz} \cdot 60 \cdot (R+2) = 10728 \cdot 5 \cdot 60 \cdot 2 = 6.44 \cdot 10^{6}$
		Q for $\overline{p} = 62.5 = 1.5 \times 10^6$; Z _T > Q Therefore bearing fails by fatigue after 1.5 x 10 ⁶ cycles

	Calculation	Ref	Value
-	<u>Specific Load</u> p [N/mm ²]	(5.1.1), Page 13	= 4 · F 4 · 50000 44 00
	Sliding Speed U [m/s]	(5.2.2), Page 14	$U = \frac{\frac{D_o + D_i}{2} \cdot \pi \cdot N}{\frac{60 \cdot 10^3}{60 \cdot 10^3}} = \frac{\frac{78 + 40}{2} \cdot \pi \cdot 25}{\frac{60 \cdot 10^3}{60 \cdot 10^3}} = 0.0772$
	High Load Factor a _E [-] (must be >0)	(5.8.1), Page 19	$a_E = \frac{\overline{p}_{lim}}{\overline{p}_{lim} - \overline{p}} = \frac{90}{90 - 14.20} = 1.187$
-	epU Factor [-]		$e\bar{p}U = \frac{a_E \cdot \bar{p}U}{a_B} = \frac{1.187 \cdot 14.20 \cdot 0.0772}{0.95} = 1.370$
-	Life L _H [h] for epU>1	(5.8.3), Page 19	$L_{H} = \frac{3000}{e\bar{\rho}U^{2.4}} \cdot a_{Q} \cdot a_{T} \cdot a_{S} = \frac{3000}{1.370^{2.4}} \cdot 1.0 \cdot 0.5 \cdot 1.0 = 704$
	L _{RG} [h]	(5.8.3), Page 19	$L_{RG} = \frac{L_H}{2} = \frac{704}{2} = 352$

Design Factors 5

6 Data Sheet

Application:

6.1 Data for bearing design calculations

B			 	
Cylindrical Bush	Thrust Washer	Slideplate	Special (Ske	etch)
Rotational movement	Steady load	Rotating load	Oscillating n	novement Linear movement
 Existing Design Quantity Dimensions in mm Inside Diameter Outside Diameter Length Length of slideplate Width of slideplate Thickness of slideplate Thickness of slideplate Adial load or specific load Axial load or specific load Movement Rotational speed Speed Length of Stroke Frequency of Stroke Oscillating cycle Oscillating frequency Service hours per day Continuous operation Intermittent operation Operating time Days per year 	New Design Di Do B L W SS F [N] p [N/mm²] F [N] p [N/mm²] N [1/min] U [m/s] Ls [mm] [1/min] φ [°] Nosz [1/min]	Shaft Bearing I Operatin Ambient Housing perties Light pre which po Non meta transfer p Alternate Mating s Material Hardness Surface f Dry Continuo Process Initial lub Hydrodyn	ag Environment temperature with good heat transf ssing or insulated hor or heat transfer prope al housing with poor h properties operation in water an surface s finish ion us lubrication fluid lubrication rication only namic conditions Fluid t viscosity	using erties
Customer Data Company: Street:	City: Post Code:	Project: Name: Tel.:		Date: Signature: Fax:

7 Bearing Assembly

7.1 Dimensions and Tolerances

For optimum performance it is essential that the correct running clearance is used and that both the diameter of the shaft and the bore of the housing are finished to the limits given in the tables.

If the bearing housing is unusually flexible

amount and the running clearance will be more than the optimum. In these circumstances the housing should be bored slightly undersize or the journal diameter increased, the correct size being determined by experiment.

the bush will not close in by the calculated

7.2 Tolerances for minimum clearance

Grease lubrication

The minimum clearance required for satisfactory performance of Hi-eX depends upon the pU factor, the sliding speed and the environmental temperature, any one or combination of which may reduce the diametral clearance in operation due to inward thermal expansion of the Hi-eX polymer lining. It is therefore necessary to compensate for this.

Fig. 21 shows the minimum diametral clearance plotted stepped against journal diameter at an ambient 20 °C. Where the stepped lines show a change of clearance for a given journal diameter, the lower value is used.

The superimposed straight lines indicate the minimum permissible diametral clear-

ance for various values of $\overline{p}Uu$ (Fig. 21), where $\overline{p}U$ is calculated as in 5.3 on Page 15, and u is a sliding speed factor for speeds in excess of 0.5 m/s given in Fig. 22.

If the clearance indicated for a pUu factor lies below the stepped lines the recommended standard shaft may be used. If above, the shaft size must be reduced to obtain the clearance indicated on the vertical axis of the relevant figure.

Under slow speed and high load conditions it may be possible to achieve satisfactory performance with diametral clearances less than those indicated. But adequate prototype testing is recommended in such cases.

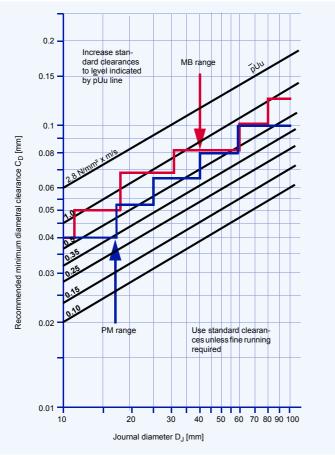


Fig. 21: Minimum clearance for PM prefinished and MB machinable range machined to H7 bore

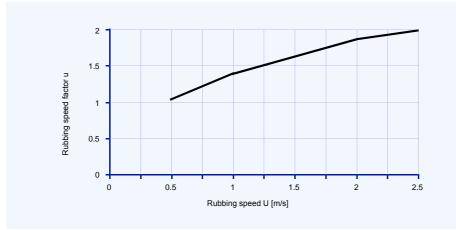


Fig. 22: Rubbing speed factor u

🔵 GLACIER GARLOCK BEARINGS

Fluid Lubrication

The minimum clearance required for journal bearings operating under hydrodynamic or mixed film conditions for a range of shaft rotational speeds and diameters is shown in Fig. 23 It is recommended that the bearing performance under minimum clearance conditions be confirmed by testing if possible.

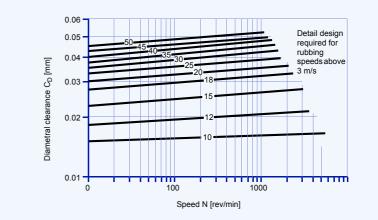


Fig. 23: Hi-eX minimum clearances - bush diameters D_i 10-50 mm

Allowance for Thermal Expansion

For operation in high temperature environments the clearance should be increased by the amounts indicated by Fig. 24 to compensate for the inward thermal expansion of the bearing lining.

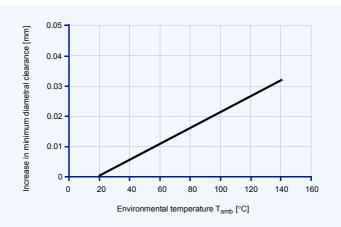


Fig. 24: Recommended increase in diametral clearance

If the housing is non-ferrous then the bore should be reduced by the amounts given in Table 5, in order to give an increased interference fit to the bush, with a similar reduction in the journal diameter additional to that indicated by Fig. 24.

Housing material	Reduction in housing diameter per 100°C rise	Reduction in shaft diameter per 100°C rise		
Aluminium alloys	0.1%	0.1% + values from Fig. 24		
Copper base alloys	0.05%	0.05% + values from Fig. 24		
Steel and cast iron	Nil	values from Fig. 24		
Zinc base alloys	0.15%	0.15% + values from Fig. 24		

Table 6: Allowance for high temperature

7.3 Counterface Design

Hi-eX bearings may be used with all conventional mating surface materials. Hardening of steel journals is not required unless abrasive dirt is present or if the projected bearing life is in excess of 2000 hours, in which cases a minimum shaft hardness of 350HB is recommended.

A ground surface finish of better than

0.4 μm R_a is recommended. The final direction of machining of the mating surface should preferably be the same as the direction of motion relative to the bearing in service.

Hi-eX is normally used in conjunction with ferrous journals and thrust faces, but in damp or corrosive surroundings stainless steel, hard chromium plated mild steel, or alternatively WH shaft sleeves are recommended. When plated mating surfaces are specified the plating should possess adequate strength and adhesion, particularly if the bearing is to operate with high fluctuating loads.

The shaft or thrust collar used in conjunction with the Hi-eX bush or thrust washer must extend beyond the bearing surface in order to avoid cutting into it. The mating surface must also be free from grooves or flats, the end of the shaft should be given a lead-in chamfer and all sharp edges or projections which may damage the soft polymer lining of the HieX must be removed.

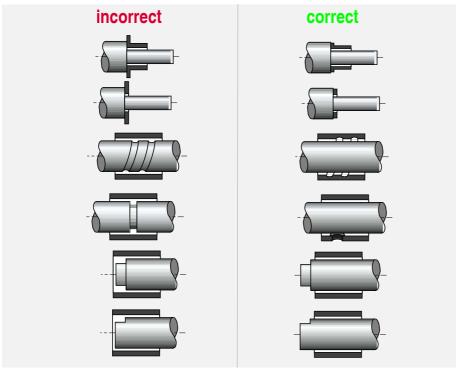


Fig. 25: Counterface design

7.4 Installation

Important Note

Care must be taken to ensure that the HieX lining material is not damaged during the installation.

Fitting of Bushes

The bush is inserted into its housing with the aid of a stepped mandrel, preferably made from case hardened mild steel, as shown in Fig. 26. The following should be noted to avoid damage to the bearing:

- · Housing diameter is as recommended
- 15-20 deg lead-in chamfer on housing
- The bush must be square to the housing
- Light smear of oil on bush OD

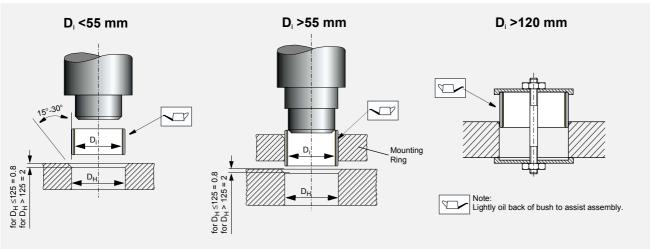


Fig. 26: Fitting of bushes

Insertion Forces

Fig. 27 gives an indication of the maximum insertion force required to correctly install

standard Hi-eX bushes.

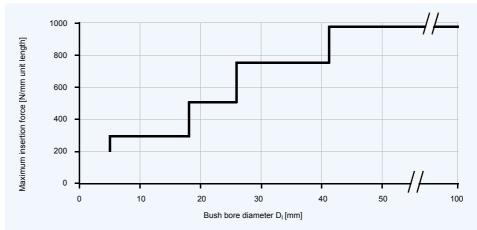


Fig. 27: Maximum insertion force F_i

Alignment

Accurate alignment is an important consideration for all bearing assemblies. With Hi-eX bearings misalignment over the length of a bush (or pair of bushes), or over the diameter of a thrust washer should not exceed 0.020 mm as illustrated in Fig. 28.

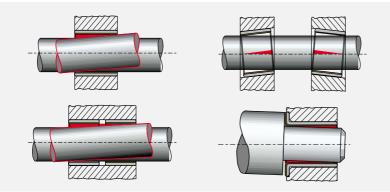


Fig. 28: Alignment

Sealing

While Hi-eX can tolerate the ingress of some contaminant materials into the bearing without loss of performance, where there is the possibility of highly

abrasive material entering the bearing, a suitable sealing arrangement, as illustrated in Fig. 29 should be provided.

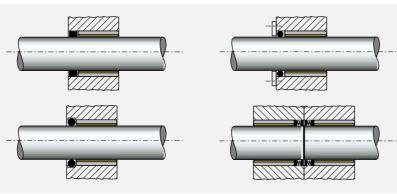


Fig. 29: Recommended sealing arrangements

Axial Location

Where axial location is necessary, it is generally advisable to fit Hi-eX thrust washers in conjunction with Hi-eX bushes, even when the axial loads are low. Experi-

Fitting of Thrust Washers

Hi-eX thrust washers should be located on the outside diameter in a recess as shown in Fig. 30. The inside diameter must be clear of the shaft in order to prevent contact with the steel backing of the Hi-eX material. The recess diameter should be 0.125 mm larger than the washer diameter and the depth as given in the product tables. ence has shown that fretting debris from unsatisfactory locating surfaces can enter an adjacent Hi-eX bush and adversely affect the bearing life and performance.

If there is no recess for the thrust washer one of the following methods of fixing may be used:

- · two dowel pins
- two screws
- adhesive

GLACIER GARLOCK BEARINGS




Fig. 30: Installation of Thrust-Washer

Hi-eX strip material for use as slideway


bearings should be installed using one of

Slideways

the following methods:

Important Note

- Dowel pins should be recessed 0.25 mm below the bearing surface
- Screws should be countersunk 0.25 mm below the bearing surface
- + Hi-eX must not be heated above 250 $^\circ\mathrm{C}$
- Contact adhesive manufacturers for guidance on the selection of suitable adhesives
- Protect the bearing surface to prevent contact with adhesive
- Ensure the washer ID does not touch the shaft after assembly
- Ensure that the washer is mounted with the steel backing to the housing
- countersunk screws
 - · adhesives
 - · mechanical location





8 Machining

8.1 Machining Practice

The PEEK polymer lining of Hi-eX has good machining characteristics and can be treated as a free cutting brass in most respects. The indents in the bearing surface may lead to the formation of burrs or whiskers due to the resilience of the lining material, but this can be avoided by using machining methods which remove the lining as a ribbon, rather than a narrow thread. When machining Hi-eX it is recommended that not more than 0.125 mm is removedfrom the lining thickness in order to ensure that the lubricant capacity of the indents remaining after machining is not significantly reduced.

Boring, reaming and broaching are all suitable machining methods for use with HieX. The recommended tool material is high speed steel or tungsten carbide, respectively diamonds for long toolservice times.

8.2 Boring

Fig. 32 illustrates a recommended boring tool which should be mounted with its axis at right angles to the direction of feed.

The essential characteristic required in the boring tool is a tip radius greater than

1.5 mm, which combined with a side rake of 30° will produce the ribbon effect required.

Cutting speeds should be high, the optimum between 2.0 and 4.5 m/s. The feed should be low, in the range 0.05/0.025 mm for cuts of 0.125 mm, the lower feeds being used with the higher cutting speeds.

Satisfactory finishes can usually be obtained machining dry and an air blast may facilitate swarfe removal. The use of coolant is not detrimental.

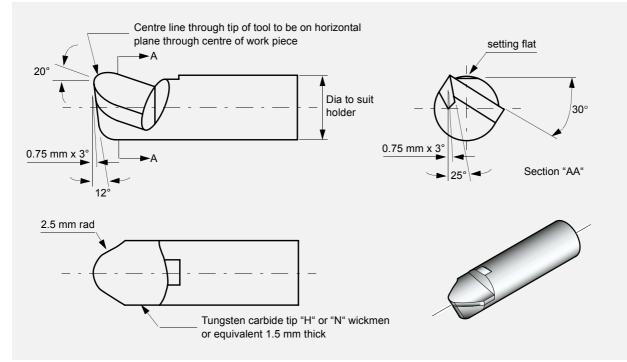



Fig. 32: Boring tool for Hi-eX

8.3 Reaming

Hi-eX can be reamed satisfactorily by hand with a straight-fluted expanding reamer. For best results the reamer should be sharp, the cut 0.025-0.050 mm and the feed slow. Where hand reaming is not desired machining speeds of about 0.05 m/s are recommended with the cuts and feeds as for boring.

8.4 Broaching

Fig. 33 shows broaches suitable for finishing bushes up to 65 mm diameter. The broach should be used dry, at a speed of 0.1-0.5 m/s.

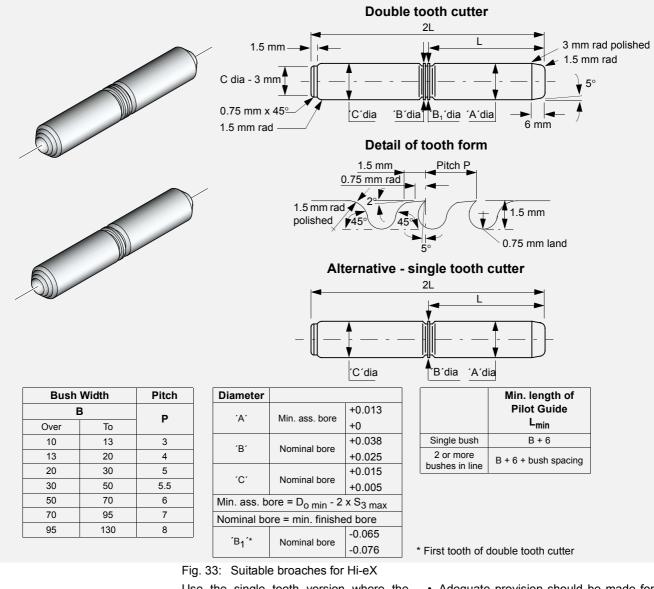

Use the single tooth version where the bush is less than 25 mm long, and the double tooth broach for longer bushes or

for two or more bushes together. If it is necessary to make up a special form of broach the following points should be noted: Adequate provision should be made for locating the bush by providing a pilot to suit the bore of the bush when pressed home. A rear support shoulder should locate in the broached bore of the bush after cutting. Alternatively, special guides may be provided external to the workpiece.

- If two bushes are to be broached in line, then the pilot guide and rear support should be longer than the distance between the two bushes.
- For large bushes it may be necessary to provide axial relief along the length of the pilot guide and rear support, in order to reduce the broaching forces.

8.5 Vibrobroaching

This technique may also be used. A single cutter is propelled with progressive reciprocating motion with a vibration frequency of typically 50 Hz. The cutter should have a primary rake of 1.5° for 0.5 mm. A cut of

0.25 mm on diameter may be made at an average cutting speed of 0.15 m/s to give a surface finish of better than 0.8 μ m R_a, which is acceptable.

the minimum cutting pressure should be

used and care taken to ensure that any

steel or bronze particles protruding into the

remaining bearing material, and all burrs,

· Unless a guided broach is used, the tool

will follow the initial bore alignment of the

bush, broaching cannot improve concen-

tricity and parallelism unless external

In general owing to the variation in wall

thickness of large diameter bushes, broa-

ching is not suitable for finishing bores of more than 60 mm diameter unless external

guides are used.

guides are used.

8.6 Modification of components

The modification of Hi-eX bearing components requires no special procedures. In general it is more satisfactory to perform machining or drilling operations from the polymer lining side in order to avoid burrs. When cutting is done from the steel side,

8.7 Drilling Oil Holes

Bushes should be adequately supported during the drilling operation to ensure that

8.8 Cutting Strip Material

Hi-eX strip material may be cut to size by any one of the following methods. Care must be taken to protect the bearing surface from damage and to ensure that no deformation of the strip occurs. no distortion is caused by the drilling pres-

- Using side and face cutter, or slitting saw, with the strip held flat and securely on a horizontal milling machine.
- Cropping

sure.

are removed.

- Guillotine (For widths less than 90 mm only)
- · Water-jet cutting, Laser cutting

9 Electroplating

Hi-eX Components

To provide corrosion protection the mild steel backing of Hi-eX may be electroplated with most of the conventional electroplating metals including the following:

- zinc ISO 2081-2
- nickel ISO 1456-8
- hard chromium ISO 1456-8

For the harder materials if the specified plating thickness exceeds approximately

Mating Surfaces

Hi-eX can be used against hard chrome plated materials and care should be taken to ensure that the recommended shaft

Note:

The parts shown in the following tables are not available from stock.


 $5\,\mu m$ then the housing diameter should be increased by twice the plating thickness in order to maintain the correct assembled bearing bore size.

Where electrolytic attack is possible tests should be conducted to ensure that all the materials in the bearing environment are mutually compatible.

sizes and surface finish are achieved after the plating process.

10 Standard Products

10.1 PM-HX cylindrical bushes

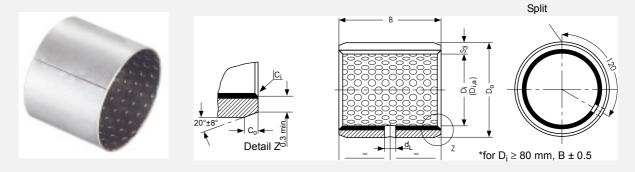

Dimensions and Tolerances according to ISO 3547 and GSP-Specifications

Part No.		ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J h8	Housing-ø D _H H7	Bush i-ø D _{1a} when ass. in H7 housing	Clearance C _D	Oil hole-ø d _L
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
PM 0808 HX			8.00 7.50		8.000 7.978	10.015 10.000		0.127 0.040	No hole
PM 0810 HX	8	10	10.00 9.50				8.107 8.040		
PM 0812 HX			12.00 11.50						
PM 1010 HX			10.25 9.75		10.000 9.978	12.018 12.000	10.110 10.040	0.135 0.040	3
PM 1012 HX	10	12	12.25 11.75						5
PM 1015 HX	10	12	15.25 14.75						4
PM 1020 HX			20.25 19.75						-
PM 1210 HX			10.25 9.75		12.000 11.973	14.018 14.000	12.110 12.040		3
PM 1212 HX			12.25 11.75						5
PM 1215 HX	12	14	15.25 14.75	0.980 0.955					
PM 1220 HX			20.25 19.75						
PM 1225 HX			25.25 24.75						
PM 1415 HX			15.25 14.75		14.000 13.973	16.018 16.000	14.110 14.040		
PM 1420 HX	14	16	20.25 19.75						4
PM 1425 HX			25.25 24.75						-
PM 1510 HX			10.25 9.75						
PM 1512 HX	15	17	12.25 11.75		15.000	17.018	15.108		
PM 1515 HX			15.25 14.75	14.973	17.000	15.040			
PM 1525 HX				25.25 24.75					

ID and OD chamfers

S ₃	Co	Ci	S ₃	Co	Ci				
0.75	max. 0.3*	max. 0.3*	2	1.2 ± 0.4	0.4 ± 0.3				
1	0.6 ± 0.4	max. 0.4*	2.5	1.8 ± 0.6	0.6 ± 0.4				
1.5	0.6 ± 0.4	$0.4\pm0.3^{\star}$	* alternatively rounded						

All dimensions in mm

GLACIER GARLOCK BEARINGS

10 Standard Products

Part No.		ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J h8	Housing-ø D _H H7	Bush i-ø D _{1a} when ass. in H7 housing	Clearance C _D	Oil hole-ø d _L
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
PM 1615 HX			15.25 14.75		16.000 15.973			0.135 0.040	
PM 1620 HX	16	18	20.25 19.75	0.980		18.018 18.000	16.110 16.040		
PM 1625 HX			25.25 24.75						
PM 1815 HX			15.25 14.75	0.955	18.000 17.973				
PM 1820 HX	18	20	20.25 19.75			20.021 20.000	18.111 18.040		
PM 1825 HX			25.25 24.75						4
PM 2010 HX			10.25 9.75						
PM 2015 HX			15.25 14.75		20.000 19.967			0.164 0.050	
PM 2020 HX	20	23	20.25 19.75			23.021 23.000	20.131 20.050		
PM 2025 HX			25.25 24.75						
PM 2030 HX			30.25 29.75						
PM 2215 HX			15.25 14.75	1.475	22.000 21.967	25.021 25.000	22.131 22.050		
PM 2220 HX	22	25	20.25 19.75						
PM 2225 HX			25.25 24.75						
PM 2230 HX			30.25 29.75						
PM 2415 HX			14.75	20.25 19.75 25.25 24.75	24.000 23.967	27.021 27.000	24.131 24.050		
PM 2420 HX	24	27	19.75						
PM 2425 HX			24.75						
PM 2430 HX			30.25 29.75						
PM 2515 HX			15.25 14.75						
PM 2520 HX	25	28	20.25 19.75		25.000 24.967	28.021 28.000	25.131 25.050		6
PM 2525 HX			25.25 24.75 30.25						
PM 2530 HX			29.75 30.25						
PM 2830 HX		31	29.75 20.25			31.025 31.000	28.131 28.050		
PM 2820 HX	28		20.25 19.75 25.25		28.000 27.967	32.025	28 155		
PM 2825 HX		32	23.25 24.75 30.25	1.970 1.935	27.907	32.025	28.155 28.060 30.155 30.060		
PM 2830 HX			29.75 20.25					0.188 0.060	
PM 3020 HX			20.25 19.75 30.25	1.000	30.000	34.025		0.000	
PM 3030 HX	30	34	29.75 40.25		29.967	34.025			
PM 3040 HX			40.25 39.75						

All dimensions in mm

Standard 10 Products

Part No.		ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J h8	Housing-ø D _H H7	Bush i-ø D _{1a} when ass. in H7 housing	Clearance C _D	Oil hole-ø d _L
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
PM 3220 HX			20.25 19.75		32.000 31.961 35.000				
PM 3230 HX		20	30.25 29.75			36.025 36.000	32.155		
PM 3235 HX	32	36	35.25 34.75				32.060		
PM 3240 HX			40.25 39.75						
PM 3520 HX			20.25 19.75			39.025			6
PM 3530 HX	35	39	30.25 29.75				35.155		0
PM 3535 HX	55	55	35.25 34.75	1.970	34.961	39.000	35.060	0.194	
PM 3550 HX			50.25 49.75	1.935				0.060	
PM 3635 HX	36	40	35.25 34.75		36.000 35.961	40.025 40.000	36.155 36.060		
PM 3720 HX	37	41	20.25 19.75		37.000 36.961	41.025 41.000	37.155 37.060		
PM 4020 HX			20.25 19.75		40.000 39.961	44.025 44.000	40.155 40.060		
PM 4030 HX	40	44	30.25 29.75						
PM 4040 HX			40.25 39.75						
PM 4050 HX			50.25 49.75						
PM 4520 HX			20.25 19.75		45.000 44.961	50.025 50.000	45.195 45.080	0.234 0.080	
PM 4530 HX			30.25 29.75						
PM 4540 HX	45	50	40.25 39.75						
PM 4545 HX			45.25 44.75						
PM 4550 HX			50.25 49.75						
PM 5040 HX			40.25 39.75		50.000 49.961	55.030 55.000	50.200 50.080	0.239 0.080	
PM 5050 HX	50	55	50.25 49.75						8
PM 5060 HX			60.25 59.75						
PM 5520 HX			20.25 19.75	2.460					
PM 5525 HX			25.25 24.75	2.415			55.200		
PM 5530 HX	55	60	30.25 29.75		55.000 54.954	60.030 60.000			
PM 5540 HX			40.25 39.75		04.904	00.000	55.080		
PM 5550 HX			50.25 49.75					0.246 0.080	
PM 5560 HX			60.25 59.75					0.060	
PM 6030 HX			30.25 29.75			65.030	60.200		
PM 6040 HX	60	65	40.25 39.75		60.000				
PM 6060 HX			60.25 59.75		59.954	65.000	60.080		
PM 6070 HX			70.25 69.75					All dimen	sions in mm

10 Standard Products

Part No.		ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J h8	Housing-ø D _H H7	Bush i-ø D _{1a} when ass. in H7 housing	Clearance C _D	Oil hole-ø d _L											
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.												
PM 6540 HX			40.25 39.75																	
PM 6550 HX	65	70	50.25 49.75		65.000	70.030	65.262													
PM 6560 HX	00	70	60.25 59.75		64.954	70.000	65.100													
PM 6570 HX			70.25 69.75																	
PM 7040 HX			40.25 39.75						8											
PM 7050 HX			50.25 49.75					0.308												
PM 7065 HX	70	75	65.25 64.75		70.000 69.954	75.030 75.000	70.262 70.100	0.100												
PM 7070 HX			70.25 69.75																	
PM 7080 HX			80.25 79.75																	
PM 7540 HX			40.25 39.75																	
PM 7560 HX	75	80	60.25 59.75		75.000 74.954	80.030 80.000	75.262 75.100													
PM 7580 HX			80.25 79.75																	
PM 8040 HX		85	40.50 39.50																	
PM 8060 HX	80		85	85	85	85	85	85	85	85	85	85	85	85	60.50 59.50	2.450	80.000	85.035	80.267	0.313
PM 8080 HX			80.50 79.50	2.384	79.954	85.000	80.100	0.100												
PM 80100 HX			100.50 99.50																	
PM 8530 HX			30.50 29.50																	
PM 8540 HX			40.50 39.50																	
PM 8560 HX	85	90	60.50 59.50		85.000 84.946	90.035 90.000	85.267 85.100		9.5											
PM 8580 HX			80.50 79.50																	
PM 85100 HX			100.50 99.50																	
PM 9040 HX			40.50 39.50					0.321												
PM 9060 HX			60.50 59.50					0.100												
PM 9080 HX	90 95	80.50 79.50		90.000 89.946	95.035 95.000	90.267 90.100														
PM 9090 HX		90.50 89.50																		
PM 90100 HX			100.50 99.50																	
PM 9560 HX	95	100	60.50 59.50		95.000	100.035	95.267													
PM 95100 HX			100.50 99.50		94.946	100.000	95.100													


Part No.		ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J h8	Housing-ø D _H H7	Bush i-ø D _{1a} when ass. in H7 housing	Clearance C _D	Oil hole-ø d _L
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
PM 10050 HX			50.50 49.50						
PM 10060 HX			60.50 59.50						
PM 10080 HX	100	105	80.50 79.50		100.000 99.946	105.035 105.000	100.267 100.100		
PM 10095 HX			95.50 94.50			100.000	100.100		
PM 100115HX			115.50 114.50						
PM 10560 HX			60.50 59.50						
PM 105110 HX	105	110	59.50 110.50 109.50		105.000 104.946	110.035 110.000	105.267 105.100	0.321 0.100	
PM 105115 HX			115.50 114.50						
PM 11060 HX			60.50 59.50						
PM 110110 HX	110	115	110.50 109.50	2.450 2.384	110.000 109.946	115.035 115.000	110.267 105.100		9.5
PM 110115 HX			115.50 114.50						
PM 11550 HX	115	120	50.50 49.50		115.000	120.035	115.267		
PM 11570 HX	115	120	70.50 69.95		114.946	120.000	115.100		
PM 12060 HX			60.50 59.50						
PM 120100 HX	120	125	100.50 99.50		120.000 119.946	125.040 125.000	120.272 120.100	0.326 0.100	
PM 120110 HX			110.50 109.50						
PM 12560 HX			60.50 59.50 100.50 99.50						
PM 125100 HX	125	130			125.000 124.937	130.040 130.000	125.272 125.100	0.335 0.100	
PM 125110 HX			110.50 109.50						
PM 13050 HX			50.50 49.50						
PM 13060 HX	130	135	60.50 59.50		130.000	135.040	130.280		
PM 13080 HX			80.50 79.50		129.937	135.000	130.130		
PM 130100 HX			100.50 99.50						
PM 13560 HX	135	140	60.50 59.50		135.000	140.040	135.280		
PM 13580 HX			80.50 79.50		134.937	140.000	135.130		
PM 14050 HX			50.50 49.50	2.435				0.343	-
PM 14060 HX	140	145	60.50 59.50	2.380	140.000	145.040	140.280	0.130	
PM 14080 HX		140 145	80.50 79.50		139.937	145.000	140.130		
PM 140100 HX			100.50 99.50						
PM 15050 HX			50.50 49.50						
PM 15060 HX	150 155	155	60.50 59.50		150.000	155.040			
PM 15080 HX		80.50 79.50		155.000	150.130				
PM 150100 HX			100.50 99.50					All dimen	sions in mm

10 Standard Products

Part No.		ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J h8	Housing-ø D _H H7	Bush i-ø D _{1a} when ass. in H7 housing	Clearance C _D	Oil hole-ø d _L	
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.		
PM 16050 HX			50.50 49.50							
PM 16060 HX			60.50 59.50		160.000	165.040	160.280			
PM16080 HX	160	165	80.50 79.50		159.937	165.000	160.130			
PM 160100 HX			100.50 99.50					0.343		
PM 17050 HX			50.50 49.50					0.130		
PM 17060 HX	470	475	60.50 59.50		170.000	175.040	170.280			
PM 17080 HX	170	175	80.50 79.50		169.937	175.000	170.130			
PM 170100 HX			100.50 99.50							
PM 18050 HX			50.50 49.50							
PM 18060 HX	180	185	60.50 59.50		180.000	185.046	180.286	0.349		
PM 18080 HX	100	105	80.50 79.50		179.937	185.000	180.130	0.130		
PM 180100 HX			100.50 99.50							
PM 19050 HX			50.50 49.50							
PM 19060 HX		90 195		60.50 59.50						
PM 19080 HX	190		80.50 79.50		190.000 189.928	195.046 195.000	190.286 190.130			
PM 190100 HX				100.50 99.50	2.435					
PM 190120 HX			120.50 19.50	2.380					-	
PM 20050 HX			50.50 49.50							
PM 20060 HX			60.50 59.50							
PM 20080 HX	200	205	80.50 79.50		200.000 199.928	205.046 205.000	200.286 200.130			
PM 200100 HX			100.50 99.50							
PM 200120 HX			120.50 119.50					0.358		
PM 22050 HX			50.50 49.50					0.130		
PM 22060 HX			60.50 59.50							
PM 22080 HX	220	225	80.50 79.50		220.000 219.928	225.046 225.000	220.286 220.130			
PM 220100 HX			100.50 99.50							
PM 220120 HX			120.50 119.50							
PM 24050 HX			50.50 49.50							
PM 24060 HX	240 245	60.50 59.50								
PM 24080 HX		80.50 79.50		240.000 239.928	245.046 240.286 245.000 240.130					
PM 240100 HX			100.50 99.50	0						
PM 240120 HX			120.50 119.50						sions in mm	

Part No.		ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J h8	Housing-ø D _H H7	Bush i-ø D _{1a} when ass. in H7 housing	Clearance C _D	Oil hole-ø d _L
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
PM 25050 HX			50.50 49.50						
PM 25060 HX			60.50 59.50						
PM 25080 HX	250	255	80.50 79.50		250.000 249.928	255.052 255.000	250.292 250.130	0.364 0.130	
PM 250100 HX		100.50 99.50 120.50 119.50							
PM 250120 HX			119.50						
PM 26050 HX			50.50 49.50						
PM 26060 HX			60.50 59.50	260.000 259.919					
PM 26080 HX	260	265	80.50 79.50 100.50 99.50			265.052 265.000	260.292 260.130		
PM 260100 HX									
PM 260120 HX			120.50 119.50	2.435					_
PM 28050 HX			50.50 49.50	2.380					
PM 28060 HX			60.50 59.50						
PM 28080 HX	280	285	80.50 79.50		280.000 279.919	285.052 285.000	280.292 280.130	0.373 0.130	
PM 280100 HX			100.50 99.50						
PM 280120 HX			120.50 119.50						
PM 30050 HX			50.50 49.50						
PM 30060 HX			60.50 59.50						
PM 30080 HX	300 305	305	80.50 79.50		300.000 299.919	305.052 305.000	300.292 300.130		
PM 300100 HX			100.50 99.50						
PM 300120 HX			120.50 119.50						

10.2MB-HX cylindrical bushes

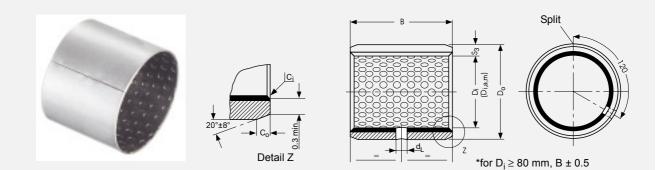

Dimensions and Tolerances according to ISO 3547 and GSP-Specifications

Part No.	-	ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J [h8]	Housing-ø D _H [H7]	Bush i-ø D _{1m} machined to H7	Clearance C _D	Oil hole-ø d _L														
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.															
MB 0808 HX			8.00 7.50																				
MB 0810 HX	8	3 10	10	10.00 9.50		7.960 7.938	10.015 10.000	8.015 8.000		No hole													
MB 0812 HX			12.00 11.50																				
MB 1010 HX			10.25 9.75					0.077 0.040	3														
MB 1012 HX	10	12	12.25 11.75		9.960	12.018	10.015		5														
MB 1015 HX	10	12	15.25 14.75		9.938	12.000	10.000		4														
MB 1020 HX			20.25 19.75						4														
MB 1210 HX								10.25 9.75						3									
MB 1212 HX			12.25 11.75						5														
MB 1215 HX	12	14	14	14	14	14	14	14	14	14	14	14	14	14	14	14	15.25 14.75	1.108 1.082	11.950 11.923	14.018 14.000	12.018 12.000		
MB 1220 HX										20.25 19.75													
MB 1225 HX			25.25 24.75																				
MB 1415 HX			15.25 14.75					0.095															
MB 1420 HX	14	16	20.25 19.75		13.950 13.923	16.018 16.000	14.018 14.000	0.050	4														
MB 1425 HX			25.25 24.75						-														
MB 1510 HX		15 17	10.25 9.75																				
MB 1512 HX	15		12.25 11.75		14.950	17.018	15.018																
MB 1515 HX	15		15.25 14.75		14.923	17.000	15.000																
MB 1525 HX				25.25 24.75																			

ID and OD chamfers

S ₃	C _o	Ci	S ₃	Co	C _i		
0.75	max. 0.3*	max. 0.3*	2	1.2 ± 0.4	0.4 ± 0.3		
1	0.6 ± 0.4	max. 0.4*	2.5	1.8 ± 0.6	0.6 ± 0.4		
1.5	0.6 ± 0.4	$0.4\pm0.3^{\star}$	* alternatively rounded				

Part No.		ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J [h8]	Housing-ø D _H [H7]	Bush i-ø D _{1m} machined to H7	Clearance C _D	Oil hole-ø d _L					
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.						
MB 1615 HX			15.25 14.75											
MB 1620 HX	16	18	20.25 19.75		15.950 15.923	18.018 18.000	16.018 16.000							
MB 1625 HX			25.25 24.75	1.108				0.095						
MB 1815 HX			15.25 14.75	1.082				0.050						
MB 1820 HX	18	20	20.25 19.75		17.950 17.923	20.021 20.000	18.018 18.000							
MB 1825 HX			25.25 24.75						4					
MB 2010 HX			10.25 9.75											
MB 2015 HX			15.25 14.75											
MB 2020 HX	20	23	23	20.25 19.75		19.935 19.902	23.021 23.000	20.021 20.000						
MB 2025 HX			25.25 24.75											
MB 2030 HX			30.25 29.75											
MB 2215 HX							14.75	15.25 14.75						
MB 2220 HX	22	25	20.25 19.75		21.935	25.021	22.021							
MB 2225 HX		22 25	25.25 24.75	1.608 1.576	21.902	25.000	22.000							
MB 2230 HX			30.25 29.75											
MB 2415 HX			15.25 14.75		23.935									
MB 2420 HX	24	27	20.25 19.75			27.021 27.000	24.021 24.000							
MB 2425 HX			25.25 24.75		23.902			0.119 0.065						
MB 2430 HX			30.25 29.75											
MB 2515 HX			15.25 14.75						6					
MB 2520 HX	25	28	20.25 19.75		24.935	28.021	25.021							
MB 2525 HX	20	-0	25.25 24.75		24.902	28.000	25.000							
MB 2530 HX			30.25 29.75											
MB 2820 HX			20.25 19.75											
MB 2825 HX	28 32	25.25 24.75		27.935 27.902	32.025 32.000	28.021 28.000								
MB 2830 HX			30.25 29.75	2.108										
MB 3020 HX	30 34	20.25 19.75	2.072											
MB 3030 HX		34	30.25 29.75		30.000 29.967	34.025 34.000								
MB 3040 HX			40.25 39.75											

10 Standard Products


Part No.		ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J [h8]	Housing-ø D _H [H7]	Bush i-ø D _{1m} machined to H7	Clearance C _D	Oil hole-ø d _L																	
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.																		
MB 3220 HX			20.25 19.75																							
MB 3230 HX	32	36	30.25 29.75		31.920	36.025	32.025																			
MB 3235 HX	52	50	35.25 34.75		31.881	36.000	32.000																			
MB 3240 HX			40.25 39.75						6																	
MB 3520 HX			20.25 19.75						Ū																	
MB 3530 HX	35	39	30.25 29.75	2.108	34.920 34.881	39.025 39.000	35.025 35.000																			
MB 3550 HX			50.25 49.75	2.072																						
MB 3720 HX	37	41	20.25 19.75		36.920 36.881	41.025 41.000	37.025 37.000																			
MB 4020 HX			20.25 19.75																							
MB 4030 HX	40	44	30.25 29.75		39.920	44.025	40.025	0.144 0.080																		
MB 4040 HX			40.25 39.75		39.881	44.000	40.000																			
MB 4050 HX			50.25 49.75																							
MB 4520 HX											20.25 19.75															
MB 4530 HX			30.25 29.75																							
MB 4540 HX	45	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	50	40.25 39.75		44.920 44.881	50.025 50.000	45.025 45.000		
MB 4545 HX			45.25 44.75																							
MB 4550 HX			50.25 49.75																							
MB 5040 HX	50	55	40.25 39.75		49.920	55.030	50.025																			
MB 5060 HX			60.25 59.75		49.881	55.000	50.000		8																	
MB 5520 HX			20.25 19.75																							
MB 5525 HX			25.25 24.75	2.634 2.588																						
MB 5530 HX	55	60	30.25 29.75		54.900	60.030	55.030																			
MB 5540 HX			40.25 39.75		54.854	60.000	55.000																			
MB 5550 HX			50.25 49.75					0.176																		
MB 5560 HX			60.25 59.75					0.100																		
MB 6030 HX			30.25 29.75																							
MB 6040 HX	60 6	65	40.25 39.75		59.900 59.854	65.030	60.030 60.000																			
MB 6060 HX		65	60.25 59.75			65.000																				
MB 6070 HX			70.25 69.75																							


Part No.		ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J [h8]	Housing-ø D _H [H7]	Bush i-ø D _{1m} machined to H7	Clearance C _D	Oil hole-ø d _L
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
MB 6540 HX			40.25 39.75						
MB 6550 HX	05	70	50.25 49.75		64.900	70.030	65.030		
MB 6560 HX	65	70	60.25 59.75		64.854	70.000	65.000		
MB 6570 HX			70.25 69.75						
MB 7040 HX			40.25 39.75						8
MB 7050 HX			50.25 49.75						
MB 7065 HX	70	75	65.25 64.75		69.900 69.854	75.030 75.000	70.030 70.000		
MB 7070 HX			70.25 69.75					0.176	
MB 7080 HX			80.25 79.75					0.100	
MB 7540 HX			40.25 39.75						
MB 7560 HX	75	80	60.25 59.75		74.900 74.854	80.030 80.000	75.030 75.000		
MB 7580 HX			80.25 79.75						
MB 8040 HX			40.50 39.50						
MB 8060 HX	80	85	60.50 59.50		79.900	85.035	80.030		
MB 8080 HX			80.50 79.50	2.634 2.568	79.854	85.000	80.000		
MB 80100 HX			100.50 99.50						
MB 8530 HX			30.50 29.50	2.300					
MB 8540 HX			40.50 39.50						
MB 8560 HX	85	90	60.50 59.50		84.880 84.826	90.035 90.000	85.035 85.000		
MB 8580 HX			80.50 79.50						
MB 85100 HX			100.50 99.50						9.5
MB 9040 HX			40.50 39.50						
MB 9060 HX	90	95	60.50 59.50		89.880 89.826	95.035 95.000	90.035 90.000		
MB 9090 HX			90.50 89.50 100.50		03.020	33.000	30.000	0.209 0.120	
MB 90100 HX			99.50 60.50					0.120	
MB 9560 HX	95	100	59.50 100.50		94.880 94.826	100.035 100.000	95.035 95.000		
MB 95100 HX			99.50 50.50		0		00.000		
MB 10050 HX			49.50 60.50						
MB 10060 HX			59.50 80.50		99.880	105.035	100.035		
MB 10080 HX	100	105	79.50 95.50		99.880	105.000	100.000		
MB 10095 HX		93.50 94.50 115.50							
MB 100115HX			115.50						

10 Standard Products

Part No.		ninal ze	Length B	Wall thickness S ₃	Shaft-ø D _J [h8]	Housing-ø D _H [H7]	Bush i-ø D _{1m} machined to H7	Clearance C _D	Oil hole-ø d _L		
	Di	Do	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.			
MB 10560 HX			60.50 59.50								
MB 105110 HX	105	110	110.50 109.50		104.880 104.826	110.035 110.000	105.035 105.000				
MB 105115 HX			115.50 114.50								
MB 11060 HX	110	115	115	115	60.50 59.50		109.880	115.035	110.035		
MB 110115 HX		110	115.50 114.50	2.634	109.826	115.000	105.000	0.209 0.120	9.5		
MB 11550 HX	115	120	50.50 49.50	2.568	114.880	120.035	115.035		0.0		
MB 11570 HX			70.50 69.95		114.826	120.000	115.000				
MB 12060 HX	120	125	60.50 59.50 100.50 99.50		119.880	125.040	120.035				
MB 120100 HX					119.826	125.000	120.000				
MB 125100 HX	125	130	100.50 99.50		124.855 124.792	130.040 130.000	125.040 125.000				
MB 13050 HX			50.50 49.50								
MB 13060 HX	130	135	60.50 59.50		129.855 129.792	135.040 135.000	130.040 130.000				
MB 130100 HX			100.50 99.50								
MB 13560 HX	135	140	60.50 59.50		134.855	140.040	135.040				
MB 13580 HX			80.50 79.50	2.619	134.792	140.000	135.000	0.248 0.145	-		
MB 14060 HX	140	145	60.50 59.50	2.564	139.855	145.040	140.040				
MB 140100 HX			100.50 99.50		139.792	145.000	140.000				
MB 15060 HX			60.50 59.50								
MB 15080 HX	150	155	80.50 79.50		149.855 149.792	155.040 155.000	150.040 150.000				
MB 150100 HX			100.50 99.50								

10.3HX Thrust Washers






Part No.	Inside-ø D _i	Outside-ø D _o	Thickness S _T	Dowel hole PCD-ø d _P	Dowel hole-ø d _D	Recess depth T _a
Part NO.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.
WC10HX	12.25 12.00	24.00 23.75		18.12 17.88	1.875 1.625	
WC12HX	14.25 14.00	26.00 25.75		20.12 19.88		
WC14HX	16.25 16.00	30.00 29.75		22.12 21.88	2.375 2.125	
WC16HX	18.25 18.00	32.00 31.75		25.12 24.88		
WC18HX	20.25 20.00	36.00 35.75		28.12 27.88		
WC20HX	22.25 22.00	38.00 37.75	1.577	30.12 29.88	3.375	1.20
WC22HX	24.25 24.00	42.00 41.75	1.487	33.12 32.88	3.125	0.95
WC24HX	26.25 26.00	44.00 43.75		35.12 34.88		
WC25HX	28.25 28.00	48.00 47.75		38.12 37.88		
WC30HX	32.25 32.00	54.00 53.75		43.12 42.88		
WC35HX	38.25 38.00	62.00 61.75		50.12 49.88	4.375	
WC40HX	42.25 42.00	66.00 65.75		54.12 53.88	4.125	
WC45HX	48.25 48.00	74.00 73.75	2.600	61.12 60.88		1.70
WC50HX	52.25 52.00	78.00 77.75	2.510	65.12 64.88		1.45

10 Standard Products

10.4HX Strip

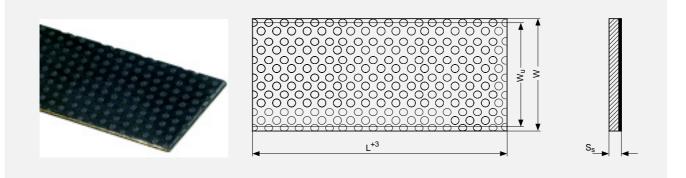

Group No.	Length	Total width	Usable Width	Thickness S _S
	L	W	Wu	max. min.
S100 90 HX		102	93	1.07 1.03
S152 00 HX	500	210	200	1.56 1.52
S202 00 HX	500		240	2.05 2.01
S252 00 HX		227	218	2.57 2.52

Glacier Garlock Bearings warrants that products described in this brochure are free from defects in workmanship and material but unless expressly agreed in writing Glacier Garlock Bearings gives no warranty that these products are suitable for any particular purpose of for use under any specific conditions notwithstanding that such purpose would appear to be covered by this publication. Glacier Garlock Bearings accepts no liability for any loss, damage, or expense whatsoever arising directly or indirectly from use of its products. All business undertaken by Glacier Garlock Bearings is subject to its standard Conditions of Sale, copies of which are available upon request. Glacier Garlock Bearings products are subject to continual development and Glacier Garlock Bearings reserves the right to make changes in the specification and design of its products without prior notice.

GLACIERTM is a Trademark of the EnPro Industries Inc., USA.

 $Hi-eX^{TM}$ is a Trademark of the EnPro Industries Inc., USA.

DSTM is a Trademark of the EnPro Industries Inc., USA.

This handbook was designed by Profidoc Silvia Freitag

www.profidoc.de